

extract of sample A, respectively, in the presence of S9 mix. Although the values of MI indicated no cytotoxicity, the ratio of live cells to total cells on the preparation was around 50% and 10%, respectively. Actually a few remaining live cells on the preparation of 40% extract of sample A were well and the chromosome morphology of the metaphase cells was fine.

Numerical chromosome aberrations consist of polyploidy and aneuploidy. Aneuploidy has been implicated in sterility, abortions, stillbirths, congenital abnormalities, and carcinogenesis.^{22,23} The *in vitro* CA test is not routinely used to detect aneuploidy, although it could be,²⁴ but polyploid induction suggests the possibility of aneuploid induction. In the present study, sample A, which had a high concentration of MBT, induced a high frequency of polyploidy in the presence of S9 mix. MBT alone at the same concentration also induced polyploidy, but with a lower frequency and with accompanying endoreduplication. Thus, the induction of polyploidy by sample A did not seem to be explained simply by the presence of MBT.

Endoreduplication, which shows an characteristic morphology (diplochromosomes), is an endomitotic chromosome duplication that occurs without mitosis-like events during interphase.²⁵ A typical endoreduplication event is characterized by two periods of DNA synthesis, S1 and S2, separated by a G period of variable duration.²⁶ Some chemicals, such as 4NQO, acridine yellow, cytoxan, captan,²⁷ and rotenone,²⁸ induce endoreduplication without S9 mix. The frequency of endoreduplication induced by those compounds was similar to the frequency induced by MBT in the present study.

The fact that sample A showed stronger cytotoxicity and induced a higher frequency of polyploidy than was predicted by MBT alone might have been due to the presence of other leachables in the sample. This suggests that sample A may be useful as a positive control for the safety evaluation of biomaterials and that the test might overcome the poor predictive value of individual components of materials.

In the Japanese guidelines for basic biological tests of medical materials and devices, the use of V79 cells is preferred in the cytotoxicity test. In the test the introduction of a metabolic activation system is not required. On the other hand, genotoxicity tests require the use of an exogenous metabolic activation system and of their methods following Japanese guidelines for drugs and chemicals, and OECD guidelines. CHL cells are popular in the CA test in Japan. In the present study each of the cytotoxicity test and the CA test followed the corresponding guideline independently. The difference in the cytotoxicity of sample A between with and without S9 mix suggests that the discussion of the introduction of an exogenous metabolic activation system into the cytotoxicity test may be needed.

References

1. MHW Notification YAKUKI No 99 (1995. 6. 27). Guidelines for basic biological tests of medical materials and devices.
2. Ikarashi Y, Toyoda K, Ohsawa N, Uchima T, Tsuchiya T, Kaniwa M, Sato M, Takahashi M, Nakamura A. Comparative studies by cell culture and *in vivo* implantation test on the toxicity of natural rubber latex materials. *J Biomed Mater Res* 1992;26:339-356.
3. Crippa M, Belleri L, Mistrello G, Carsana T, Neri G, Alessio L. Prevention of latex allergy among health care workers: evaluation of the extractable latex protein content in different types of medical gloves. *Am J Ind Med* 2003;44:24-31.
4. Yip ES. Accommodating latex allergy concerns in surgical settings. *AORN J* 2003;78:595-598, 601-603.
5. Acero S, Alvarez MJ, Garcia BE, Echechipia S, Olaguibel JM, Tabar AI. Occupational asthma from natural rubber latex. Specific inhalation challenge test and evolution. *J Invest Allergol Clin Immunol* 2003;13:155-161.
6. Ruutu M, Alfthan O, Heikkinen L, Järvinen A, Lehtonen T, Merikallio E, Standertskjöld-Nordenstam CG. "Epidemic" of acute urethral stricture after open-heart surgery. *Lancet* 1982; 1:218.
7. Smith JM, Neligan M. Urethral strictures after open heart surgery [letter]. *Lancet* 1982;1:392.
8. Fraser ID, Beaton NR, McGinn EP. Catheters and postoperative urethral stricture [letter]. *Lancet* 1982;1:622.
9. Syme RR. Epidemic of acute urethral stricture after prostate surgery. *Lancet* 1982;2:925.
10. Ruutu M, Alfthan O, Heikkinen L, Järvinen A, Konttinen M, Lehtonen T, Merikallio E, Standertskjöld-Nordenstam CG. Unexpected urethral strictures after short-term catheterization in open-heart surgery. *Scand J Urol Nephrol* 1984;18:9-12.
11. Nakamura A, Kanazawa Y, Sato H, Tsuchiya T, Ikarashi T, De Jong WH, Andersen KE, Knudsen B. Evaluation of allergic potential of rubber products: comparison of sample preparation methods for the testing of polymeric medical devices. *J Toxicol* 2003;22:169-185.
12. Elkind MM, Sutton H. Radiation response of mammalian cells grown in culture. I. Repair of X-ray damage in surviving Chinese hamster cells. *Radiat Res* 1960;13:556-593.
13. Koyama H, Utakoji T, Ono T. A new cell line derived from newborn Chinese hamster lung tissue. *Gann* 1970;61:161-167.
14. Ishidate M Jr, Odashima S. Chromosome tests with 134 compounds on Chinese hamster cells *in vitro* - a screening for chemical carcinogens. *Mutat Res* 1977;48:337-354.
15. Matsuoka A, Hayashi M, Ishidate M Jr. Chromosomal aberration tests on 29 chemicals combined with S9 mix *in vitro*. *Mutat Res* 1979;66:277-290.
16. Matsuoka A, Sofuni T, Miyata N, Ishidate M Jr. Clastogenicity of 1-nitropyrene, fluorene, and mononitrofluorenes in cultured Chinese hamster cells. *Mutat Res* 1991;259:103-110.
17. Nakamura A, Ikarashi Y, Tsuchiya T, Kaniwa MA, Sato M, Toyoda K, Takahashi M, Ohsawa N, Uchima T. Correlations among chemical constituents, cytotoxicities and tissue responses: in the case of natural rubber latex materials. *Biomaterials* 1990;11:92-94.
18. Tinkler J, Gott D, Bootman J. Risk assessment of dithiocarbamate accelerator residues in latex-based medical devices: genotoxicity considerations. *Food Chem Toxicol* 1998;36:849-866.
19. Hedenstedt A, Rannug U, Ramel C, Wachtmeister CA. Mutagenicity and metabolism studies on 12 thiuram and dithiocarbamate compounds used as accelerators in the Swedish rubber industry. *Mutat Res* 1979;68:313-325.
20. Rannug A, Rannug U, Ramel C. Genotoxic effects of additives in synthetic elastomers with special consideration to the mechanism of action of thiurams and dithiocarbamates. *Prog Clin Biol Res* 1984;141:407-419.

21. Anderson BE, Zeiger E, Shelby MD, Resnick MA, Gulati DK, Ivett JL, Loveday KS. Chromosome aberration and sister chromatid exchange test results with 42 chemicals. *Environ Mol Mutagen* 1990;16(suppl 18):55-137.
22. Barrett JC, Oshimura M, Tanaka N, Tsutsui T. Role of aneuploidy in early and late stage of neoplastic progression of Syrian hamster embryo cells in culture. In: Hollaender A, editor. *Aneuploidy-etiology and mechanisms*. New York: Plenum Press; 1985. p 523-538.
23. Oshimura M, Barrett JC. Chemically induced aneuploidy in mammalian cells: mechanisms and biological significance in cancer. *Environ Mutagen* 1986;8:129-159.
24. Matsuoka A, Ozaki M, Takeshita K, Sakamoto H, Glatt HR, Hayashi M, Sofuni T. Aneuploidy induction by benzo[a]pyrene and polyploidy induction by 7,12-dimethylbenz[a]anthracene in Chinese hamster cell lines V79-MZ and V79. *Mutagenesis* 1997;12:365-372.
25. Levan A, Hauschka TS. Endomitotic reduplication mechanisms in ascites tumors of the mouse. *J Natl Cancer Inst* 1953;14:1-43.
26. Rizzoni M, Palitti F. Regulatory mechanism of cell division, I. Colchicine-induced endoreduplication. *Exp Cell Res* 1973;77:450-458.
27. Sutou S, Tokuyama F. Induction of endoreduplication in cultured mammalian cells by some chemical mutagens. *Cancer Res* 1974;34:2615-2623.
28. Matsumoto K, Ohta T. Rotenone induces aneuploidy, polyploidy and endoreduplication in cultured Chinese hamster cells. *Mutat Res* 1991;263:173-177.

Enhancement of Gap Junctional Intercellular Communication of Normal Human Dermal Fibroblasts Cultured on Polystyrene Dishes Grafted with Poly-*N*-isopropylacrylamide

TSUTOMU NAGIRA, Ph.D.,^{1,2} SUSAN BIJOO MATTHEW, Ph.D.,¹
YOKO YAMAKOSHI, Ph.D.,³ and TOSHIE TSUCHIYA, Ph.D.¹

ABSTRACT

Technology developed to allow recovery of cells without enzyme treatment, involving a dish grafted with a thermoreactive polymer gel of poly-*N*-isopropylacrylamide (PIPAAm), was found to significantly enhance gap junctional intercellular communication (GJIC) in normal human dermal fibroblasts (NHDF cells). NHDF cells were cultured for 4 days on PIPAAm-grafted dishes irradiated with various doses of electron beams, and GJIC was assayed by the scrape-loading dye transfer method. The area of dye transfer was greater in the PIPAAm-grafted dishes than in the control culture dishes, indicating that the PIPAAm-grafted dishes enhanced the GJIC of NHDF cells. Connexin-43 (Cx43) expression was analyzed because Cx43 is considered to be a main component of the gap junctional channel. PIPAAm-grafted dishes irradiated with 100, 250, or 500 kGy of electron beams showed significantly enhanced expression of Cx43-NP, Cx43-P1, and especially Cx43-P2. Enhanced expression of Cx43-P2, a functional transmembrane protein, may be related to the promotion of GJIC. These results suggest that the PIPAAm-grafted dish not only enables the enzyme-free recovery of a cell monolayer for use in the construction of a three-dimensional artificial tissue, but also significantly contributes to the enhancement of GJIC, which may partly promote tissue strength on the surface of the PIPAAm-grafted dish.

INTRODUCTION

GAP JUNCTIONS exist on the cell membrane and work as intercellular channels that allow the exchange of substances with molecular masses up to 1 kDa, such as ions, sugars, and amino acids, by the function called gap junctional intercellular communication (GJIC).¹⁻³ Gap junctions are constructed from transmembrane proteins, called connexins,^{4,5} that form a hemichannel, called a connexon. GJIC is suggested to be well correlated with passage of metabolites,⁶ cell proliferation,⁷ and cell dif-

ferentiation⁸; thus, enhancement of the function of the gap junction is supposed to be important in the differentiation of engineered tissue products, such as those involving heart cells.⁹⁻¹¹ Poly-*N*-isopropylacrylamide (PIPAAm)-grafted dishes, which were originally developed as a thermosensitive scaffold for cell culture, are useful to maintain the GJIC of tissues cultured on them because they do not require enzyme treatment, which destroys connexins.¹²⁻¹⁴

PIPAAm is a thermoresponsive polymer that has a low critical solution temperature of 32°C: hydrated PIPAAm

¹Division of Medical Devices, National Institute of Health Sciences, Tokyo, Japan.

²Japan Association for the Advancement of Medical Equipment, Tokyo, Japan.

³Center for Polymers and Organic Solids, Department of Chemistry and Biochemistry, University of California, Santa Barbara, Santa Barbara, California.

has an extended chain conformation below 32°C and dehydrated PIPAAm has a collapsed chain conformation above 32°C.¹⁵⁻²⁷ This property of PIPAAm has been exploited in intelligent materials for drug delivery systems and chromatography technology.¹⁶⁻²³ The PIPAAm-grafted dish has been found to enable the recovery of cell monolayers easily without enzyme treatment because cells cannot adhere to a hydrophilic surface below 32°C.²⁴⁻²⁶ Cell monolayers are the basic units used to construct three-dimensional tissues *in vitro*. Because a cell monolayer recovered without enzyme treatment maintains normal adhesive and junctional proteins, it can easily adhere to the other tissues or cell sheets to construct a three-dimensional artificial tissue.²⁷⁻²⁹ Thus, the PIPAAm-grafted dish has the potential to enable the development of new techniques in tissue engineering.

Although the PIPAAm-grafted dish has made a new era in tissue engineering possible, its effects on connexin-43 (Cx43) expression and GJIC have not been studied well. These effects are important because Cx43 plays an important role in cell proliferation and cell differentiation.

In this study, GJIC and expression of Cx43 molecules were examined by scrape-loading dye transfer (SLDT) assay³⁰ and Western blotting, respectively, using NHDF cells cultured on PIPAAm-grafted dishes irradiated with various doses of electron beams in order to clarify the safety and appropriateness of this material for the culture of artificial cultured tissues.

MATERIALS AND METHODS

Materials

N-isopropylacrylamide monomer (NIPAAm) was purchased from Wako Pure Chemical Industries (Osaka,

Japan). Isopropyl alcohol was obtained from Dojindo (Kumamoto, Japan), and Lucifer yellow dye was from Molecular Probes (Eugene, OR).

Cell culture

Normal human dermal fibroblasts (NHDF cells; Sanko Junyaku, Tokyo, Japan) were cultured in Dulbecco's modified Eagle's medium (GIBCO DMEM; Invitrogen, San Diego, CA), supplemented with 10% heat-inactivated fetal calf serum (FCS; Invitrogen) and antibiotics (penicillin [100 units/mL]-streptomycin [100 units/mL]) (Invitrogen) at 37°C. NHDF cells were maintained in a humidified atmosphere of 5% CO₂ and 95% air.

Preparation of PIPAAm-grafted culture dishes

One hundred microliters of 40% NIPAAm dissolved in isopropyl alcohol was added to 35-mm dishes and irradiated with various doses of electron beams (25, 100, 250, or 500 kGy), using an area electron beam-processing system (Nissin High Voltage, Kyoto, Japan). The PIPAAm-grafted dishes were then rinsed three times with ice-cold sterile water (2 ml) for 5 min, sealed, and dried under vacuum.

Cell morphology

NHDF cells were cultured on control and PIPAAm-grafted dishes. Confluent cells (after 4 days of culture) were fixed with formalin solution, stained with 3% Giemsa solution, and observed with an optical microscope.

Protein assay

The protein concentration of cells cultured on control and PIPAAm-grafted dishes was measured with a bicinchoninic acid (BCA) protein assay kit (Pierce Biotechnology, Rockford, IL). Ten-microliter cell samples were

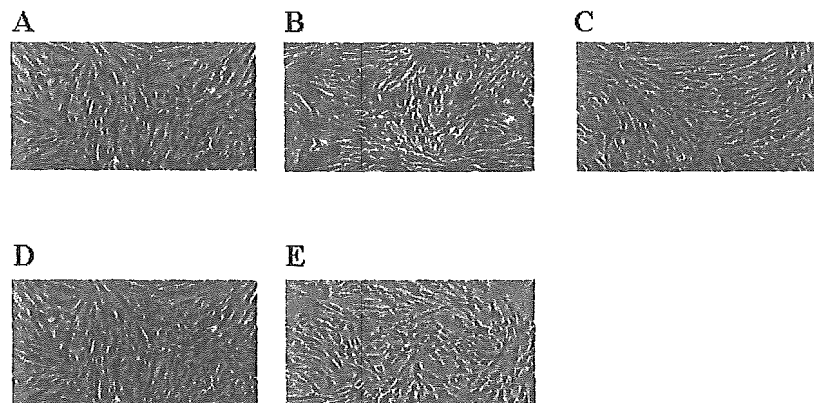


FIG. 1. Optical microscopy images of NHDF cells cultured on PIPAAm-grafted dishes. NHDF cells were cultured for 4 days on PIPAAm-grafted dishes prepared by irradiation with various doses of electron beams (0, 25, 100, 250, or 500 kGy). (A) Non-irradiated; (B) 25-kGy electron beam; (C) 100-kGy electron beam; (D) 250-kGy electron beam; (E) 500-kGy electron beam.

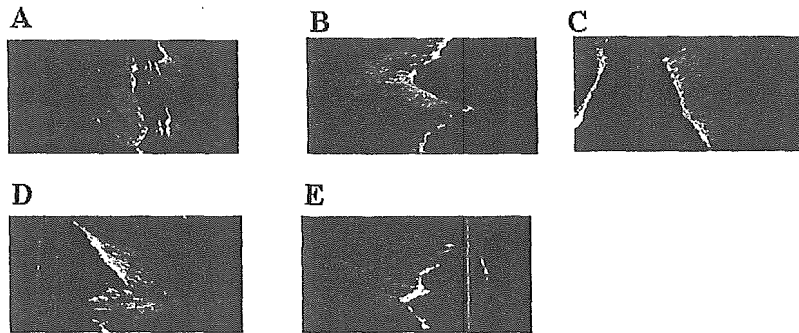


FIG. 2. Fluorescence of NHDF cells by SLDT assay. Transmission of Lucifer yellow into NHDF cells cultured on PIPAAm-grafted dishes irradiated with various doses of electron beams was detected 5 min after scrape-loading. (A) Nonirradiated; (B) 25-kGy electron beam; (C) 100-kGy electron beam; (D) 250-kGy electron beam; (E) 500-kGy electron beam.

added to 200 μL of the working solution and incubated at 37°C for 30 min in a 96-well plate. Absorbance was then measured at 562 nm in accordance with the manufacturer's protocols.

Scrape-loading dye transfer assay

NHDF cells were seeded on control and PIPAAm-grafted dishes at a density of 1×10^5 cells/mL and cultured for 4 days to form a confluent monolayer. Confluent NHDF cells were washed three times with phosphate-buffered saline containing Ca^{2+} and Mg^{2+} [PBS(+)], and the cell monolayer was scraped with a surgical blade. Fluorescent dye (Lucifer yellow; MW 457.2) at a concentration of 0.1% in PBS(+) was added.^{30,31} Cells were exposed to the dye at 37°C for 5 min, and then the dye was discarded and the cells were washed four times with PBS(+). The distance that the dye had migrated was measured under a fluorescence microscope equipped with a type UFX-DXII CCD camera and super high-pressure mercury lamp power supply (Nikon, Tokyo, Japan). The dye migration was measured from the cut edge of the scrape to the edge of the dye front in the cells that were visually detectable.³⁰

Western blotting

NHDF cells were cultured for 4 days. After being washed with ice-cold PBS(-) three times, the cells were lysed in 500 μL of lysis buffer (50 mM Tris-HCl [pH 6.8] containing 150 mM NaCl, 5 mM EDTA, 0.1 mM leupeptin, 1 mM phenylmethylsulfonyl fluoride, and 1% Nonidet P-40) for 30 min on ice with shaking. The cell lysates were centrifuged (10,000 rpm) at 4°C for 20 min, and the supernatants were collected. The protein concentrations of the lysates were determined by BCA assay.

Equivalent amounts of protein sample were applied to 12% sodium dodecyl sulfate (SDS)-polyacrylamide gels and then transferred to a nitrocellulose membrane at 120 V for 60 min. The membrane was blocked with Block

Ace (Yukijirusi, Tokyo, Japan) overnight at 4°C. After being washed for 30 min in PBS with 0.05% Tween 20, the membrane was incubated for 2 h with anti-Cx43 polyclonal antibody [diluted 1:1000 in PBS(-) with 0.05% Tween 20; Zymed Laboratories, South San Francisco, CA], followed by incubation with horseradish peroxidase (HRP)-conjugated goat anti-rabbit IgG secondary antibody (diluted 1:5000; Zymed Laboratories). The image was visualized with an enhanced chemiluminescence (ECL) detection kit (Amersham Biosciences/GE Healthcare, Little Chalfont, UK).

Statistical analysis

Significant differences between groups were evaluated by Student *t* test. Mean differences were considered significant when $p < 0.05$.

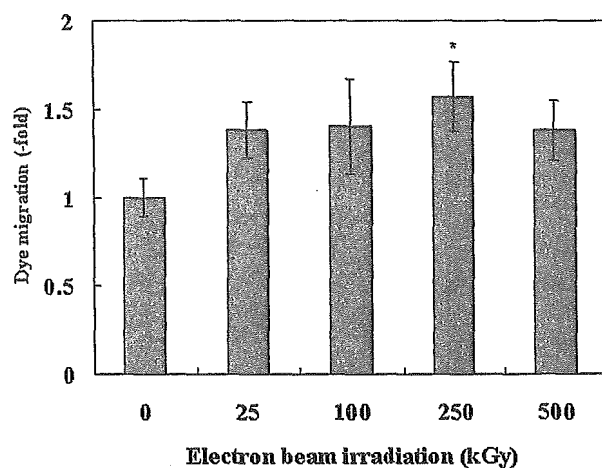


FIG. 3. Positive dye transfer in NHDF cells cultured on PIPAAm-grafted dishes. Transmission of Lucifer yellow was detected 5 min after scrape-loading in NHDF cells cultured on PIPAAm-grafted dishes irradiated with various electron beam doses (0, 25, 100, 250, or 500 kGy). Values represent means \pm SD for three dishes. *Significant difference compared with control at $p < 0.05$ by *t* test.

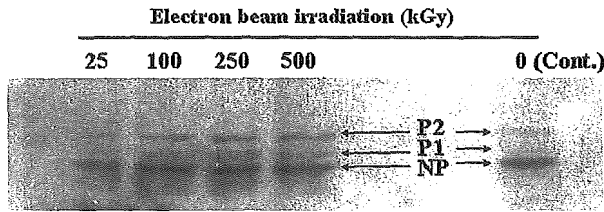


FIG. 4. Western blot of Cx43-NP, Cx43-P1, and Cx43-P2 expression; lysates of NHDF cells cultured on PIPAAm-grafted dishes irradiated with various doses of electron beams (0, 25, 100, 250, or 500 kGy) were applied to SDS-polyacrylamide gels. Fractionated proteins in the gels were transferred to nitrocellulose membrane and immunoblotted with anti-Cx43 polyclonal antibody as described in Material and Methods. Images of Cx43 on Western blot were captured with an Image scanner and analyzed with NIH Image software.

RESULTS

The appearance of NHDF cells grown on PIPAAm-grafted dishes irradiated with various doses of electron beams are shown in Fig. 1. No significant differences were observed by optical microscopy analysis between cells grown in dishes irradiated with various doses of electron beams. These results suggest that PIPAAm-grafted dishes are not toxic to NHDF cells.

The SLDT assay showed that dye migration in cells cultured on PIPAAm-grafted dishes irradiated with electron beams (25, 100, or 500 kGy) was enhanced by about 1.4-fold compared with that on control dishes. Interestingly, the dye migration in cells cultured on PIPAAm-grafted dishes irradiated with the 250-kGy electron beam was particularly enhanced, about 1.6 times higher than that on control dishes (Figs. 2 and 3). These results suggested that the GJIC of NHDF cells cultured on PIPAAm-grafted dishes was enhanced and that the GJIC on PIPAAm-grafted dishes irradiated with the 250-kGy electron beam was affected the most.

To further elucidate the effects of the PIPAAm grafting of culture dishes on GJIC, we analyzed the expression of Cx43, a transmembrane protein involved in GJIC. There are three forms of Cx43: Cx43-NP (nonphosphorylated Cx43), Cx43-P1 (monophosphorylated Cx43), and Cx43-P2 (another phosphorylated Cx43); Cx43-P2 is the most important and functional protein involved in GJIC. The results of Western blotting showed that the expression of Cx43-P1 and Cx43-P2 in NHDF cells cultured on PIPAAm-grafted dishes irradiated with 25, 100, 250, or 500 kGy of electron beams was considerably enhanced. Further, NHDF cells cultured on PIPAAm-grafted dishes irradiated with 100, 250, or 500 kGy of electron beams showed enhanced Cx43-NP expression (Figs. 4 and 5A). The Cx43-P2 expression of cells cultured on PIPAAm-grafted dishes irradiated with the 250-kGy electron beam dose showed the highest value, about 46% higher than that of control dishes. Cells cultured on PIPAAm-grafted dishes irradiated with electron beam doses of 25, 100, and 500 kGy were shown to have enhanced total Cx43 expression. Cells cultured on PIPAAm-grafted dishes irradiated with 100- and 250-kGy electron beam doses showed the highest total Cx43 expression, about 36.6% higher than that of control dish (Fig. 5B).

The Cx43-P2 expression of NHDF cells cultured on PIPAAm-grafted dishes irradiated with 25, 100, 250, and 500 kGy correlated well with GJIC ($R^2 = 0.9398$).

DISCUSSION

Thermoresponsive PIPAAm-grafted dishes irradiated with electron beams have been used to culture cell monolayers because the monolayers can be recovered without enzyme treatment, making PIPAAm a useful material for tissue engineering.

It has been reported that junctional proteins, cellular adherence proteins on the cell membrane, interact via

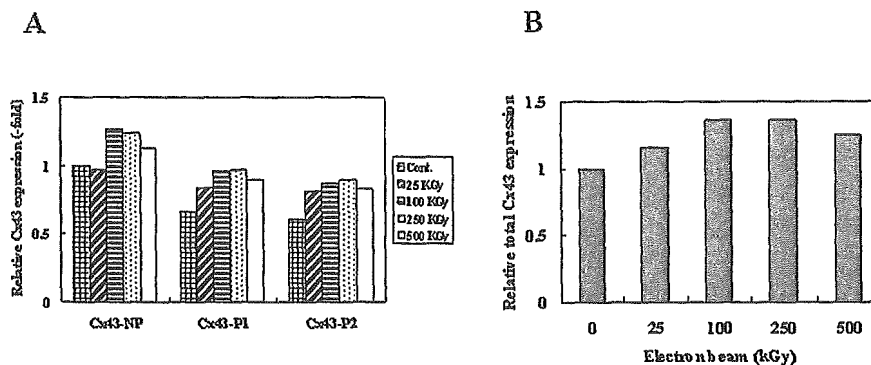


FIG. 5. Relative expression levels of Cx43-NP, Cx43-P1, and Cx43-P2 (A) and relative expression levels of total Cx43 (NP+P1+P2) (B) of NHDF cells cultured on PIPAAm-grafted dishes irradiated with various doses of electron beams (0, 25, 100, 250, or 500 kGy).

GJIC.³¹ In this study, an SLDT assay demonstrated that dye migration in cultured NHDF cells was significantly enhanced in all PIPAAm-grafted dishes tested. Therefore, the chemical structure of the PIPAAm surface may stimulate junctional proteins on the cell membrane, and the stimulated junctional proteins may induce the enhancement of GJIC.

Cx43 expression of NHDF cells cultured on PIPAAm-grafted dishes irradiated with a 250-kGy electron beam changed significantly. Structural differences in PIPAAm triggered by the 250-kGy electron beam induced Cx43 protein expression by NHDF cells, probably by affecting the gene expression of NHDF cells. Further, total Cx43 expression was shown to be enhanced in cells cultured on PIPAAm-grafted dishes irradiated with various doses of electron beams (25, 100, 250, or 500 kGy). Differences due to the electron beam dose should be studied further.

Although the mechanism involved was not determined, it has been reported that basic fibroblast growth factor (bFGF) and keratinocyte growth factor (KGF) enhance GJIC activity and the expression of Cx43.³²⁻³⁵ If bFGF and KGF in FCS are adsorbed onto the PIPAAm surface, cells can efficiently access these growth factors from the PIPAAm surface, and GJIC may be enhanced. It is also reported that bFGF activates protein kinase A (PKA),³⁶ an important regulator of Cx43, promoting the phosphorylation of Cx43 and enhancing GJIC.³⁷ Therefore, bFGF adsorbed onto the PIPAAm surface may bind its receptor and induce the activation of PKA, resulting in an enhancement of GJIC on NHDF cells caused by the increase in Cx43-P2 band protein.

In the process of posttranslational change, Cx43-P2 becomes insoluble in Triton X-100.³⁸ Thus, not all Cx43-P2 may be included in the lysate, and some Cx43-P2 may have been included in the pellet. More Cx43-P2 may have existed than was detected in the present results obtained by Western blotting.

In this study, it was shown that the use of PIPAAm-grafted dishes irradiated with various doses of electron beams enhanced GJIC and Cx43 expression in cultured NHDF cells. This suggests that PIPAAm-grafted dishes may promote efficient tissue regeneration, because GJIC plays an important role in increasing tissue strength.³⁹

ACKNOWLEDGMENTS

This work was supported in part by a Grant-in-Aid for Scientific Research on Advanced Medical Technology from the Ministry of Labor, Health, and Welfare, Japan and by a Grant-in-Aid from the Japan Human Sciences Foundation.

REFERENCES

- Giaume, C., Taberner, A., and Medina, J.M. Metabolic trafficking through astrocyte gap junctions. *Glia* **21**, 114, 1997.
- Abdullah, K.M., Luthra, G., Bilski, J.J., Abdullah, S.A., Reynolds, L.P., Redmer, D.A., and Grazul-Bilska, A.T. Cell-to-cell communication and expression of gap junctional proteins in human diabetic and nondiabetic skin fibroblasts. *Endocrine* **10**, 35, 1999.
- Grossman, H.B., Liebert, M., Lee, I.W., and Lee, S.W. Decreased connexin expression and intercellular communication in human bladder cancer cells. *Cancer Res.* **54**, 3062, 1994.
- Vera, B., Sanchez-Abarca, L.I., Bolanos, J.P., and Medina, J.M. Inhibition of astrocyte gap junctional communication by ATP depletion is reversed by calcium sequestration. *FEBS Lett.* **392**, 225, 1996.
- Bukauskas, F.F., Jordan, K., Bukauskiene, A., Bennett, M.V., Lampe, P.D., Laird, D.W., and Verselis, V.K. Clustering of connexin 43-enhanced green fluorescent protein gap junction channels and functional coupling in living cells. *Proc. Natl. Acad. Sci. U.S.A.* **97**, 2556, 2000.
- Giaume, C., Taberner, A., and Medina, J.M. Metabolic trafficking through astrocytic gap junctions. *Glia* **21**, 114, 1997.
- Taberner, A., Jimenez, C., Velasco, A., Giaume, C., and Medina, J.M. The enhancement of glucose uptake caused by the collapse of gap junction communication is due to an increase in astrocyte proliferation. *J. Neurochem.* **78**, 890, 2001.
- Tsuchiya, T. A useful marker for evaluating tissue-engineered products: Gap-junctional communication for assessment of the tumor-promoting action and disruption of cell differentiation in tissue-engineered products. *J. Biomater. Sci. Polym. Ed.* **11**, 947, 2000.
- Giaume, C., Marin, P., Cordier, J., Glowinski, J., and Preumont, J. Adrenergic regulation of intercellular communications between cultured striatal astrocytes from the mouse. *Proc. Natl. Acad. Sci. U.S.A.* **88**, 5577, 1991.
- Warn-Cramer, B.L., Cottrell, G.T., Burt, J.M., and Lau, A.F. Regulation of connexin-43 gap junctional intercellular communication by mitogen-activated protein kinases. *J. Biol. Chem.* **273**, 9188, 1998.
- Shimizu, T., Yamato, M., Isoi, Y., Akutsu, T., Setomaru, T., Abe, K., Kikuchi, A., Umezu, M., and Okano, T. Fabrication of pulsatile cardiac tissue grafts using a novel 3-dimensional cell sheet manipulation technique and temperature-responsive cell culture surfaces. *Circ. Res.* **22**, e40, 2002.
- Nandkumar, M.A., Yamato, M., Kushida, A., Konno, C., Hirose, M., Kikuchi, A., and Okano, T. Two-dimensional cell sheet manipulation of heterotypically co-cultured lung cells utilizing temperature-responsive culture dishes results in long-term maintenance of differentiated epithelial cell functions. *Biomaterials* **23**, 1121, 2002.
- Kushida, A., Yamato, M., Kikuchi, A., and Okano, T. Two-dimensional manipulation of differentiated Madin-Darby canine kidney (MDCK) cell sheets: The noninvasive harvest from temperature-responsive culture dishes and transfer to other surfaces. *J. Biomed. Mater. Res.* **54**, 37, 2001.
- Shimizu, T., Yamato, M., Akutsu, T., Shibata, T., Isoi, Y., Kikuchi, A., Umezu, M., and Okano, T. Electrically com-

- municating three-dimensional cardiac tissue mimic fabricated by layered cultured cardiomyocyte sheets. *J. Biomed. Mater. Res.* **60**, 110, 2002.
15. Takezawa, T., Mori, Y., and Yoshizato, K. Cell culture on a thermo-responsive polymer surface. *Biotechnology* **8**, 854, 1990.
 16. Chung, J.E., Yokoyama, M., Yamato, M., Aoyagi, T., Sakurai, Y., and Okano, T. Thermo-responsive drug delivery from polymeric micelles constructed using block copolymers of poly(*N*-isopropylacrylamide) and poly(butylmethacrylate). *J. Control. Release* **62**, 115, 1999.
 17. Chung, J.E., Yokoyama, M., and Okano, T. Inner core segment design for drug delivery control of thermo-responsive polymeric micelles. *J. Control. Release* **65**, 93, 2000.
 18. Kurisawa, M., Yokoyama, M., and Okano, T. Gene expression control by temperature with thermo-responsive polymeric gene carriers. *J. Control. Release* **69**, 127, 2000.
 19. Kobayashi, J., Kikuchi, A., Sakai, K., and Okano, T. Aqueous chromatography utilizing pH-/temperature-responsive polymer stationary phases to separate ionic bioactive compounds. *Anal. Chem.* **73**, 2027, 2001.
 20. Kikuchi, A., and Okano, T. Pulsatile drug release control using hydrogels. *Adv. Drug Deliv. Rev.* **54**, 53, 2002.
 21. Kanazawa, H., Sunamoto, T., Ayano, E., Matsushima, Y., Kikuchi, A., and Okano, T. Temperature-responsive chromatography using poly(*N*-isopropylacrylamide) hydrogel-modified silica. *Anal. Sci.* **18**, 45, 2002.
 22. Kobayashi, J., Kikuchi, A., Sakai, K., and Okano, T. Aqueous chromatography utilizing hydrophobicity-modified anionic temperature-responsive hydrogel for stationary phases. *J. Chromatogr. A* **958**, 109, 2002.
 23. Yoshizako, K., Akiyama, Y., Yamanaka, H., Shinohara, Y., Hasegawa, Y., Carredano, E., Kikuchi, A., and Okano, T. Regulation of protein binding toward a ligand on chromatographic matrixes by masking and forced-releasing effects using thermoresponsive polymer. *Anal. Chem.* **74**, 4160, 2002.
 24. Kikuchi, A., Okuhara, M., Karikusa, F., Sakurai, Y., and Okano, T. Two-dimensional manipulation of confluent cultured vascular endothelial cells using temperature-responsive poly(*N*-isopropylacrylamide)-grafted surfaces. *J. Biomater. Sci. Polym. Ed.* **9**, 1331, 1998.
 25. Kushida, A., Yamato, M., Konno, C., Kikuchi, A., Sakurai, Y., and Okano, T. Temperature-responsive culture dishes allow nonenzymatic harvest of differentiated Madin-Darby canine kidney (MDCK) cell sheets. *J. Biomed. Mater. Res.* **51**, 216, 2000.
 26. Shimizu, T., Yamato, M., Kikuchi, A., and Okano, T. Two-dimensional manipulation of cardiac myocyte sheets utilizing temperature-responsive culture dishes augments the pulsatile amplitude. *Tissue Eng.* **7**, 141, 2001.
 27. Hirose, M., Yamato, M., Kwon, O.H., Harimoto, M., Kushida, A., Shimizu, T., Kikuchi, A., and Okano, T. Temperature-responsive surface for novel co-culture systems of hepatocytes with endothelial cells: 2-D patterned and double layered co-cultures. *Yonsei Med. J.* **41**, 803, 2000.
 28. Yamato, M., Utsumi, M., Kushida, A., Konno, C., Kikuchi, A., and Okano, T. Thermo-responsive culture dishes allow the intact harvest of multilayered keratinocyte sheets without disperse by reducing temperature. *Tissue Eng.* **7**, 473, 2001.
 29. Harimoto, M., Yamato, M., Hirose, M., Takahashi, C., Isoi, Y., Kikuchi, A., and Okano, T. Novel approach for achieving double-layered cell sheets co-culture: Overlaying endothelial cell sheets onto monolayer hepatocytes utilizing temperature-responsive culture dishes. *J. Biomed. Mater. Res.* **62**, 464, 2002.
 30. el-Fouly, M.H., Trosko, J.E., and Chang, C.C. Scrape-loading and dye transfer: A rapid and simple technique to study gap junctional intercellular communication. *Exp. Cell Res.* **168**, 422, 1987.
 31. Defamie, N., Mograbi, B., Roger, C., Cronier, L., Malasine, A., Brucker-Davis, F., Fenichel, P., Segretain, D., and Pointis, G. Disruption of gap junctional intercellular communication by lindane is associated with aberrant localization of connexin43 and zonula occludens-1 in 42GPA9 Ser-toli cells. *Carcinogenesis* **22**, 1537, 2001.
 32. Pepper, M.S., and Meda, P. Basic fibroblast growth factor increases junctional communication and connexin 43 expression in microvascular endothelial cells. *J. Cell. Physiol.* **153**, 196, 1992.
 33. Nadarajah, B., Makarenkova, H., Becker, D.L., Evans, W.H., and Parnavelas, J.G. Basic FGF increases communication between cells of the developing neocortex. *J. Neurosci.* **18**, 7881, 1998.
 34. Park, J.U., and Tsuchiya, T. Increase in gap junctional intercellular communication by high molecular weight hyaluronic acid associated with fibroblast growth factor 2 and keratinocyte growth factor production in normal human dermal fibroblasts. *Tissue Eng.* **8**, 419, 2002.
 35. Doble, B.W., and Kardami, E. Basic fibroblast growth factor stimulates connexin-43 expression and intercellular communication of cardiac fibroblast. *Mol. Cell. Biochem.* **143**, 81, 1995.
 36. Pursiheimo, J.P., Jalkanen, M., Tasken, K., and Jaakkola, P. Involvement of protein kinase A in fibroblast growth factor-2-activated transcription. *Proc. Natl. Acad. Sci. U.S.A.* **97**, 168, 2000.
 37. Faucheux, N., Zahm, J.M., Bonnet, N., Legeay, G., and Nagel, M.D. Gap junction communication between cells aggregated on a cellulose-coated polystyrene: Influence of connexin 43 phosphorylation. *Biomaterials* **25**, 2501, 2004.
 38. Musil, L.C., and Goodenough, D.A. Biochemical analysis of connexin43 intracellular transport, phosphorylation, and assembly into gap junctional plaques. *J. Cell Biol.* **115**, 1357, 1991.
 39. Gutstein, D.E., Morley, G.E., Tamaddon, H., Vaidya, D., Schneider, M.D., Chen, J., Chien, K.R., Stuhlman, H., and Fishman, G.I. Conduction slowing and sudden arrhythmic death in mice with cardiac-restricted inactivation of connexin43. *Circ. Res.* **88**, 333, 2001.

Address reprint requests to:
Toshie Tsuchiya, Ph.D.
Division of Medical Devices
National Institute of Health Sciences
1-18-1 Kamiyoga
Setagaya-ku, Tokyo 158-8501, Japan

E-mail: tsuchiya@nihs.go.jp

F.Watari T.Akazawa M.Uo T.Akasaka

Archives of BioCeramics Research

Volume 5



Asian BioCeramics Symposium 2005

Sapporo, JAPAN

***In vitro* study on the osteogenesis of normal human osteoblasts cultured on the discs of various kinds of calcium phosphate ceramics**

Masato Tamai^{1, a}, Ryusuke Nakaoka^{1, b} and Toshie Tsuchiya^{1, c}

¹Division of Medical Devices, National Institute of Health Science

1-18-1 Kamiyoga, Setagaya-ku, Tokyo 158-8501 Japan

^am-tamai@nihs.go.jp, ^bnakaoka@nihs.go.jp, ^ctsuchiya@nihs.go.jp

Keywords: Calcium phosphate ceramics, osteogenesis, cytotoxicity,

Abstract. We estimated effects of various CP ceramics on the properties of normal human osteoblasts (NHOst) as well as a viability of V79 fibroblasts. In the present study, five kinds of CP ceramics, namely, hydroxyapatite (HAp) fluoroapatite (FAP), α -tricalcium phosphate (α -TCP), β -tricalcium phosphate (β -TCP) and tetracalcium phosphate (TTCP), were tested. Cytotoxicity test was carried out using V79 fibroblasts by colony assay system. The amounts differentiation level of NHOst was estimated from alkaline phosphatase (ALP) activity and osteocalcin.

From the results of colony assay, FAp and α -TCP showed strong cytotoxicities on V79 cells. The results from the proliferation studies of NHOst with CP ceramics were consistent with the results of colony assay. In addition, the ALP activities of NHOst with CP ceramics after 1 week culture were significantly suppressed in comparison with that of NHOst alone. The osteocalcin amounts produced from NHOst cultured on β -TCP was the highest among five kinds of CP ceramics.

Introduction

Calcium phosphate (CP) ceramics have been studied to utilize as the scaffolds for repairing bone defects. For instance, hydroxyapatite ($\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$, HAp) or β -tricalcium phosphate ($\beta\text{-Ca}_3(\text{PO}_4)_2$, β -TCP), can be biologically bonded to natural bones and their porous materials are effective for restoration of bone defects [1]. Fluoroapatite ($\text{Ca}_{10}(\text{PO}_4)_6\text{F}_2$, FAp) has been reported to have a potential of novel bone repairing materials with high stability *in vivo*, since solubility of FAp is lower than that of HAp [2]. In addition, CP cement is also promising for bone repair and it is well known that α -tricalcium phosphate ($\alpha\text{-Ca}_3(\text{PO}_4)_2$, α -TCP) or tetracalcium phosphate ($\text{Ca}_4(\text{PO}_4)_2\text{O}$, TTCP) are starting materials for the harden reaction of the bone cement [3].

To develop biomaterials for utilizing for bone tissue, various properties, e.g. biological, physical or chemical property, should be satisfied. Among them, biological safety and osteogenesis properties, e.g. proliferation and differentiation of the osteoblasts, should be important factors to provided to the biomaterials. However, understandings of the biological interaction between osteoblasts and various CP ceramics are few, since the interaction has not been studied under the same experimental condition in detail. Therefore, we estimated effects of various CP ceramics on the properties of normal human osteoblasts (NHOst) as well as a viability of V79 fibroblasts in this study.

Materials and Methods

Materials

Cytotoxicity and osteogenesis of NHOst on five kinds of CP ceramics, namely, HAp, FAp, α -TCP, β -TCP and TTCP (Wako chem. Co. Ltd., Tokyo, Japan), were evaluated. 0.25g of CP powders was put into stainless mold and uniaxially pressed at 30MPa for 1 min to form pellets. The dimensions of the obtained CP pellet were 1mm in thickness and 12mm in diameter. CP pellets were sterilized by the autoclave 121°C for 20 min.

Cytotoxicity test on CP ceramics

Cytotoxicity test was carried out using Chinese hamster V79 lung fibroblasts by the colony assay system. V79 cells were maintained in Eagle's minimum essential medium (Nissui Pharmaceutical Co. Ltd.) with 10% fetal calf serum (FCS, Intergen company) and incubated at 37 °C in a humidified atmosphere with 5% CO₂.

The method of cell seeding was shown below; At first, each CP pellets were placed in each culture wells of 24 well culture plates (Corning Co. Ltd.) and 300µl of culture medium was added into each well. Next, 50 cells/300µl of culture medium was added into each well and incubated for 4 h at 37°C. Finally, 400µl of culture medium was added and incubated at 37 °C in a humidified atmosphere with 5 % CO₂ for 7days.

In order to investigate the cell adhesive property on the CP ceramics, the culture medium was changed after cultivations for 4 h and incubated for 7days. The removed culture medium was transferred to another well of the plate and incubated for 7days as well.

Cytotoxicity of extracts from CP ceramics was also investigated in this study. Suspensions of CP ceramics in the culture medium (100mg/mL) were stirred at 37°C for 3days in 150rpm. The suspensions were centrifuged and the supernatants were collected to use as test extracts. The cytotoxicity test was carried out culturing 50 V79 cells in 1ml of the extracts and incubated at 37 °C for 7days.

After 7days, the cells were fixed in methanol and the number of the V79 colonies was counted after staining cells with 5%-Giemsa solution. In addition, the pH of the medium after 7-days culture was measured to estimate effect of the pH of the medium on the cytotoxicity test.

Osteogenesis evaluation of NHOst cultured on CP ceramics

NHOst were purchased from BioWhittaker Inc.(Walkersville,MD). The NHOst were maintained in alpha minimum essential medium (αMEM, Gibco, Grand Island, NY) containing 10%-FCS. incubators at 37 °C in a humidified atmosphere with 5% CO₂. All assays were performed using αMEM containing 10%-FCS supplemented with 10mM beta-glycerophosphate. Similar to the method of the cytotoxicity test, each CP pellets were placed in 24-well culture plates (Corning Co. Ltd.) and 300µl of culture medium was added into each well, followed by addition of 1ml of cell suspension (4×10^4 cells/ml) into each well.

Proliferation of NHOst cells cultured on various kinds of CP ceramics was estimated by Tetracolor One assay (Seikagaku Co., Ltd. Tokyo, Japan), which incorporates an oxidation reduction indicator based on detection of metabolic activity. After 7-days incubation, 2%-TetraColor One/αMEM solution was added to each well, followed by 2h incubation. The absorbance of the supernatant at 450nm was estimated using µQuant spectrophotometer (Bio-tek Instrument, Inc., Winooski, VT). After estimating the proliferation, the cells were washed by phosphate-buffered saline (PBS(-)), followed by addition of 1ml of 0.1M glycine buffer (pH=10.5) containing 10mM MgCl₂, 0.1mM ZnCl₂ and 4mM p-nitrophenylphosphate sodium salt. After incubating at room temperature for 5min, the absorbance of 405 nm of glycine buffer was detected using µQuant spectrophotometer to evaluated alkaline phosphatase (ALP) activity of the test cells. The amount of Osteocalcin produced by NHOst was evaluated using Gla-type Osteocalcin EIT kit (Takara. Co., Ltd.). The structural change of CP before and after autoclave sterilization or culture were investigated by powder X-ray diffraction (XRD) analysis and scanning electron microscopy(SEM). XRD analysis was carried out (Rigaku Co., Ltd. / RINT 2000) with the CuK_α radiation at 40kV, 50mA. SEM observations were performed (JEOL / JSM-5800LV) with an accelerating voltage of 25kV.

Results

Cytotoxicity of various CP ceramics

The results of the cytotoxicity test of CPs are summarized in table 1. Notably, the colonies were hardly formed on FAp and α -TCP pellets and the ratios of the colony formation against V79-alone culture were 22.6% and 0.0%, respectively. In addition, the ratios of the colony formation on the HAp, β -TCP and TTCP pellets were 58.1%, 57.3% and 78.4%, respectively. From these results, it is suggested that V79 cells were viable and adhered on the pellet after for 4h after seeding despite of the type of CP ceramics, irrespective of the type of CP ceramics. On the other hand, the cytotoxicity test of extracts from CPs revealed that the tendency of their cytotoxicity was almost the same as that of the respective CP pellets themselves (table1).

Proliferation and differentiation of NHOst cultured on CP ceramics

The effects of various kinds of CP ceramics on the osteogenesis of NHOst are represented in table2. The effects of the CPs on proliferation were consistent with those on the colony formation. Similar to the cytotoxicity test, the proliferation of NHOst was inhibited on FAp and α -TCP pellets. ALP activities of NHOst on CP ceramics after 7-days culture were significantly suppressed in comparison with that of NHOst alone. On the other hand, the osteocalcin amounts produced from NHOst were influenced by the type of CP ceramics. NHOst on β -TCP showed the highest Osteocalcin production among five kinds of CP ceramics.

4. Discussion

The fact that less formation of colonies was observed on FAp and α -TCP pellets suggests that they are strongly cytotoxic. It is suggested that the differences in the colony formation on various CP pellets are ascribed to difference in extract properties from the CP related with the composition or crystal structure (table1). In addition, proliferation of NHOst also was inhibited on FAp and α -TCP. The pH values of culture medium after incubation for 7 days are shown in table1. As shown in the table, the pH of culture medium after incubation with FAp pellets is almost the same as that of HAp, while the pH of the α -TCP medium is much lower than other CP ceramics. In order to considering the reason of the low pH of the culture medium with α -TCP pellet, a surface structural change of α -TCP before and after incubation was analyzed by SEM. SEM images of α -TCP after extraction treatment are shown in Fig.1.

Table1. Cytotoxicity test of various CP ceramics.

Samples	Composition	Formation of colony		pH of medium after culturing	Ca concentration ¹⁾ /ppm
		On pellets /%	Extraction / %		
V79 alone	-	100.0±4.5	100.0±13.9	7.12	-
HAp	Ca ₁₀ (PO ₄) ₆ (OH) ₂	58.1±12.8	84.6±15.1	7.24	0.19
FAp	Ca ₁₀ (PO ₄) ₆ F ₂	22.6±20.9**	26.9±8.6*	7.20	0.17
α -TCP	α -Ca ₃ (PO ₄) ₂	0.0*	7.6±5.1*	6.76	72.62
β -TCP	β -Ca ₃ (PO ₄) ₂	57.3±6.9	81.1±19.3	7.40	1.27
TTCP	Ca ₄ (PO ₄) ₂ O	78.2±5.0	93.7±6.8	7.65	0.58

*p<0.01 against V79 alone, **p<0.05 against V79 alone, 1)The Ca ions concentration was extracted Ca ions from CP-ceramics in PBS(-), which were measured by inductivity coupled plasma-atomic emission spectroscopy.

Table2. Osteogenesis of NHOst cultured on various kinds of CP ceramics.

Samples	Proliferation / %	Differentiation level	
		ALP activity / %	Osteocalcin / %
NHOst alone	100±7.9	100±4.4	100±46.2
HAp	63.2±3.5	20.4±1.8*	81.1±31.0
FAp	42.9±19.5	1.24±0.3*	47.2±20.7
α -TCP	18.3±2.5	17.9±3.8*	110.7±18.8
β -TCP	56.0±4.7	6.3±3.2*	177.1±78.4**
TTCP	82.3±27.3	17.5±4.6*	114.8±4.0

*p<0.01 against NHOst alone, **p<0.01 against HAp


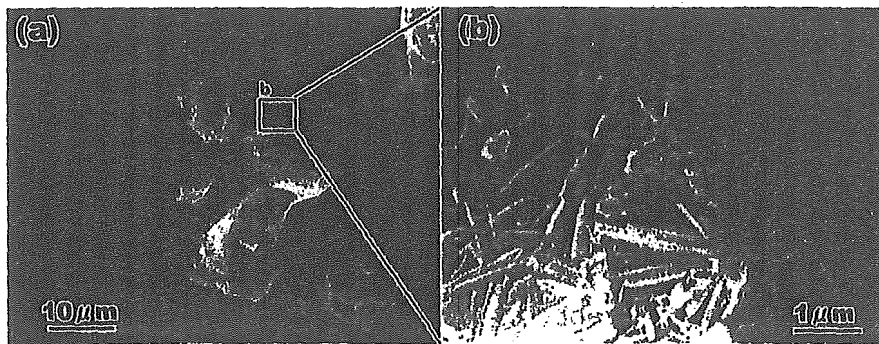


Fig.1. SEM images of α -TCP after extract treatment. (a) whole image and (b) enlarged image of the area enclosed by a rectangle in (a)

Before the extraction, a particle size of α -TCP was about $10\mu\text{m}$ and its surface was smooth. However, as shown in Fig.1, whisker-like precipitates of $1\text{-}2\mu\text{m}$ in length and $2\text{-}300\text{nm}$ in width are observed at the surface of α -TCP after the extraction, although there is no change in its particle size. It is well known that slightly water-soluble calcium phosphates convert to HAp in aqueous solution with high pH value. Since the solubility of α -TCP is higher than that of other calcium phosphates, the α -TCP converts to HAp rapidly as following the reaction.



According to the report of this conversion [4], HAp produced by the above reaction has whisker-like morphology. Therefore, the whisker-like precipitates can be regarded as HAp, so that it is considered that the above conversion occurs at the surface of the α -TCP during incubation. In this case, phosphoric acid is produced as a byproduct in the conversion reaction and the phosphoric acid caused the decrease in the pH of solution. Morita and co-workers [5] have reported that low pH itself could be clastogenic to mammalian cells and the pH of 50% V79 cell survival was 6.5 for 24h incubation. Therefore, it is suggested that the cytotoxicity of α -TCP was mainly due to the pH decreasing resulting from an increase of the phosphoric acid ion produced by the hydrolysis conversion from α -TCP to HAp.

On the other hand, FAp has the same crystal structure of HAp but the hydroxyl ions in HAp substituted by fluorine ions. Since difference of the colony formation on various CP ceramics would be due to eluted substances from CP as described above, the cytotoxicity of FAp would be due to eluted fluoride ions from FAp.

Effects of CP ceramics on osteogenesis function of NHOst are shown in table2. As shown in the table, ALP activities of NHOst were significantly suppressed on CP ceramics irrespective of their type and the amount of osteocalcin on β -TCP was the highest among five kinds of CP ceramics. Since it is well known that osteocalcin express in maturated stage of differentiation level of NHOst, these results suggest that maturation of NHOst proceeds on β -TCP. The differences of maturation of NHOst on various kinds of CP ceramics may be related with the amount of extracted Ca^{2+} and/or PO_4^{3-} ions.

References

- [1] Y. Ito, N. Tanaka, Y. Fujimoto, Y. Yasunaga, O. Ishida, M. Agung, M. and Ochi, J. Biomed. Mater. Res: Vol.69A(3) (2004) p454
- [2] K. Cheng K, W. Weng, H. Qu, P. Du, G. Shen, G. Han, J. Yang and M. J. Ferreira: J.Biomed. Mater. Res. B, Vol.69(1) (2004) p33
- [3] M. E. Ooms, J. G. C. Wolke, J. C. P. M. Waerden and J. A. Jansen, Trabecular, J.Biomed. Mater. Res. Vol.61 (2002) p9
- [4] M.Tamai, T.Isshiki, K.Nishio, M.Nakamura, A.Nakahira and H.Endoh: J. Mater. Res. Vol.18 (2003), p.2633
- [5] T.Morita, T.Nagaki, I.Fukuda and K.Okumura: Muta. Res. Vol.268 (1992), p.297

Cytotoxicity of Various Calcium Phosphate Ceramics Masato Tamai^{1a}, Ryusuke Nakaoka^{1b} and Toshie Tsuchiya^{1c}

Division of Medical Devices, National Institute of Health Science
1-18-1 Kamiyoga, Setagaya-ku, Tokyo 158-8501 Japan

^am-tamai@nihs.go.jp, ^bnakaoka@nihs.go.jp, ^ctsuchiya@nihs.go.jp

Keywords: Calcium phosphate ceramics, Cytotoxicity,

Abstract. The cytotoxicity of five calcium phosphate ceramics, hydroxyapatite (HAp), fluoroapatite (FAP), α -tricalcium phosphate (α -TCP), β -tricalcium phosphate (β -TCP) and tetracalcium phosphate (TTCP), was investigated. Based on the guidelines of biological test for medical devices in Japan, a cytotoxicity test of these calcium phosphates was carried out using Chinese hamster V79 lung fibroblasts. The cytotoxic study revealed that FAP and α -TCP showed high cytotoxicities. From various analyses, it was considered that the cytotoxicity of the FAP was due to fluorine ions extracted in a culture medium and the cytotoxicity of α -TCP resulted from a decrease in pH of the medium by the phosphoric acid, which produced by hydrolysis of the α -TCP.

Introduction

From the view point of biological affinity to bone, calcium phosphate (CP) ceramics have been studied to utilize for many purposes in a medical field. For instance, hydroxyapatite ($\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$, HAp) and β -tricalcium phosphate ($\beta\text{-Ca}_3(\text{PO}_4)_2$, β -TCP), are known to be biologically bonded to natural bones and their porous materials have been studied for effective restoration of bone defects.[1,2] Fluoroapatite ($\text{Ca}_{10}(\text{PO}_4)_6\text{F}_2$, FAP) has been reported to have a potential of novel bone repairing materials with high stability *in vivo*, since solubility of FAP is lower than that of HAp.[3,4] In addition, CP cement is also promising for bone repair and it is well known that α -tricalcium phosphate ($\alpha\text{-Ca}_3(\text{PO}_4)_2$, α -TCP) and tetracalcium phosphate ($\text{Ca}_4(\text{PO}_4)_2\text{O}$, TTCP) are starting materials for the harden reaction of the bone cement.[5,6]

To develop biomaterials for utilizing for bone tissue, various properties, e.g. biological, physical and chemical property, should be satisfied. Among them, biological safety is important for the biomaterials. Since only a few studies which discuss the cytotoxicity of calcium phosphate ceramics have been reported, the cytotoxicity of CP ceramics is worthy to be investigated in order to design bioceramics with good biological safety for medical application. Therefore, the cytotoxicities of five calcium phosphate ceramics, hydroxyapatite (HAp), fluoroapatite (FAP), α -tricalcium phosphate (α -TCP), β -tricalcium phosphate (β -TCP) and tetracalcium phosphate (TTCP) were investigated.

Materials and Methods

Materials

Five kinds of CP ceramics, HAp, FAP, α -TCP, β -TCP and TTCP were purchased from Wako chem. Co. Ltd. CP powders (0.25 g) was put into stainless mold and uniaxially pressed at 30MPa for 1 min to form a pellet. The dimensions of the obtained CP pellet were 1mm in thickness and 12mm in diameter. CP pellets were sterilized by an autoclave at 121°C for 20 min.

Cytotoxicity test on CP ceramics

Cytotoxicity test was carried out using Chinese hamster V79 lung fibroblasts by a colony assay system. V79 cells were maintained in Eagle's minimum essential medium (Nissui Pharmaceutical Co. Ltd.) with 10% fetal calf serum (FCS, Intergen Co. Ltd.) and incubated at 37°C in a humidified atmosphere with 5% CO_2 .

The method of cell seeding in the cytotoxicity test of CP ceramics was shown below; each CP pellets were placed in each culture wells of 24 well culture plates (Corning Co. Ltd.) and 300 μ l of culture medium was added into each well. Then, 50 cells/300 μ l of the cell suspension in the

culture medium were added into each well and incubated at 37°C for 4 h. Finally, 400µl of the culture medium was added into each well and the plates were incubated at 37°C in a humidified atmosphere with 5% CO₂ for 7 days. In order to investigate a cell adhesive property on the CP ceramics, the culture medium was changed after 4 h and further incubated for 7 days. The removed culture medium was transferred to another well of a new plate and incubated for 7 days as well.

Cytotoxicity of extracts from CP ceramics was also investigated in this study. Suspensions of CP ceramics in the culture medium (100mg/mL) were stirred at 37°C for 3 days under the rotation condition at 150rpm. The suspensions were centrifuged and the supernatants were collected as test extracts. In addition, media with various pH values were prepared using HCl solution to investigate an effect of pH on cell survival. Fifty V79 cells in 1ml of the extracts or the medium with different pH value were incubated at 37°C for 7 days.

After 7-day incubation, the cells were fixed in methanol and the number of the V79 colonies was counted after staining cells with 5%-Giemsa solution to estimate the cytotoxicity of the test sample. In addition, the pH of the medium after 7-days culture was measured to estimate the effect of the pH of the medium on the cytotoxicity test.

Characterization of CP ceramics

The structural changes of CP before and after an autoclave-sterilization or an incubation at 37°C culture were investigated by powder X-ray diffraction (XRD) analysis and scanning electron microscopy (SEM). XRD analysis was carried out (Rigaku Co., Ltd. / RINT 2000) with the CuK_α radiation at 40kV, 50mA. SEM observations were performed (JEOL / JSM-5800LV) with an accelerating voltage of 25kV.

Results and Discussion

Cytotoxicity of various CP ceramics

From XRD analysis, no structural changes of CPs were observed after an autoclave sterilization. After staining CP pellets, it was observed that cell colonies were formed on various CP ceramics pellets (Fig.1(a)). The results of the cytotoxicity test of CPs are shown in Fig.1(b). The cell colonies were hardly formed on FAp and α-TCP pellets and the ratios of the colonies formed on these pellets against V79-alone culture were 22.6% and 0.0%, respectively. In addition, the ratios of the colonies on the HAp, β-TCP and TTCP pellets were 58.1%, 57.3% and 78.4%, respectively. As no colonies were observed after 7-day culture of the removed medium in cell adhesion studies of CP ceramics, these results suggested that V79 cells can adhere and be viable on these pellets, irrespective of the type of CP ceramics. Figure 2 shows the formation of colonies cultured in extract from CP ceramics. The cytotoxicity test of extracts from CPs revealed that the tendency of their cytotoxicities was similar to that of the cytotoxicities on the respective CP pellets themselves (Fig.1(b)).

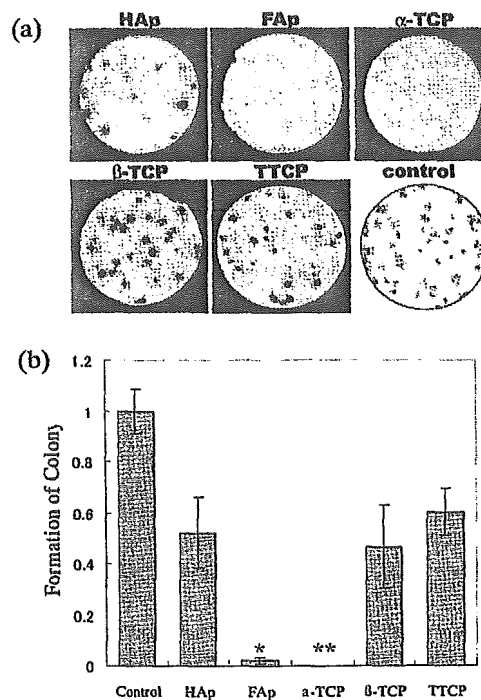


Fig.1. The appearance of colonies on various CP pellets (a) and their colony formation ratios (b). (*p<0.05 against for V79 alone, **p<0.01 against for V79 alone)

The fact that less formation of colonies was observed on FAp and α -TCP pellets suggests that they are highly cytotoxic. In addition to results shown in Fig.2, it is suggested that the differences in the colony formation ratio on various CP pellets are ascribed to difference in extract properties from the CP, which may be related with the composition or crystal structure. As shown in Table 1, the pH of culture medium after incubation with FAp pellets is almost the same as that of HAp, while the pH of the α -TCP-incubated medium is much lower than that of the other CP ceramics-incubated media. In order to consider the reason of the low pH of the α -TCP-incubated medium, a surface structural change of α -TCP before and after incubation was analyzed by SEM. SEM images of α -TCP before and after extraction treatment are shown in Fig.3. Before extraction, a particle size of α -TCP was about $10\mu\text{m}$ and its surface was smooth (Fig.3(a) and (b)). However, whisker-like precipitates of $1\text{-}2\mu\text{m}$ in length and $2\text{-}300\text{nm}$ in width were observed at the surface of α -TCP after the extraction, although there was no change in its particle size (Fig.3(c) and (d)). It is well known

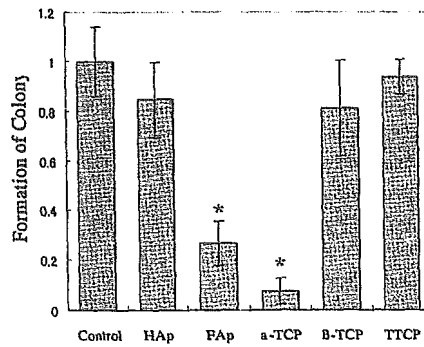


Fig.2. Formation of colony cultured in extract from various CP ceramics. (* $p < 0.01$ against for V79 alone)

Table 1. The pH and Ca concentration of culture medium after incubation.

Samples	pH of medium after culturing	Ca concentration /ppm
V79 alone	7.12	-
HAp	7.24	0.19
FAp	7.20	0.17
α -TCP	6.76	72.62
β -TCP	7.40	1.27
TTCP	7.65	0.58


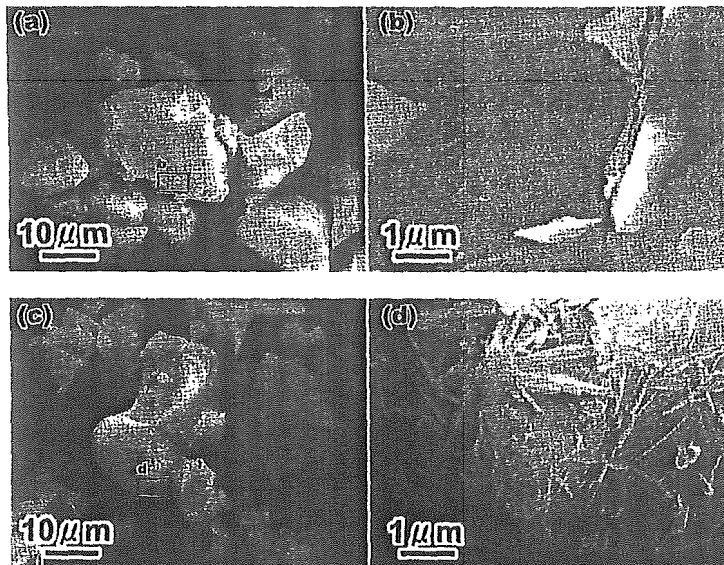


Fig.3. SEM images of α -TCP before (a), (b) and after extract treatment (c), (d). (a) and (c) are whole image of before and after extract treatment, respectively. (b) and (d) are enlarged image of the area enclosed by a rectangle in (a) and (c), respectively.

that calcium phosphates convert to HAp in aqueous solution with high pH value. Since the solubility of α -TCP is higher than that of other calcium phosphates, α -TCP rapidly converts to HAp as follows;



According to the report of this conversion [7], HAp produced by the above reaction has whisker-like morphology. Therefore, the whisker-like precipitates in Fig.3 (d) can be regarded as HAp, so that it is considered that the above conversion occurs at the surface of the α -TCP during incubation.

In this case, phosphoric acid is produced as a byproduct in the conversion reaction and the phosphoric acid causes the decrease in pH of the solution. As shown in Fig.4, Morita and co-workers[8] have reported that low pH itself could be clastogenic to mammalian cells and the pH of 50% V79 cell survival was 6.5 for 24h incubation. In the present colony assay system, the pH of 50% V79 cell survival was 6.9 for 7-days incubation. In addition, we confirmed that phosphoric acid showed no or weak cytotoxicities under our present experimental conditions. Therefore, it is suggested that the cytotoxicity of α -TCP is mainly due to the pH decrease resulting from an increase of the phosphoric acid ion by the hydrolysis conversion from α -TCP to HAp.

On the other hand, FAp has the same crystal structure of HAp but the hydroxyl ions in HAp substituted by fluorine ions. Since it is probable that difference of the colony formation on various CP ceramics are due to eluted substances from CP as described above, the cytotoxicity of FAp would be due to eluted fluoride ions from FAp. In conclusion, this study has revealed that FAp and α -TCP have a cytotoxicity, while TTCP has lower cytotoxicity than other calcium phosphates. To develop biomaterials made from calcium phosphate, further studies are necessary to clarify their cytotoxic mechanisms.

Acknowledgment

This study was supported in part by a Grant-in-Aid for Scientific Research on Advanced Medical Technology from Ministry of Labour, Health and Welfare, Japan and a Grant-in-Aid from Japan Human Sciences Foundations.

References

- [1] Y.Ito, N.Tanaka, Y.Fujimoto, Y.Yasunaga, O.Ishida, M.Agung and M.Ochi: *J. Biomed. Mater. Res.* Vol.69A (2004), p.454
- [2] Y.Wang, T.Uemiura, J.Dong, J.Tanaka and T.Tateishi: *Tissue Eng.* Vol.9 (2003), p.1205
- [3] S.M.Barinov, F.Rustichelli, P.V.Orlovskii, A.Lodini, S.Oscarsson, A.S.Firstov, V.S.Tumanov, P.Millet and A.Rosengren: *J.Mater.Sci:Mater in Med.* Vol.15 (2004), p.291
- [4] K.Cheng, W.Weng, H.Qu, P.Du, G.Shen, G.Han, J.Yang and M.J.Ferreira: *J. Biomed. Mater. Res. B* Vol 69 (2004), p.33
- [5] E.L.Carey, H.H.Xu, G.C.Simon, S.Takagi and C.L.Chow: *Biomaterials* Vol 26 (2005), P.5002
- [6] M.E.Ooms, J.G.C.Wolke, J.P.C.M.Waerden and J.A.Jansen: *J. Biomed. Mater. Res.* Vol.61 (2002), p.9
- [7] M.Tamai, T.Isshiki, K.Nishio, M.Nakamura, A.Nakahira and H.Endoh: *J. Mater. Res.* Vol.18 (2003), p.2633
- [8] T.Morita, T.Nagaki, I.Fukuda and K.Okumura: *Muta. Res.* Vol.268 (1992), p.297

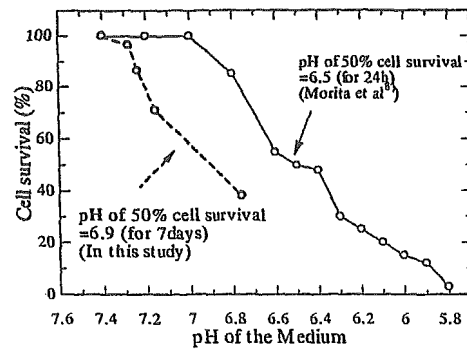


Fig.4. V79 cell survival in the medium with various pH values.

Novel Calcium Phosphate Ceramics : The Remarkable Promoting Action on the Differentiation of the Normal Human Osteoblasts

Masato Tamai^{1a}, Ryusuke Nakaoka^{1b}, Kazuo Isama^{1c} and Toshie Tsuchiya^{1d}

¹Division of Medical Devices, National Institute of Health Sciences,
1-18-1 Kamiyoga, Setagaya-ku, Tokyo 158-8501 Japan

^am-tamai@nihs.go.jp, ^bnakaoka@nihs.go.jp, ^cisama@nihs.go.jp, ^dtsuchiya@nihs.go.jp

Keywords: Hydroxyapatite, Niobium ion, Osteoblast, Alkaline phosphatase activity

Abstract.

To promote the activity of normal human osteoblasts (NHOst), the novel HAp ceramics containing Nb ions (NbHAp) were synthesized by wet chemical process, which reacting aqueous solution containing a mixture of $\text{Ca}(\text{NO}_3)_2$, $(\text{NH}_4)_2\text{HPO}_4$, and the Nb aqueous solution. X-ray diffraction patterns indicated that NbHAp had a monolithic apatitic structure, although crystallite decreased as Nb content increased. From inductively coupled plasma analysis, maximum amount of Nb ions in the sample was almost 8.2atom% of P ions. The NbHAp were presented as aggregates and composed of fine crystal of $<1\mu\text{m}$ in diameter. Nb ions in NbHAp were uniformly distributed in the aggregates. Furthermore, high-resolution XPS spectra of Nb $3d_{5/2}$ indicated that Nb ions in the HAp were presented as Nb^{5+} . These results suggested that Nb ions were at PO_4 site in crystal structure of HAp. When NHOst were cultured with the NbHAp, their ALP activity were twice as much as that of NHOst cultured with HAp without Nb ions.

Introduction

Tissue engineering takes advantages of the combined use of cultured living cells and scaffolds to deliver vital cells to the damaged site of the patient. Some tissue engineering approaches have been devised to repair large bone defect. In developing of the scaffold for bone tissue, the interaction between osteoblasts cells and scaffolds are much important. To achieve the restoration of the bone tissue at early stage, the scaffold is required to have the ability of promoting proliferation and mineralization.

It is well known that hydroxyapatite ($\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$, HAp) ceramics can be biologically bonded to natural bones and have been studied to utilize as the scaffolds. In addition, the structure is very tolerant of ionic substitutions and Ca^{2+} ions, PO_4^{3-} ions and OH^- ions can be replaced by various cationic or anionic ions, partly or completely[1]. For example, K^+ , Mg^{2+} and Sb^{3+} , can substituted for Ca ions and CO_3^{2-} and VO_4^{3-} can substituted for PO_4^{3-} ions, completely or partially. Thus various kinds of ion substitutions can be made to synthesize novel modified-HAps.

Recently, our co-workers reported that niobium (Nb) ions have the significant effect which promotes the proliferation and differentiation of normal human osteoblastic cells (NHOst)[2]. In the present study, therefore, we attempted to synthesize the novel HAp ceramics containing Nb ions (NbHAp) to promote the activity of NHOst and investigated the interaction between NbHAp and NHOst.

Materials and Methods

Synthesis of Nb containing HAp

The NbHAp was synthesized by wet chemical process, which reacting aqueous solution containing a mixture of $\text{Ca}(\text{NO}_3)_2$, $(\text{NH}_4)_2\text{HPO}_4$, and the Nb aqueous solution. The reagent grade $\text{Ca}(\text{NO}_3)_2$, $(\text{NH}_4)_2\text{HPO}_4$ and NbCl_5 (Wako Pure Chemical Industries, Ltd) were used without purification. The metal ion chemical reagent was completely dissolved in an exact amount of distilled water. The Nb aqueous solution was prepared by the mixing of distilled water and NbCl_5 solution, which dissolved in 5vol%-hydroxyacetone and 5vol%-2-aminoethanol[3].

0.2M-(NH₄)₂HPO₄ and 0.01M NbCl₅ solutions were mixed and stirred with a magnetic bar. The Nb/(Nb+P) molar ratio of the mixing solution was set to 0.0000, 0.0167 and 0.1667. The pH of the mixing solution was adjusted to 10 using 1N-NaOH. 0.2M-Ca(NO₃)₂ was slowly dropped in the mixing solution (20ml/min). The ionic content of those starting solutions are shown in table 1. The pH was monitored and the reaction was terminated at pH 10.0. After the reaction, the suspension was stirred for 24h at room temperature. The precipitates were centrifuged at 3000rpm for 5min and washed with distilled water. The obtained apatites were annealed at 800°C for 2h (heating rate: 5°C/min). In this study, those precipitates obtained by reaction of Ca(NO₃)₂ solution and the mixing solution with different Nb/(Nb+P) molar ratio of 0.000, 0.0167 and 0.1667 are named HAp, NbHAp-I and NbHAp-II, respectively.

Characterization of NbHAp

The NbHAp were characterized by X-ray diffraction analysis (XRD, Rigaku, Rint2000). Ca, P and Nb ions concentrations in apatites are measured by inductively coupled plasma (ICP, Hewlett-Packard, HP4500). Microstructural evaluation was performed by scanning electron microscopy (SEM) and energy dispersive X-ray spectroscopy (EDS) (JEOL, LV5800). The chemical state of Nb ions in HAp was investigated by X-ray photon spectroscopy (XPS, Shimadzu, ESCA-3200).

Osteogenesis evaluation of NHOst cultured with NbHAp

NHOst were purchased from BioWhittaker Inc.(Walkersville,MD). The NHOst were maintained in alpha minimum essential medium (αMEM, Gibco, Grand Island, NY) containing 10%-FCS in incubators at 37°C in a humidified atmosphere with 5% CO₂. All assays were performed using αMEM containing 10%-FCS supplemented with 10mM beta-glycerophosphate. NHOst cells (4×10⁴ cells/well/ml) were co-cultured with 5mg of the apatites for 7days to evaluated the effects of the apatites on NHOst.

Proliferation of NHOst cells cultured with the apatites was estimated by Tetracolor One assay (Seikagaku Co., Ltd. Tokyo, Japan), which incorporates an oxidation reduction indicator based on detection of metabolic activity. After 7-days incubation, 2%-TetraColor One/αMEM solution was added to each well, followed by 2h incubation. The absorbance of the supernatant at 450nm was estimated using μQuant spectrophotometer (Bio-tek Instrument, Inc., Winooski, VT). After estimating the proliferation, the cells were washed by phosphate-buffered saline (PBS(-)), followed by addition of 1ml of 0.1M glycine buffer (pH=10.5) containing 10mM MgCl₂, 0.1mM ZnCl₂ and 4mM p-nitrophenylphosphate sodium salt. After incubating at room temperature for 5min, the absorbance at 405 nm was detected using the μQuant spectrophotometer to evaluated alkaline phosphatase (ALP) activity of the test cells.

Results and Discussion

XRD patterns of NbHAp prepared by wet chemical process are shown in Fig.1(a). Irrespective of Nb/(Nb+P) molar ratio in starting solution, the precipitates were identified as monolithic HAp.

Table1. The ionic content of starting solution and the composition of the obtained precipitates.

Samples	Ionic content of Starting Solution*			Theoretical Ca/(Nb+P)**	Nb/(Nb+P)**		Color of Precipitates
	Ca	PO ₄	Nb		Theoretical	Measured**	
HAp	60.0	36.0	0.0	1.67	0.0000	-	White
NbHAp-I	60.0	35.4	0.6	1.67	0.0167	0.015	Pale yellow
NbHAp-II	60.0	30.0	6.0	1.67	0.1667	0.082	Buff yellow

*mmol, **Molar ratio, ***The precipitates were dissolved with HCl and the ionic concentration of HCl solutions were measured by ICP.

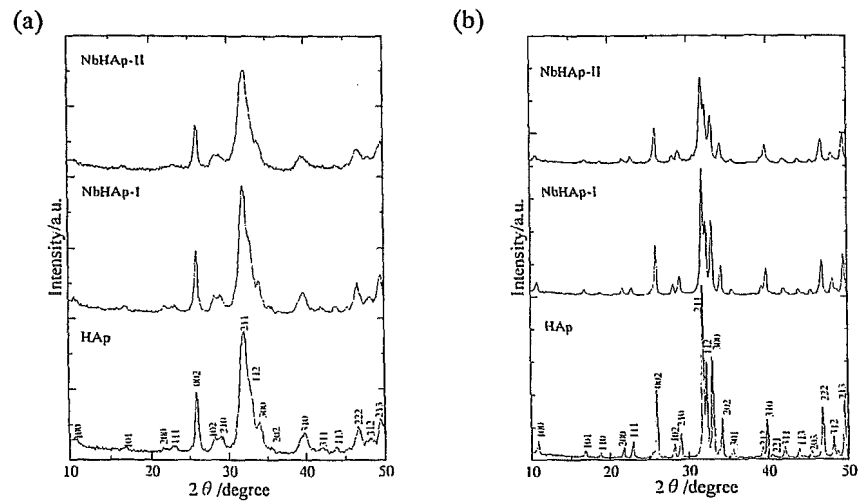


Fig.1. XRD patterns of HAp and NbHAp-I and NbHAp-II before (a) and after (b) annealing(800°C, 2h).

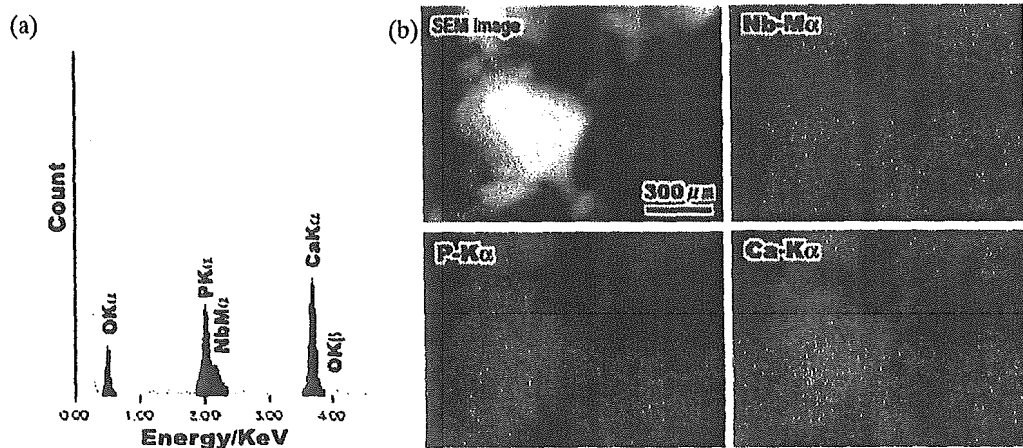


Fig.2. SEM-EDX analysis of NbHAp-II. ((a) An EDX spectrum and (b) SEM image and element mapping images of Nb, Ca and P).

As shown in Table 1, the Nb/(Nb+P) molar ratio of NbHAp-I and NbHAp-II were 0.015 and 0.082, respectively. SEM observation revealed that the precipitates were present as aggregates composed of primary particles of less than 1 μm in diameter.

XRD patterns of NbHAp annealed at 800°C are shown in Fig.1(b). The crystallinity of the precipitates became high by the annealing and XRD patterns of all annealed NbHAp could be identified as monolithic apatitic structure. It is noted that the crystallite size of the NbHAp decreased as Nb content increased. Figure 2(a) shows an EDX spectrum of the whole region of SEM image in Fig.2(b). The EDX spectrum from Nb M_α was separated from P K_α line and could be observed at 2.17 keV, although the intensity of the spectra was weak. The mapping images of Nb, Ca and P ions are shown in Fig.2(b). As shown in Fig.2(b), Nb ions were present at the same site of Ca and P ions. Based on these observations, Nb ions are suggested to be uniformly distributed in the