

Oka K, <u>Murase T</u> , Moritomo H, Goto A, Sugamoto K, Yoshikawa H.	Patterns of bone defect in scaphoid nonunion: a 3-dimensional and quantitative analysis.	J Hand Surg [Am]	30	359-65	2005
Goto A, Moritomo H, <u>Murase T</u> , Oka K, Sugamoto K, Arimura T, Masumoto J, Tamura S, Yoshikawa H, Ochi T	In vivo three-dimensional wrist motion analysis using magnetic resonance imaging and volume-based registration.	Journal of Orthopaedic Research	23	750-756	2005
<u>Murase T</u> , Moritomo H, Goto A, Sugamoto K, Yoshikawa H.	Does three-dimensional computer simulation improve results of scaphoid nonunion surgery?	Clinical Orthopaedics and Related Research.	434	143-150	2005
Moritomo H, <u>Murase T</u> , Goto A, Oka K, Sugamoto K, Yoshikawa H.	In vivo three-dimensional kinematics of the mid carpal joint of the wrist.	J Bone Joint Surg	88A	611-621	2006
Namba J, Shimada K, Saito M, <u>Murase T</u> , Yamada H, Yoshikawa H.	Modulation of peritendinous adhesion formation by alginate solution in a rabbit flexor tendon model.	Journal of Biomedical Material Research Part B	80	273-279	2007
Kitamura T, Hashimoto J, <u>Murase T</u> , Tomita T, Hattori T, Yoshikawa H, Sugamoto K.	Radiographic study of joint destruction patterns in the rheumatoid elbow.	Clinical Rheumatology	Epub ahead of print		2006

Feasibility of Polysaccharide Hybrid Materials for Scaffolds in Cartilage Tissue Engineering: Evaluation of Chondrocyte Adhesion to Polyion Complex Fibers Prepared from Alginate and Chitosan

Norimasa Iwasaki,*† Shin-Tarou Yamane,† Tokifumi Majima,† Yasuhiko Kasahara,† Akio Minami,† Kazuo Harada,‡ Sachiko Nonaka,‡ Nobuhiko Maekawa,‡ Hiroshi Tamura,§ Seiichi Tokura,§ Masamichi Shiono,# Kenji Monde,# and Shin-Ichiro Nishimura#

Department of Orthopaedic Surgery, Hokkaido University School of Medicine, Sapporo 060-8638, Japan, Chemical Biology Institute Co. Ltd. (CBI), Sapporo 004-0814, Japan, Chemistry Branch, Faculty of Engineering, Kansai University, Osaka 564-8680, Japan, and Laboratory for Bio-Macromolecular Chemistry, Division of Biological Sciences, Graduate School of Science, Hokkaido University, Sapporo 060-0810, Japan

Received January 21, 2004; Revised Manuscript Received April 2, 2004

The ideal cell-carrier material for cartilage regeneration should be one that closely mimics the natural environment in a living articular cartilage matrix. In the current study, we considered that alginate-based chitosan hybrid biomaterials could provide excellent supports for chondrocyte adhesion. To test this hypothesis, we investigated the adhesion behavior of rabbit chondrocytes onto an alginate polymer versus the adhesion of the chondrocytes onto some alginate-based chitosan hybrid polymer fibers *in vitro*. We demonstrated that the alginate-based chitosan hybrid polymer fibers showed much improved adhesion capacity with chondrocytes in comparison with alginate polymer fiber. Additionally, morphologic studies revealed maintenance of the characteristic round morphology of the chondrocyte and the dense fiber of the type II collagen produced by the chondrocytes in the hybrid polymer. On the basis of these results, we conclude that an alginate-based chitosan hybrid polymer fiber has considerable potential as a desirable biomaterial for cartilage tissue scaffolds.

Introduction

The limited potential for self-repair of articular cartilage necessitates surgical procedures to treat injured cartilage. However, no current procedures for cartilage repair have successfully regenerated long-lasting hyaline cartilage tissue to replace a cartilaginous lesion. On the other hand, a large number of tissue engineering studies, involving the regeneration of hyaline cartilage by culturing isolated chondrocytes on biocompatible and biodegradable polymers as scaffolds onto which cells are seeded, have been performed.^{1–10} Some of these studies have shown the importance of selecting the appropriate biomaterials as scaffolds for the chondrocyte adhesion and supporting cell proliferation.^{3,5} Although a variety of biomaterials, including both naturally occurring and synthetic, have been introduced as potential scaffolds for cartilage repair,^{1,2,4,6–10} we believe that the ideal cell-carrier substance should be one that closely mimics the natural environment in the cartilage-specific extracellular matrixes (ECMs).

Given the importance of glycosaminoglycans (GAGs) in stimulating chondrogenesis *in vitro*,^{2,8,9} the uses of GAGs or GAGs-like materials as components of a scaffold seems to be a reasonable approach for enhancing chondrogenesis. In the current study, we focused on simplifying complicated three-dimensional (3D) networks of ECMs composed of a variety of cell adhesive proteins and proteoglycans. This was achieved by preparing a novel model of polyion complex fibers from alginate and chitosan. Alginate is one of the naturally abundant and anionic polysaccharides composed of a disaccharide repeating unit, [GlcA β (1–4) Glc β (1–3)].¹¹ Moreover, this polysaccharide is known as a hyaluronic acid-like biocompatible polymer often used in biomaterials science because it contains D-glucuronic acid as a main sugar residue of the repeating unit.^{12,13} Alginate could be considered to be a good mimic for cartilage GAGs. However, because of its anionic nature, the cellular adhesivity of the chondrocytes to alginate is limited.¹⁴

On the other hand, chitosan has been employed as an excellent biocompatible material for wound healing and tissue repair.^{15–17} Since chitosan is regarded as a cationic polysaccharide showing excellent cell adhesive properties, we hypothesized that a hybrid material composed of alginate combined with chitosan could improve the chondrocyte adhesion to the material. To test this hypothesis, we investigated the *in vitro* adhesion behavior of rabbit chondrocytes onto

* To whom correspondence should be addressed. Phone: 81-11-706-5937. Fax: 81-11-706-6054. E-mail: niwasaki@med.hokudai.ac.jp.

† Hokkaido University School of Medicine.

‡ Chemical Biology Institute Co. Ltd.

§ Kansai University.

Graduate School of Science, Hokkaido University.

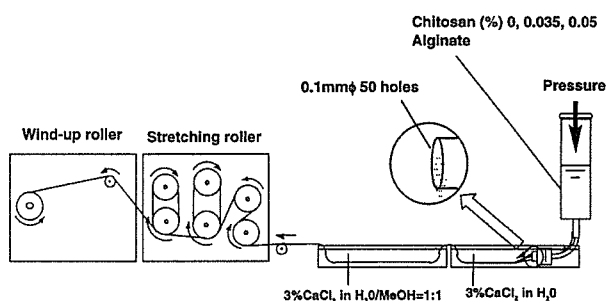


Figure 1. Original spinning apparatus for alginate fiber coated with chitosan.

alginate-based chitosan hybrid polymer fibers. The objectives of the current study are to quantify the degree of rabbit chondrocyte adhesion onto alginate-based chitosan hybrid polymer fibers and onto an alginate polymer fiber and to compare the data obtained from the respective fiber types. In addition, we present the chondrocyte proliferation and the morphologic findings onto the alginate-based chitosan hybrid polymer fibers. The results derived from this study provide the essential information on the interactions between chondrocytes and the novel hybrid polymer fibers as a biomedical material for cartilage tissue scaffolds.

Experimental Section

Preparation of Polyion Complex Fiber. The process of preparing the alginate polymer fiber and the alginate-based chitosan hybrid polymer fibers was essentially the same as that reported by coauthors.¹⁸ A solution of sodium alginate (4% w/w, $M_w = 600\,000$, Kibun Food Chemifa, Co. Ltd., Tokyo, Japan) and chitosan oligomer (0, 0.035, or 0.05% w/w, $M_w = 18\,000$, Kimitsu Chemical, Co. Ltd., Tokyo, Japan) in water was poured subsequently into the coagulation system (a: 3% CaCl_2 in H_2O ; b: 3% CaCl_2 in $\text{H}_2\text{O}/\text{MeOH}$) through a nozzle containing 50 holes, each with a diameter of 0.1 mm (Figure 1). The fibers were washed with methanol and dried at room temperature and used for the further experiments after sterilization. In the current study, alginate polymer fiber (alginate group) and alginate-based chitosan hybrid polymer fibers (alginate with 0.035% chitosan, alginate-chitosan 0.035% group; alginate with 0.05% chitosan, alginate-chitosan 0.05% group) were originally prepared. Polymer fiber of polyglactin 910, a 90:10 copolymer of glycolide and lactide, coated with polyglactin 370 and calcium stearate (9-0 Vicryl suture material, Ethicon Co., Somerville, NJ) was also used as a control material. This fibrous material, which has the same diameter as the novel fibers, has been widely used in clinical fields.

Measurement of Mechanical Properties. The mechanical properties of each fiber group were measured according to the Japanese Industrial Standards L1015. Tensile tests for five samples of each fiber group were performed at a crosshead speed of 20 mm/min using the material testing machine (P/N346-51299-02, Shimadzu, Kyoto, Japan). The cross-sectional area was determined using a microscope (BX50, Olympus, Tokyo, Japan) and a video dimension analyzer (VM-30, Olympus, Tokyo, Japan).

Microscopic Observation of Fibers. Microarchitecture of each fiber was observed by scanning electron microscopy (SEM, S-4500, Hitachi, Ltd., Tokyo, Japan). To quantitatively evaluate the alteration in the fibrous structure through the degradation process, the diameter of each fiber in wet and dry conditions ($n = 10$ in each group) was measured with a SEM image analysis system (Quartz PCI, Quartz Imaging Corporation, Tokyo, Japan).

Preparation of Chondrocyte Suspension. Chondrocytes were isolated from the articular surfaces of a Japanese white rabbit (2.0 kg, Hokudo Co. Ltd., Sapporo, Japan) under sterile conditions using a technique described by Wakitani et al.¹⁹ Articular cartilage slices, gathered from the knee, hip, and shoulder joints were detached from the adherent connective tissues. The cartilage specimens were minced like paste and washed in sterile 0.9% sodium chloride. Then, the chondrocytes were isolated with 0.25% trypsin in sterile saline for 30 min followed by 0.25% type II collagenase in Dulbecco's modified Eagle's medium (Gibco, Grand Island, NY) supplemented with 10% fetal bovine serum, 100 IU/mL penicillin, 100 $\mu\text{g}/\text{mL}$ streptomycin, and 0.25 $\mu\text{g}/\text{mL}$ amphotericin B for 6 h at 37 °C in a culture bottle. Finally, the isolated cells were collected by centrifugation at 1500 g for 5 min at 37 °C after removal from the culture bottle and washed three times with the culture medium. The isolated cells were quantitated using a hemocytometer, and then the higher concentrated chondrocyte suspension was diluted to 5×10^6 cells/mL.

Cell Adhesion Study. Cell adhesion to the fibrous materials was basically assessed by the method as previously reported by Nishimura et al.²⁰ The fibrous samples were cut into 10 mm pieces and packed in Teflon tubes (25 mm length, 4.8 mm inner diameter, Sanplatec, Osaka, Japan). Each fibrous sample consisted of 230 fibers. Then, 0.1 mL of chondrocyte suspension containing 0.5×10^6 cells was loaded on the column at room temperature. The cells were allowed to adhere in a humidified incubator (37 °C and 5% CO_2) for 1 h. Each column was gently rinsed with 1 mL of 1 M phosphate-buffered saline (PBS) per 30 s using a syringe and the number of unattached cells was quantified by the microscopic observation of the rinsed solution. Parallel samples of $n = 5$ were used for each group of polymer fibers.

Cell Proliferation Study. To assess the cell proliferation on each fibrous material, the sheets consisting of each polymer fiber were created in a perpendicular pattern with one layer (8×8 mm). At 1, 7, and 14 days after cultivation, five cultured materials of each fiber group were harvested to quantify the total amount of DNA. The DNA content was measured in aliquots of the sodium citrate (0.05 M phosphoric acid, 2 M NaCl) dissolved powdered samples by a modified fluorometric assay using a bisbenzimidazole dye (Hoechst dye 33258, Polyscience Inc., Northampton, U.K.).²¹ In fluorescence measurements, the excitation wavelength was 356 nm and the emission wavelength was 458 nm. The results were extrapolated from a standard curve using salmon testis DNA (Worthington, Freehold, NJ).

Morphological Observations. Cell morphology in the fiber was observed by light microscopy and SEM after 14

Table 1. Mean Mechanical Properties in Each Fiber Group^a

	alginate	alginate-chitosan 0.035%	alginate-chitosan 0.05%
tensile strength (N/mm ²)	242.6 ± 3.2	246.4 ± 4.1	229.0 ± 2.2 ^b
strain at failure (%)	11.4 ± 0.1	11.5 ± 0.8	11.0 ± 0.2

^a Mean ± SE. ^b $p < 0.05$ vs alginate group. $p < 0.005$ vs alginate-chitosan 0.035% group.

days in culture. For the SEM observations, the samples with chondrocyte adhesion were rinsed with Ringer's solution and then fixed with 2.5% glutaraldehyde in 0.1 M PBS. The samples were covered with 1% osmium tetroxide (OsO₄) and 1% tannic acid to fix the samples for the electron microscope. After dehydration in a graded series of ethanols starting at 50% and continuing to 100%, samples were critical-point dried with CO₂ and sputter coated with gold. Samples were visualized by SEM.

Statistical Analysis. All data were represented as mean ± standard error. Statistical comparisons among the fiber groups were performed using one-way analysis of variance (ANOVA) and Fisher's PLSD test. The alterations in the fibrous diameter between dry and wet conditions in each group were analyzed using a paired t-test. Differences were considered significant for $p < 0.05$.

Results

Mechanical Properties. Table 1 summarizes the mechanical properties in each fiber group. The tensile strength in the alginate-chitosan 0.05% group was significantly lower than that in other groups ($p < 0.05$ vs the alginate group, $p < 0.005$ in the alginate-chitosan 0.035% group). In terms of the strain at failure, there were no statistically significant differences among the three groups.

Microarchitecture of Fibers. Figure 2 shows the SEM images of fibers with altered concentrations of chitosan in dry and wet conditions. Although the surface of the alginate nonhybrid fiber was uneven, it became smooth as the chitosan concentration increased. The diameters of each fiber group in dry and wet conditions are summarized in Table 2. There were no statistically significant differences in the diameter of fiber among the three groups. No significant alterations in the values were found from dry to wet condition in any groups.

Cell Adhesion. Adhesivities of chondrocytes are expressed by the percentage of chondrocyte trapped in the column (percentage of adhesion), which is calculated using the equation given in Figure 3. As shown in Figure 3, the value in the alginate-chitosan 0.05% group was significantly higher than that in the control ($83.4 \pm 4.5\%$ vs $19.2 \pm 6.2\%$, $p < 0.0001$) and the alginate groups ($83.4 \pm 4.5\%$ vs $67 \pm 4.6\%$, $p < 0.05$).

DNA Quantification. The total amount of DNA in each fibrous material was expressed as the amount per dry weight of the cultured material ($\mu\text{g/g}$). The value at each time period is summarized in Table 3. At day 1, the value in the alginate-chitosan 0.05% group was significantly higher than that in

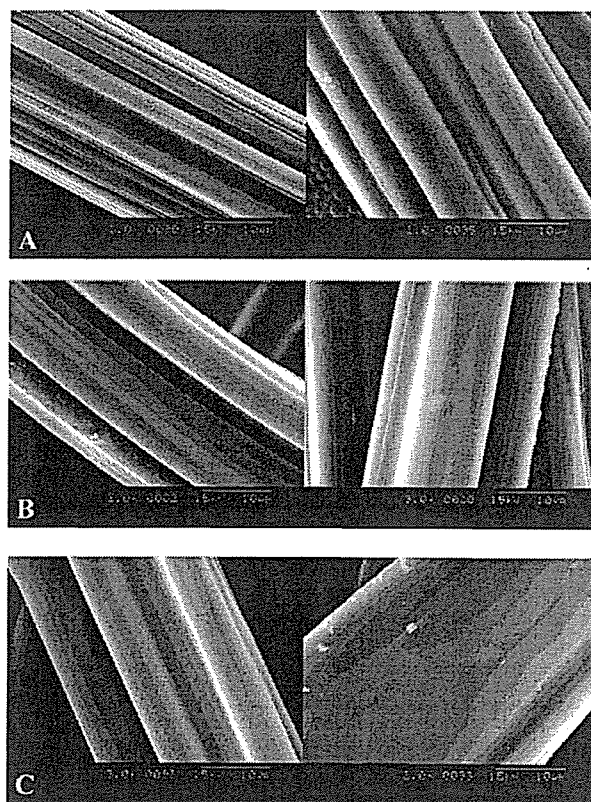


Figure 2. SEM image of fibers with altered concentrations of chitosan. A, Alginate polymer fiber; B, Alginate-based 0.035% chitosan hybrid polymer fiber; C, Alginate-based 0.05% chitosan hybrid polymer fiber. Left, dry condition; Right, wet condition. Although the surface of the alginate nonhybrid fiber is uneven, it becomes smooth as the chitosan concentration increases. No significant alterations in the microarchitecture are found between dry and wet conditions in any fiber groups.

Table 2. Mean Diameter of Each Fiber Group^a

	alginate	alginate-chitosan 0.035%	alginate-chitosan 0.05%
dry condition (μm)	28.3 ± 1.3	27.5 ± 1.2	29.2 ± 0.8
wet condition (μm)	29.8 ± 1.7	28.6 ± 1.7	31.3 ± 1.5

^a Mean ± SE.

other groups ($p < 0.01$ vs the alginate group, $p < 0.05$ vs the alginate-chitosan 0.035% group). Although there were no statistically significant differences in the DNA amount at day 7 and day 14 among the three groups, the values in the alginate-chitosan hybrid groups tended to increase from day 7 to day 14.

Cell Morphology. Phase contrast micrographs showed the adhesion of the chondrocytes to the polymer fibers. There was no significant effect of the compositions of the polymer fiber on cell morphology after 14 days in culture. Scanning electron micrographs revealed the characteristic round morphology of the chondrocyte on an alginate-based 0.05% chitosan hybrid fiber (Figure 4). The image shows the proliferated cells in the dense fiber of the type II collagen produced by the chondrocytes (Figure 4).

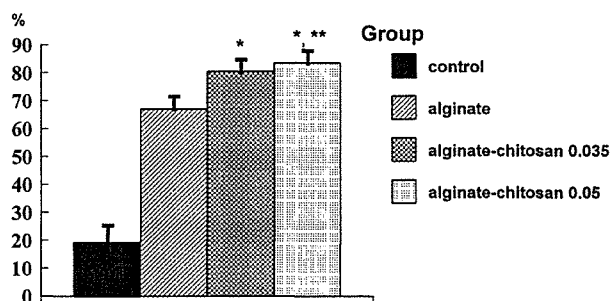


Figure 3. Percentage of chondrocytes trapped in the column (percentage of adhesion). Percentage of adhesion = $(5 \times 10^6 \text{ cells} - \text{the number of unattached cells in rinsed solution}) / 5 \times 10^6 \text{ cells} \times 100$. 0.5×10^6 cells, initial cell number in chondrocyte suspension on the column. * $p < 0.0001$, compared with the control group. ** $p < 0.05$, compared with the alginate group.

Table 3. Mean Total Amount of DNA in Each Fiber Group^a

	day 1 ($\mu\text{g/g}$)	day 7 ($\mu\text{g/g}$)	day 14 ($\mu\text{g/g}$)
alginate	19.2 \pm 1.0	28.8 \pm 0.8	27.5 \pm 1.0
alginate-chitosan 0.035%	20.2 \pm 1.2	24.6 \pm 2.3	35.7 \pm 5.4
alginate-chitosan 0.05%	26.2 \pm 2.3 ^b	26.0 \pm 2.7	38.7 \pm 6.2

^a Mean \pm SE. ^b $p < 0.01$ vs alginate group. $p < 0.05$ vs alginate-chitosan 0.035% group.

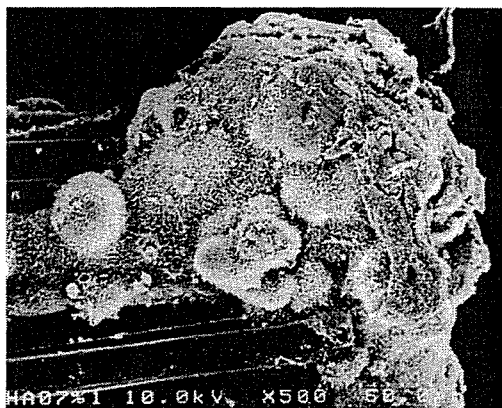


Figure 4. SEM image of rabbit articular chondrocytes seeded on alginate-based 0.05% chitosan hybrid fiber after 14 days of culture. The characteristic round morphology of the chondrocyte and the dense fiber of the type II collagen produced by the chondrocytes can be seen on the composite fibers.

Discussion and Conclusions

In articular cartilage tissue engineering, we must consider that the articular cartilage is subject to excessive mechanical stress. Therefore, to maintain the number of attached chondrocytes, highly cellular adhesivity is a requirement for scaffold materials in cartilage tissue engineering. Several studies have shown that alginate has an excellent potential of enhancing chondrogenesis in vitro culture systems.²²⁻²⁴ However, one drawback of alginate is that the cells within this material do not strongly adhere to the surface due to its anionic nature. To improve the cellular adhesivity, Genes et al.¹⁴ introduced an RGD peptide to alginate material. They demonstrated that the adhesion of chondrocytes to the RGD-alginate was 10–20 times higher than that to unmodified alginate. The background of developing the current alginate-

based chitosan hybrid material is also to improve the chondrocyte adhesivity to alginate. This study demonstrated that the adhesivity of chondrocytes was significantly higher on the alginate-based chitosan hybrid polymer fiber than on the alginate polymer fiber. Madihally et al.⁶ reported that the cationic nature of chitosan allowed for electrostatic interactions with anionic GAGs, proteoglycans, and other negatively charged species. These ionic interactions may serve as a mechanism for retaining and recruiting cells, growth factors, and cytokines within a tissue scaffold. In addition, the DNA quantification of cultured chondrocytes showed that the attached chondrocytes to the alginate-chitosan hybrid fibers tended to proliferate, as compared with those to the alginate polymer fiber. Consequently, alginate-based chitosan hybrid polymer has great potential as a desirable biomaterial for cartilage tissue scaffolds.²⁵⁻²⁷

Although several basic studies have demonstrated the chondrogenic potential of GAG-augmented chitosan hydrogels,^{2,8,9,28,29} these hydrogels do not have the required mechanical strength. Several studies have shown a critical role of mechanical stimulations to the chondrocytes in enhancing cartilage tissue regeneration.³⁰⁻³⁴ In vivo studies, using animal models, have clearly demonstrated that moderate exercise leads to an increase in the proteoglycan content of articular cartilage.^{31,32} In vitro studies have indicated that cyclic loading to cartilage explants stimulates synthesis of ECMs by chondrocytes.^{30,33,34} In addition, Démarteanu et al.³⁰ showed that GAGs accumulation in the chondrocyte culture system increased in response to dynamic compression only if the GAGs content prior to compression was sufficiently high. This indicates that the response of chondrocytes to dynamic compression directly depends on the GAGs amount surrounding the cells. Therefore, if the mechanical stimulation is applied to cartilage tissue engineering, a strategy for enhancing deposition of GAGs at the early culture stages must be considered. We believe that the use of alginate, which is one of the cartilage GAGs mimics, as a component of a scaffold biomaterial should be a rational strategy for cartilage tissue engineering.

A scaffold for cartilage tissue engineering requires adequate mechanical strength to maintain the initial shape of the implanted scaffold. To achieve this requirement, we have developed a new polymer fiber as a fundamental material for 3D fabricated scaffold. In the development of the novel fibers, one of the most critical points was to increase the mechanical strength of the fibers for 3D fabrication. The obtained mechanical properties of the novel fibers indicated enough mechanical strength to create a 3D fabricated scaffold using the original apparatus. On the other hand, Silver et al.³⁵ reported that the tensile strength of the type II collagen fibrous tissue in the cartilage was between 1000 N/mm² and 3000 N/mm². In the current study, the tensile strength of the fiber was 242.6 N/mm² in the alginate group, 246.4 N/mm² in the alginate-chitosan 0.035% group, and 229.0 N/mm² in the alginate-chitosan 0.05% group. Theoretically, the mechanical property of a scaffold material consisting of a large number of the current fibers should be comparable to that of the type II collagen fibrous tissue. Therefore, a 3D fabricated scaffold based on the novel fibers

may have suitable mechanical strength for cartilage tissue regeneration.

Regarding technical limitations in preparing the novel fiber, we must consider the following point: alginate is an anionic polysaccharide consisting of polyguluronate and polymannuronate residues. It is well-known that the calcium ion chelates to alginate chains of polyguluronate sequences, and the strength and specificity of the complexes are explained in terms of an egg-box model.³⁶ In contrast, chitosan is a cationic polysaccharide consisting of glucosamine residues. The calcium ion and chitosan exist in the first coagulation bath. The strength of alginate fibers would decrease due to the inhibition of chelation of calcium ion with alginate chains at high concentration of chitosan. Therefore, in this study, we did not prepare the hybrid fibers coated with over 0.05% chitosan concentration.

In conclusion, the alginate-based chitosan hybrid polymer fibers promoted favorable biological responses of seeded chondrocytes including enhanced cell attachment and proliferation *in vitro*. In addition, the mechanical strength of these fibers could make it possible to create a 3D fabricated scaffold using an apparatus formed from the novel fibers. Ideally, the mechanical properties of 3D scaffolds based on the alginate-based chitosan hybrid fibers must be tested to determine the optimum properties for cartilage regeneration. However, the data obtained here strongly suggest that the novel fibers may be a suitable candidate for 3D scaffold biomaterial in cartilage tissue engineering. Further studies will be performed to design a desirable 3D fabricated scaffold for cartilage regeneration based on the novel fibers, to clarify the biodegradability and biocompatibility in living joints, and to evaluate the *in vivo* cartilage regeneration using the developed 3D scaffold.

Acknowledgment. This work was supported by a grant for "Research and Development on Glycocluster Controlling Biomolecules" from the New Energy and Industrial Technology Development Organization (NEDO). The authors thank Dr. Hiromi Iwanaga for her help with the scanning electron microscopy study.

References and Notes

- (1) Aigner, J.; Tegeler, J.; Hutzler, P.; Campoccia, D.; Pavesio, A.; Hammer, C.; Kastenbauer, E.; Naumann, A. Cartilage tissue engineering with novel nonwoven structured biomaterial based on hyaluronic acid benzyl ester. *J. Biomed. Mater. Res.* **1998**, *42*, 172.
- (2) Guo, J. F.; Jourdain, G. W.; MacCallum, D. K. Culture and growth characteristics of chondrocytes encapsulated in alginate beads. *Connect. Tissue Res.* **1989**, *19*, 277.
- (3) Hutmacher, D. W. Scaffolds in tissue engineering bone and cartilage. *Biomaterials* **2000**, *21*, 2529.
- (4) Ishaug-Riley, S. L.; Okun, L. E.; Prado, G.; Applegate, M. A.; Ratcliffe, A. Human articular chondrocyte adhesion and proliferation on synthetic biodegradable polymer films. *Biomaterials* **1999**, *20*, 2245.
- (5) LeBaron, R. G.; Athanasiou, K. A. *Ex vivo* synthesis of articular cartilage. *Biomaterials* **2000**, *21*, 2575.
- (6) Madhally, S. V.; Matthew, H. W. T. Porous chitosan scaffolds for tissue engineering. *Biomaterials* **1999**, *20*, 1133.
- (7) Nehrer, S.; Breina, H. A.; Ramappa, A.; Shortkroff, S.; Young, G.; Minas, T.; Sledge, C. B.; Yannas, I. V.; Spector, M. Canine chondrocytes seeded in type I and type II collagen implants investigated *in vitro*. *J. Biomed. Mater. Res.* **1997**, *38*, 95.
- (8) Sechrist, V. F.; Miao, Y. J.; Niyibizi, C.; Larson, A. W.; Matthew, H. W.; Evans, C. W.; Fu, F. H.; Suh, J. K. GAG-augmented polysaccharide hydrogel: a novel biocompatible and biodegradable material to support chondrogenesis. *J. Biomed. Mater. Res.* **2000**, *49*, 534.
- (9) Suh, J. K. F.; Matthew, H. W. T. Application of chitosan based polysaccharide biomaterials in cartilage tissue engineering: a review. *Biomaterials* **2000**, *21*, 2589.
- (10) Vacanti, C. A.; Langer, R.; Vacanti, J. P. Synthetic polymers seeded with chondrocytes provide a template for new cartilage formation. *Plast. Reconstr. Surg.* **1991**, *88*, 753.
- (11) Budavari, S. *The Merck Index*; Merck Co., Inc.: Whitehouse Station, 1996.
- (12) Jianqi, H.; Hong, H.; Lieping, S.; Genghua, G. Comparison of calcium alginate film with collagen membrane for guide bone regeneration in mandibular defects in rabbits. *J. Oral Maxillofac. Surg.* **2002**, *60*, 1449.
- (13) Dar, A.; Shachar, M.; Leor, J.; Cohen, S. Optimization of cardiac cell seeding and distribution in 3D porous alginate scaffolds. *Biotechnol. Bioeng.* **2002**, *80*, 305.
- (14) Genes, N. G.; Rowley, J. A.; Mooney, D. J.; Bonassar, L. J. Effect of substrate mechanics on chondrocyte adhesion to modified alginate surfaces. *Arch. Biochem. Biophys.* **2004**, *422*, 161.
- (15) Degim, Z.; Celebi, N.; Sayan, H.; Babul, A.; Erdogan, D.; Take, G. An investigation on skin wound healing in mice with a taurine-chitosan gel formation. *Amino Acids* **2002**, *22*, 187.
- (16) Peh, K.; Khan, T.; Ching, H. Mechanical, bioadhesive strength and biological evaluations of chitosan films for wound dressing. *J. Pharm. Sci.* **2000**, *3*, 303.
- (17) Nishimura, S. I. Chemical Biology and Biomedicine. In *Glycoscience: Chemistry and Chemical Biology I-III*; Fraser-Reid, B. O., Ed.; Springer: New York, 2001; Chapter 6.
- (18) Tamura, H.; Tsuruta, Y.; Tokura, S. Preparation of chitosan alginate filament. *Mater. Sci. Eng. C* **2002**, *20*, 143.
- (19) Wakitani, S.; Kimura, T.; Hirooka, A.; Ochi, T.; Yoneda, M.; Yasui, N.; Owaki, H.; Ono, K. Repair of rabbit articular surfaces with allograft chondrocytes embedded in collagen gel. *J. Bone Joint Surg.* **1989**, *71B*, 74.
- (20) Nishimura, S.; Nishi, N.; Tokura, S. Adhesion behavior of murine lymphocytes on the surface of fibrous chitin and its derivatives. *Int. J. Biol. Macromol.* **1985**, *7*, 100.
- (21) Kim, Y. J.; Sah, R. L.; Doong, J. Y.; Grodzinsky, A. J. Fluorometric assay of DNA in cartilage explants using Hoechst 33258. *Anal. Biochem.* **1988**, *174*, 168.
- (22) Guo, J. F.; Jourdain, G. W.; MacCallum, D. K. Culture and growth characteristics of chondrocytes encapsulated in alginate beads. *Connect. Tissue Res.* **1989**, *19*, 277.
- (23) Hauselmann, H. J.; Fernandes, R. J.; Mok, S. S.; Schmid, T. M.; Block, J. A.; Aydelotte, M. B.; Kuettner, K. E.; Thonar, E. J. Phenotypic stability of bovine articular chondrocytes after long-term culture in alginate beads. *J. Cell Sci.* **1994**, *107*, 17.
- (24) Van Susante, J. L.; Buma, P.; Van Osch, G. J.; Versleyen, D.; Van der Kraan, P. M.; Van der Berg, W. B.; Homminga, G. M. Culture of chondrocytes in alginate and collagen carrier gels. *Acta Orthop. Scand.* **1995**, *66*, 549.
- (25) Chung, T. W.; Yang, J.; Akaike, T.; Cho, K. Y.; Nah, J. W.; Kim, S. I.; Cho, C. S. Preparation of alginate/galactosylated chitosan scaffold for hepatocyte attachment. *Biomaterials* **2002**, *23*, 2827.
- (26) Sakai, S.; Ono, T.; Ijima, H.; Kawakami, K. Control of molecular weight cutoff for immunoisolation by multilayering glycol chitosan-alginate polyion complex on alginate-based microcapsules. *J. Microencapsulation* **2000**, *17*, 691.
- (27) Wang, L.; Khor, E.; Lim, L. Y. Chitosan-alginate-CaCl₂ system for membrane coat application. *J. Pharm. Sci.* **2001**, *90*, 1134.
- (28) Campoccia, D.; Doherty, P.; Radice, M.; Brun, P. A. G.; Williams, D. F. Semisynthetic resorbable materials from hyaluronan esterification. *Biomaterials* **1998**, *19*, 2101.
- (29) Chen, W. Y.; Abatangelo, G. Functions of hyaluronan in wound repair. *Wound Repair Regen.* **1999**, *7*, 79.
- (30) Démarteau, O.; Wendt, D.; Braccini, A.; Jacob, D.; Schäfer, D.; Heberer, M.; Martin, I. Dynamic compression of cartilage constructs engineered from expanded human articular chondrocytes. *Biochem. Biophys. Res. Commun.* **2003**, *310*, 580.
- (31) Kiviranta, I.; Tammi, M.; Jurvelin, J.; Saamanen, A. M.; Helminen, H. J. Moderate running exercise augments glycosaminoglycans and thickness of articular cartilage in the knee joint of young beagle dogs. *J. Orthop. Res.* **1988**, *6*, 188.

- (32) Saamanen, A. M.; Tammi, M.; Kiviranta, I.; Jurvelin, J.; Helminen, H. J. Maturation of proteoglycan matrix in articular cartilage under increased and decreased joint loading. A study in young rabbits. *Connect. Tissue Res.* **1987**, *16*, 163.
- (33) Steinmeyer, J.; Knue, S. The proteoglycan metabolism of mature bovine articular cartilage explants superimposed to continuously applied cyclic mechanical loading. *Biochem. Biophys. Res. Commun.* **1997**, *240*, 216.
- (34) Vunjak-Novakovic, G.; Martin, I.; Obradovic, B.; Treppo, S.; Grodzinsky, A. J.; Langer, R.; Freed, L. E. Bioreactor cultivation conditions modulate the composition and mechanical properties of tissue-engineered cartilage. *J. Orthop. Res.* **1999**, *17*, 130.
- (35) Silver, F. H.; Bradica, G.; Tria, A. Elastic energy storage in human articular cartilage: estimation of the elastic modulus for type II collagen and changes associated with osteoarthritis. *Matrix Biol.* **2002**, *21*, 129.
- (36) Grant, G. T., Morris, E. R., Rees, D. A., Smith, P. J. C., Thom, D. Biological interactions between polysaccharides and divalent cations. *FEBS Lett.* **1973**, *32*, 195.

BM0400067



Feasibility of chitosan-based hyaluronic acid hybrid biomaterial for a novel scaffold in cartilage tissue engineering[☆]

Shintaro Yamane^{a,b,*}, Norimasa Iwasaki^{a,b}, Tokifumi Majima^{a,b}, Tadanao Funakoshi^{a,b},
Tatsuya Masuko^{a,b}, Kazuo Harada^c, Akio Minami^{a,b}, Kenji Monde^{b,d},
Shin-ichiro Nishimura^{b,d}

^a Department of Orthopaedic Surgery, Hokkaido University School of Medicine, Kita-ku Kita 14-jo Nishi 5-chyome, Sapporo 060-8648, Japan

^b Frontier Research Center for Post-genomic Science and Technology, Hokkaido University, Sapporo, Japan

^c Chemical Biology Institute, Sapporo, Japan

^d Laboratory of Bio-Macromolecular Chemistry, Division of Biological Sciences, Graduate School of Science, Hokkaido University, Sapporo, Japan

Received 14 October 2003; accepted 13 March 2004

Abstract

In this study, we hypothesized that hyaluronic acid could provide superior biological effects on the chondrocytes in a three-dimensional culture system. To test this hypothesis, we investigated the *in vitro* behavior of rabbit chondrocytes on a novel chitosan-based hyaluronic acid hybrid polymer fiber. The goal of the current study was to show the superiority of this novel fiber as a scaffold biomaterial for cartilage tissue engineering. Chitosan polymer fibers (chitosan group) and chitosan-based hyaluronic acid hybrid polymer fibers (HA 0.04% and HA 0.07% groups, chitosan coated with hyaluronic acid 0.04% and 0.07%, respectively) were originally developed by the wet spinning method. Articular chondrocytes were isolated from Japanese white rabbits and cultured in the sheets consisting of each polymer fiber. The effects of each polymer fiber on cell adhesivity, proliferation, morphological changes, and synthesis of the extracellular matrix were analyzed by quantitative cell attachment test, DNA quantification, light and scanning electron microscopy, semi-quantitative RT-PCR, and immunohistochemical analysis. Cell adhesivity, proliferation and the synthesis of aggrecan were significantly higher in the hybrid fiber (HA 0.04% and 0.07%) groups than in the chitosan group. On the cultured hybrid polymer materials, scanning electron microscopic observation showed that chondrocytes proliferated while maintaining their morphological phenotype and with a rich extracellular matrix synthesis around the cells. Immunohistochemical staining with an anti-type II collagen antibody demonstrated rich production of the type II collagen in the pericellular matrix from the chondrocytes. The chitosan-based hyaluronic acid hybrid polymer fibers show great potential as a desirable biomaterial for cartilaginous tissue scaffolds.

© 2004 Elsevier Ltd. All rights reserved.

Keywords: Chitin/chitosan; Chondrocyte; Hyaluronic acid/hyaluronan; Cell culture; Cell adhesion

1. Introduction

In living organisms, the authentic substrate for most cells is the extracellular matrix (ECM). The ECM adheres to cells via integrins, which are membrane-spanning heterodimeric receptors [1]. Through the cell-matrix adhesions, the ECM transduces physiological signals regulating cell growth, cell proliferation, cell differentiation, and matrix remodeling to the cells [1].

Therefore, the ECM plays an important role in living tissue development and regeneration.

In a tissue engineering technique, tissue regeneration is achieved by culturing isolated cells on biocompatible and biodegradable materials as scaffolds onto which cells are seeded. A large number of studies have shown the importance of selecting the appropriate biomaterials as scaffolds for the cell adhesion and supporting the proliferation [2–10]. For the reason given above, the ideal scaffold material should be one which closely mimics the natural environment in the tissue-specific ECM [9].

Once damaged, the articular cartilage consisting of hyaline cartilage tissue has little capacity for spontaneous

[☆] Supported by Regional Consortium Research Development Work.

*Corresponding author. Tel.: +81-11-706-1161x5937; fax: 81-11-706-6054.

E-mail address: s-yamane@med.hokudai.ac.jp (S. Yamane).

healing. Although the limited potential for self-repair of the articular cartilage necessitates operations to treat injured cartilage, no current procedures for cartilage repair have successfully regenerated long-lasting hyaline cartilage tissue to replace a cartilaginous lesion [11,12]. To solve this limitation, tissue engineering techniques by culturing isolated chondrocytes on a variety of scaffold materials, including naturally occurring and synthetic, have been developed [4–10]. However, there have been no ideal materials for cartilage tissue engineering.

One of the considerable characteristics in the cartilage tissue is that a small number of chondrocytes are embedded in the rich ECM. Therefore, cell–matrix interactions play a crucial role in the development and regeneration of the cartilage tissue. To successfully achieve cartilage tissue regeneration, a cell-carrier substance which closely mimics the natural environment in the cartilage-specific ECM must be developed. In the current study, hyaluronic acid, which is a main component of the proteoglycans (PGAs) in the cartilage, was applied to chitosan as a fundamental biomaterial.

Recently, several studies have demonstrated that cellular functions differ in two-dimensional and three-dimensional (3D) systems [13,14]. In cartilage tissue engineering, a closer approximation to *in vivo* environments should be attained by culturing cells in 3D materials. Additionally, the articular cartilage must be considered for its mobility as an excessively stressed tissue. To structurally mimic the environments of the cartilage tissue, the fundamental structure of a scaffold should be a 3D system with adequate mechanical strength. In the current study, the authors have structurally developed a novel polymer fiber—chitosan-based hyaluronic acid hybrid fiber—as a biomaterial to easily fabricate 3D scaffolds.

In this study, we hypothesized that hyaluronic acid could provide superior biological effects on the chondrocytes in a 3D culture system. To test this hypothesis, we investigated the *in vitro* behavior of rabbit chondrocytes on a novel chitosan-based hyaluronic acid hybrid polymer fiber. The objectives of the current study were to evaluate the chondrocyte adhesion, proliferation, and the synthesis of the ECMs in the chitosan-based hyaluronic acid hybrid polymer fiber and to show the superiority of this novel fiber as a scaffold biomaterial for cartilage tissue engineering.

2. Materials and methods

2.1. Polymer fibers

Polymer fibers were developed by the wet spinning method as described by Tamura et al. [15] with the following modification. Fig. 1 shows the process of

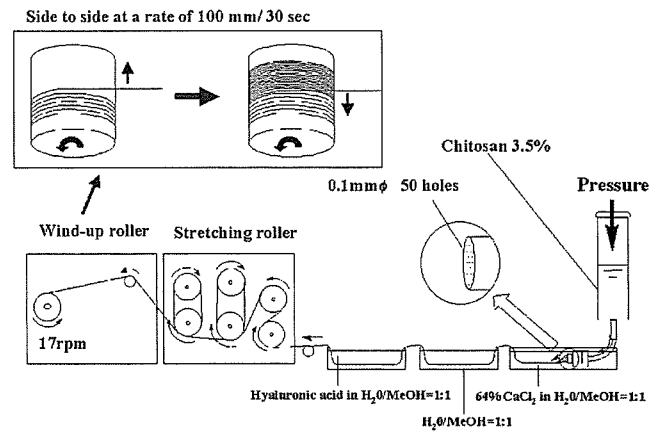


Fig. 1. The original roller system.

developing the fibers using an original apparatus [15]. Chitosan is a commercial material purchased from Kimitu Chemical Co. Inc., (Tokyo, Japan). Hyaluronic acid produced by lactic acid bacteria, with a viscosity average molecular weight of 2,400,000, was gifted from DENKI KAGAKU KOUGYO Co. Ltd. (Tokyo, Japan). The degree of deacetylation of the chitosan was 81%, and viscosity average molecular weight was 600,000. To prepare the polymer fiber 7 g of chitosan powder was dissolved in 200 ml of 2% aqueous acetic acid solution to give 3.5% of polymer concentration. Dope of chitosan was spun into a calcium coagulant bath (64% CaCl_2 dissolved in 50% aqueous methanol solution) through a stainless steel spinnlet (0.1 mm diameter, 50 holes) at a winding speed of 4.4 m/min at room temperature. Then, 50% aqueous methanol solution was used as a second coagulation bath and 0.04 or 0.07% hyaluronic acid dissolved in 50% aqueous methanol solution was a third coagulation bath. Using an original roller system (Okada Co. Inc., Sapporo, Japan), the resulting fibers were stretched and treated with 0.8% sodium hydroxide (NaOH) dissolved in 90% aqueous methanol solution to neutralize the acidity of the fibers. The fibers wound in the roller were washed with methanol and dried at room temperature. The diameter of each fiber was 0.03 mm. In the current study, chitosan polymer fiber (chitosan group) and chitosan-based hyaluronic acid hybrid polymer fiber (chitosan coated with hyaluronic acid 0.04%, HA0.04% group; chitosan coated hyaluronic acid 0.07%, HA0.07% group) were originally developed. For further investigations of the chondrocyte culture system, we automatically made a fiber sheet using the original apparatus (Fig. 1). Coagulated fibers were passed through a cross feeding guide and wound onto a stainless roller (120 mm diameter and 120 mm wide) at the rate of 17 rpm. The cross feeding guide set forward in the roller was moved from side to side at a rate of 100 mm/30 s. The cross-feed length and rotation count were 100 mm and 40 times,

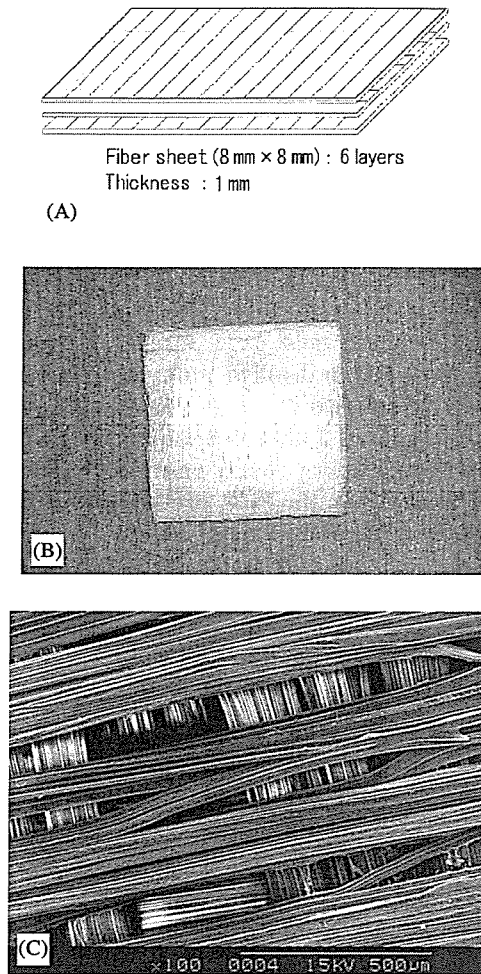


Fig. 2. (A,B) Three-dimensional (3D) scaffold material for the chondrocyte culture. Sheets consisting of each polymer fiber are stacked in a perpendicular pattern with six layers (8 × 8 mm, 1 mm thickness). (C) Scanning electron micrograph of the 3D scaffold material.

respectively. The fibers wound onto the roller were washed and dehydrated with methanol, and then dried at room temperature. The dry filaments were cut from the roller and a sheet fiber of filaments were piled 40 high (380 mm length, 100 mm wide and 0.25 mm thickness). The sheets consisting of each polymer fiber were cut into small sheets and stacked in a perpendicular pattern with six layers (8 × 8 mm, 1 mm thickness) (Fig. 2A,B,C). Each sheet was peripherally adhered with 2% chitosan gel and dried at 40°C for over night. During this process, we constantly obtained the same 3D fabrications. These 3D materials were sterilized in autoclave at 135°C for 20 minutes for the chondrocyte culture.

2.2. Measurement of material properties

Material properties of five samples in each fiber group were measured according to the Japanese Industrial

Standards L1015. Tensile tests for each fiber group were performed at a crosshead speed of 20 mm/min using a material testing machine (P/N346-51299-02, SHIMADZU, Kyoto, Japan). The cross-sectional area was determined using a microscope (BX50, OLYMPUS, Tokyo, Japan) and a video dimension analyzer (VM-30, OLYMPUS, Tokyo, Japan).

2.3. Chondrocyte suspension

Ten week old Japanese white rabbits with a mean body weight of 2.0 kg (Hokudo, Sapporo, Japan) were used in this study. Articular cartilage slices, gathered from the knee, the hip, and the shoulder joints of each animal, were detached from the adherent connective tissues. Cartilage specimens were minced like paste and washed three times in sterile 0.9% sodium chloride. Then, the chondrocytes were isolated with 0.25% trypsin (Difco Lab., Detroit, MI) in sterile saline for 30 minutes followed by 0.25% collagenase (Worthington, Freehold, NJ) in Dullbecco's modified Eagle's medium (SIGMA Chemical Co., St. Louise, MO) supplemented with 10% fetal bovine serum (Invitrogen Corp., Carlsbad, CA), 100 IU/ml penicillin, 100 μg/ml streptomycin, and 0.25 μg/ml fungizone (BIOWHITAKER, Walkersville, MD) for 6 h at 37°C in a culture bottle. Finally, the isolated cells were collected by centrifugation (1,500 g, 37°C, 5 min) after removal from the culture bottle and washed three times with the culture medium. The final cell density of chondrocyte suspension was adjusted for further investigations.

2.4. Cell adhesion study

Chondrocyte adhesion to the polymer fibers was assessed by the method as previously reported by Nishimura et al. [16]. The polymer fibers of Polyglactin 910, a 90:10 copolymer of glycolide and lactide, coated with polyglactin 370 (9-0 Vicryl suture material, Ethicon Co., Somerville, NJ), were used as control materials. The fibrous samples were cut into 10 mm pieces and packed in Teflon tubes (25 mm length, 4.8 mm inner diameter) and then 0.1 ml of chondrocyte suspension containing 0.5×10^6 cells was loaded on the column at room temperature. The cells were allowed to adhere in a humidified incubator (37°C, 5% CO₂) for 1 h. Each column was gently rinsed with 1 ml of 1 M phosphate-buffered saline (PBS), and the number of unattached cells in the rinsed solution was quantified by microscopic observation using a hemocytometer. Parallel samples of $n = 5$ were used for each group of polymer fiber.

2.5. Chondrocyte culture

The 3D scaffold materials mentioned previously were used for the chondrocyte culture. Chondrocyte suspension

containing 0.6×10^6 cells was embedded on the materials. These samples were placed in a 37°C, humidified 5% CO₂ incubator for 1 h and then overlaid with 2 ml of the culture medium. Chondrocyte cultures were placed in a humidified incubator and replaced with a fresh medium twice a week.

2.6. DNA quantification

At 1, 7, and 14 days after cultivation, 5 cultured materials of each fiber group were harvested to quantify the total amount of DNA. The DNA content ($\mu\text{g}/\text{sample}$) was measured in aliquots of the sodium citrate (0.05 M phosphoric acid, 2 M NaCl) dissolved powdered samples by the modified fluorometric assay using a bisbenzimidazole dye (Hoechst dye 33258, Polyscience Inc., Northampton, UK) [17]. In fluorescence measurements, disposable cuvettes were used; the excitation wavelength was 356 nm and the emission wavelength was 458 nm. The results were extrapolated from a standard curve using salmon testis DNA (Worthington, Freehold, NJ).

2.7. RNA isolation

After 14 days of culture, samples of each fiber group were frozen in liquid nitrogen prior to RNA extraction. Total RNA was extracted by the TRIspin method described previously [18]. Briefly, frozen samples were powdered in liquid nitrogen cooled with Brown Dismembrater vessels (B. Braun Biotech., Allentown, PA). The TRIzol reagent (Life Technologies, Gaithersburg, MD) was added to the powdered tissue at the rate of 1 ml/100 mg sample weight and the samples warmed to room temperature. The samples, to which chloroform was added, were centrifuged at 12,000 g for 15 min at 4°C. Then, the upper aqueous phase containing the RNA was obtained and mixed with 70% ethanol. Finally, total RNA was isolated using the RNeasy total RNA kit (Qiagen, Chatsworth, CA) according to the manufacturer's protocol.

2.8. Semiquantitative reverse transcriptase-polymerase chain reaction (RT-PCR) analysis

Total RNA yield was fluorometrically quantified with the SYBR[®] Green reagent (Molecular Probes, Eugene, OR) according to the manufacturer's recommendations. According to the previous reports, semiquantitative RT-PCR analysis was performed using rabbit specific primer sets for type I collagen, type II collagen, aggrecan, and a housekeeping gene, glyceraldehyde-3-phosphate dehydrogenase (GAPDH) [19–22]. First, 1 μg of total RNA was reverse-transcribed into cDNA using the StratScript RNase H⁻ kit (Stratagene, La Jolla, CA). Second, aliquots (1.5 μl of 50 μl total value) of the

resulting cDNA were amplified in a total volume of 50 μl containing PCR buffer, 0.2 μM dNTP mixture, 1.5 mM MgCl₂, 0.5 μM of each primer, and 1 unit of the Taq DNA polymerase (Life Technologies Inc., Gaithersburg, MD). As reported previously, conditions were determined to be in the linear range for both the PCR amplification and the image analysis system [19–22]. The PCR products were separated by electrophoresis of 20 μl of each reaction mixture in a 2% agarose gel at 100 V/cm in 1 \times Tris-acetate-EDTA buffer. Following electrophoresis, the gels were stained with ethidium bromide, destained in distilled water and photographed using a charge coupled device (CCD) camera. Comparison to the standard 1 kb DNA ladder (Life Technologies Inc., Gaithersburg, MD) ensured proper size of PCR products. Then, the PCR products were separated by electrophoresis. Finally, the images were captured with a CCD camera and analyzed with Quantity One (PDI, Inc., Huntington Station, NY). To yield a semi-quantitative assessment of the gene expression, the data were expressed as normalized ratios by comparing the integrated density values for the genes in question with those for GAPDH.

2.9. Morphological and immunohistochemical analysis

Cell morphology in the 3D scaffold material was observed by light microscopy and scanning electron microscopy (SEM) at 14 days after cultivation. At the end of the cultivation period, all samples were rinsed with Ringer's solution to remove nonattached cells. The cells in the material were fixed over night with 2.5% glutaraldehyde supplemented with 0.1 M phosphate buffer. After fixation, the SEM specimens were rinsed with 0.1 M phosphate buffer and fixed in 1% OsO₄ for 1 h, then soaked in 1% tannic acid for an additional 1 h. These processes were repeated three times. The specimens were dehydrated through a graded ethanol series and dried at the critical point of CO₂. The specimens were then mounted on an aluminum stub and sputtered with argon using an ion coater (Hitachi, Tokyo, Japan), and viewed with a SEM (Hitachi S-4500, Hitachi, Tokyo, Japan) immediately after preparation. Immunohistochemical stains were performed with anti-type I and anti-type II collagen antibodies (Fuji Pharm. Lab., Toyama, Japan) to detect expression of the type I and type II collagen products.

2.10. Statistical analysis

All data were represented as mean \pm standard error. Statistical comparisons were performed using one-way analysis of variance (ANOVA) and Fisher's PLSD test. Differences were considered significant for $p < 0.05$.

3. Results

3.1. Material properties

The tensile strength of each fiber group was $87.4 \pm 2.0 \text{ N/mm}^2$ in the chitosan group, $168.2 \pm 7.0 \text{ N/mm}^2$ in the HA0.04% group, and $144.4 \pm 2.1 \text{ N/mm}^2$ in the HA0.07% group. The values of the hyaluronic acid hybrid fiber significantly increased as compared with that of the chitosan fiber ($p < 0.0001$). The strain at failure was $11.2 \pm 1.7\%$ in the chitosan group, $9.8\% \pm 2.4\%$ in the HA0.04% group, and $9.7 \pm 1.9\%$ in the HA0.07% group. There were no significant differences among the 3 groups.

3.2. Cell adhesion

Adhesivities of the chondrocytes were expressed by the percentage of chondrocytes trapped in the column to the total chondrocytes loaded on the column (0.5×10^6 cells). The percentage was $53.3 \pm 7.1\%$ in the control group, $79.3 \pm 2.2\%$ in the chitosan group, $95.1 \pm 1.3\%$ in the HA0.04% group, and $90.5 \pm 3.2\%$ in the HA0.07% group. The values in the HA 0.04% and HA 0.07% groups were significantly higher than that in the control ($p < 0.0001$) and in the chitosan groups ($p < 0.05$).

3.3. Cell proliferation

Light micrographs (Fig. 4) showed the proliferation of chondrocytes on all the fibers at 14 days after cultivation. From day 1 to day 14 of the culture period, the total amount of DNA increased in all the fiber groups (Fig. 3). After 7 days in culture, the total amount of DNA in each group was $134.5 \pm 3.9 \mu\text{g/sample}$ in the chitosan group, $142.2 \pm 11.2 \mu\text{g/sample}$ in the HA0.04% group, and $240.1 \pm 23.0 \mu\text{g/sample}$ in the HA0.07% group. The value in the HA 0.07% group was significantly higher than that in the chitosan and HA0.04% groups ($p < 0.05$). On the other hand, at 14 days after cultivation, there were no significant differences among the 3 groups.

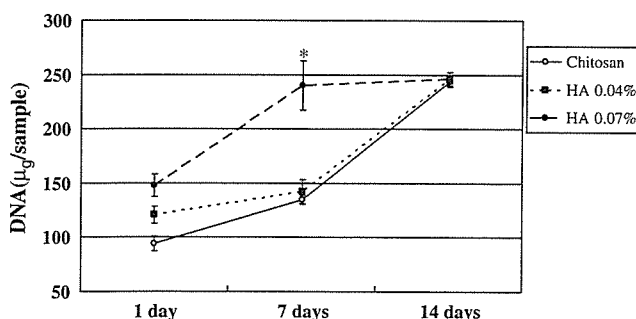


Fig. 3. The increase of DNA content per sample ($\mu\text{g/sample}$) in the chitosan and hybrid 3D scaffolds seeded with chondrocytes. * $p < 0.05$ versus the other groups. $N = 5$, mean \pm standard error.

3.4. Cell morphology


There was no effect of fiber material on cell morphology at 14 days after cultivation. Light micrographs (Fig. 4) and SEM micrographs (Fig. 5A,B) revealed the characteristic round morphology of the chondrocytes on all the fibers.

3.5. Extracellular matrix products

The SEM micrographs revealed the dense fiber, which indicated the type II collagen, in interstitial space between the fibers (Fig. 5B). At 14 days after cultivation, the quantity of total mRNA yield per mg wet weight in the chitosan group, in the HA0.04% group, and in the HA0.07% group were 0.27 ± 0.02 , 0.24 ± 0.02 , and $0.15 \pm 0.02 \mu\text{g/mg}$, respectively. The mRNA for GAPDH was well expressed in all samples. Based on the analysis of $1 \mu\text{g}$ of total RNA converted to cDNA by RT from each sample, integrated density values of GAPDH in the linear PCR range (25 cycles) of the chitosan group, of the HA0.04% group, and of the HA0.07% group were 0.20 ± 0.01 , 0.22 ± 0.01 , and 0.20 ± 0.01 integrated density units, respectively. There were no significant differences in GAPDH band density among the 3 groups. These results support the normalization of subsequent assessments to this gene. At 14 days the culture materials, normalized ratio of mRNA of type I collagen, of type II collagen, and of aggrecan to that of GAPDH is summarized in Table 1. In the values of type I and type II collagen, there were no statistically significant differences among the 3 groups (Table 1 and Fig. 6). On the other hand, no expression of the mRNA of the aggrecan was identified in the chitosan group (Table 1 and Fig. 6). The normalized ratio of the HA0.07% group significantly increased, as compared to that in the HA0.04% group ($p < 0.05$). In a histochemical study, safranin O lightly stained the pericellular matrix around the chondrocytes in all the fibers at 14



Fig. 4. Light micrograph of chondrocytes proliferated in the 3D scaffold material consisting of the chitosan-based 0.04% hyaluronic acid hybrid polymer fiber at 14 days after cultivation (hematoxylin-eosin staining, original magnification $\times 50$).

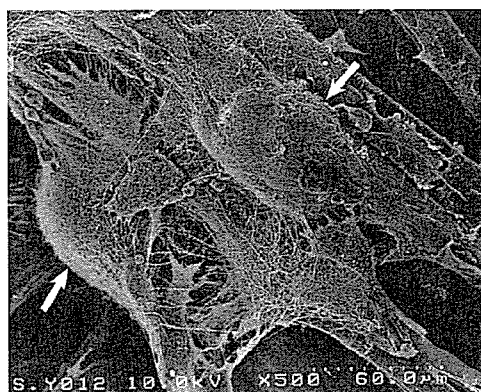

(A)



(B)

Fig. 5. Scanning electron micrographs of the chondrocytes seeded on the 3D scaffold material consisting of the chitosan-based 0.07% hyaluronic acid hybrid polymer fiber at 14 days after cultivation. (A) Scaffold superficial surface; (B) scaffold sagittal surface. The characteristic round morphology of the chondrocytes (white arrows) and the dense fibers of the type II collagen can be found around the chondrocytes. Arrow heads, polymer fiber.

Table 1

Material groups (n = 5)	Type II collagen	Aggrecan	Type I collagen
Chitosan group	1.51 ± 0.07	No expression	0.45 ± 0.04
HA 0.04% group	1.59 ± 0.07	1.07 ± 0.17	0.60 ± 0.11
HA 0.07% group	1.37 ± 0.12	1.59 ± 0.09*	0.43 ± 0.11

* *p* = 0.025 versus HA 0.04% group.

days after cultivation. Immunohistochemical staining with an anti-type II collagen antibody demonstrated rich type II collagen production in the pericellular matrix (Fig. 7A). However, there was no staining for type I collagen in all the fibers (Fig. 7B).

4. Discussion

The final goal of the current study was to clarify the feasibility of the novel chitosan-based hyaluronic acid

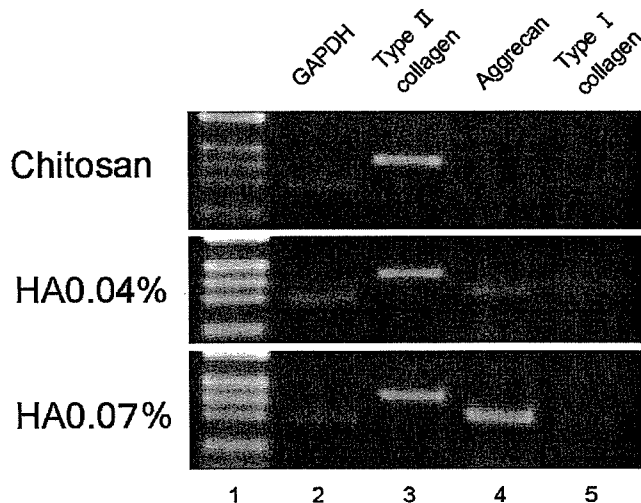


Fig. 6. Reverse transcriptase-polymerase chain reaction (RT-PCR) analysis in the chitosan, the HA0.04%, and the HA0.07% group specimens. Lane 1, ladder marker; lane 2, GAPDH; lane 3, type II collagen; lane 4, aggrecan; lane 5, type I collagen. At 14 days after cultivation, the mRNA for type II collagen was well expressed in all specimens. On the other hand, no expression of the mRNA of the aggrecan was identified in the chitosan group specimens.

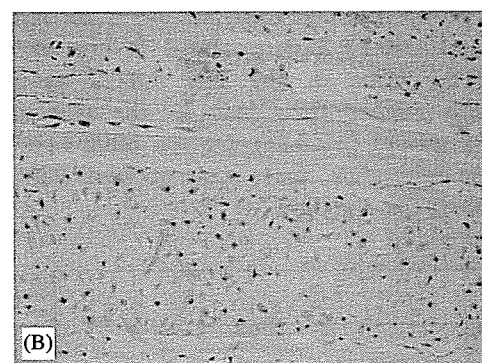
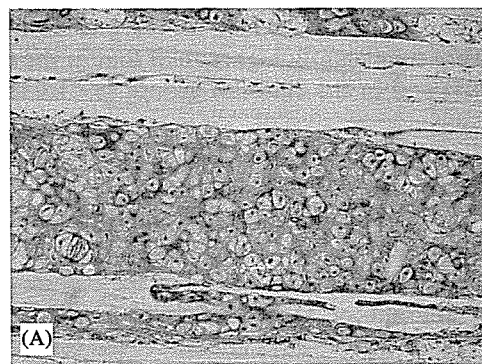


Fig. 7. Immunohistochemical stainings with anti-type I and II collagen antibodies. A, Rich production of type II collagen is indicated in the HA0.07% group. B, No staining of type I collagen is found in the HA0.07% group. (original magnification × 100).

hybrid polymer fibers as a scaffold biomaterial for cartilage tissue engineering. Recently, several reports have shown the potential of chitosan scaffold biomaterial for cartilage tissue engineering [6,8,9,44]. Suh and

Matthew [9] reported that chitosan is well suited as a carrier material for the transplant of autologous chondrocytes. Our results demonstrated that adhesion, proliferation, and ECM products of the chondrocytes were significantly higher on the hybrid polymer fibers than on the non-hybrid chitosan polymer fiber, which is well accepted as a scaffold material. Based on these previous and our current results, we reasonably conclude that the chitosan-based hyaluronic acid hybrid polymer fibers have a great potential as a desirable biomaterial in cartilage tissue scaffolds.

Of emphasis in our novel biomaterial is that hyaluronic acid, which is a main component of cartilage glycosaminoglycans (GAGs), is applied to chitosan as a fundamental substance. The ideal cell-carrier substance should be one which closely mimics the natural environment in the cartilage ECM. Glycosaminoglycans, which are parts of the cartilage ECM components, play an important role in regulating expression of the chondrocyte phenotype and in supporting chondrogenesis [8,23–26]. Therefore, the application of hyaluronic acid as a component of the cartilage scaffold biomaterial must be a reasonable approach for enhancing chondrogenesis. Concerning the cell adhesivity of hyaluronic acid, Zimmerman et al. [27] showed that hyaluronic acid is an adhesion modulator molecule, which can mediate the early stage of cell-substrate interaction. On the other hand, CD44 is well known as a cell surface receptor for hyaluronic acid [28,29]. CD44 is a transmembrane glycoprotein expressed in a variety of cell types in connective tissues and a major cell surface protein in chondrocytes. This has been postulated to have a function as the principal receptor for hyaluronic acid, a common GAG component of the ECMs [29–31]. Murdoch et al. [32] demonstrated that there was a dramatic increase of CD44 expression on the isolated chondrocytes from the cartilage. Based on these previous data and the current results, we reasonably conclude that scaffold biomaterials introducing hyaluronic acid can provide excellent chondrocyte adhesive activity.

In the current study, another important point is that a polymer fiber has been applied to the scaffold biomaterial. A scaffold for cartilage tissue engineering requires adequate mechanical strength to maintain the initial shape of the implanted scaffold. Several studies have demonstrated the chondrogenic potential of GAGs-augmented chitosan hydrogels [8,45]. However, these hydrogels do not have the required mechanical strength as mentioned above. Therefore, scaffolds consisting of these hydrogels cannot be transplanted into large cartilaginous lesions in advanced degenerative diseases such as osteoarthritis and rheumatoid arthritis. To solve this drawback, we have developed a new polymer fiber as a fundamental material for 3D fabric. The obtained data showed a significant increase of mechanical

strength in the hyaluronic acid hybrid fibers. This indicates that introducing hyaluronic acid to the fundamental materials plays an important role in increasing the material properties of the scaffold. Tamura et al. [15] reported the enhancement of tensile strength by the coating of alginate fiber with chitosan. Ionic interaction is the most convenient way to form a tight bond between two molecules. They concluded that the tight bond of chitosan to alginate increased the tensile strength of the hybrid fibers. In the current study, the tensile strength of a chitosan polymer fiber increased by applying hyaluronic acid coating. As chitosan is a cationic polysaccharide consisting of glucosamine residues and hyaluronic acid has anionic behavior, a tight bond between both molecules was expected. The main reason for the increase of mechanical strength in the novel hybrid fiber is this tight bond between chitosan and hyaluronic acid polymers. The novel fabric consisting of chitosan-based hyaluronic acid hybrid polymer fibers will serve as an ideal scaffold with adequate strength for cartilage tissue engineering.

Chitosan is a partially deacetylated derivative of chitin, the primary structural polymer in arthropod exoskeletons. Structurally, chitosan is a linear polysaccharide consisting of $\beta(1 \rightarrow 4)$ linked D-glucosamine residues with a variable number of randomly located *N*-acetyl-glucosamine groups. The average molecular weight ranges from 50 to 1000 kDa. The potential of chitosan as a biomaterial is based on its cationic nature and high charge density in solution. Madihally et al. [6] reported that the cationic nature of chitosan allowed for electrostatic interactions with anionic GAGs, PGAs, and other negatively charged species. These ionic interactions may serve as a mechanism for retaining and recruiting cells, growth factors, and cytokines within a tissue scaffold. Consequently, chitosan has been already employed as an excellent biomaterial for wound healing and tissue repair [33–35]. Since chitosan is regarded as a cationic polysaccharide showing excellent cell supporting properties, a hybrid material composed of chitosan combined with hyaluronic acid might prove to be a novel class of polyion complex effective for cartilage specific scaffolds.

The current strategies for the treatment of damaged adult articular cartilage are limited. To solve the limitations of the current operations such as osteotomies and total joint arthroplasties, several tissue engineering techniques have been developed and clinically applied to such lesions [42,43]. However, because of the mechanical weakness of scaffold materials and the limited number of donor cells, the present techniques can be used only for relatively small cartilaginous lesions following traumatic injuries and osteochondritis dessecans. Ideally, a tissue engineering technique could be available as an alternative to the current operations mentioned above for the treatment of large cartilaginous lesions

in degenerative diseases, including osteoarthritis and rheumatoid arthritis. In articular cartilage tissue engineering, we must consider that the articular cartilage is subject to excessive compression and shear stress. Therefore, to maintain the initial shape of the scaffold surface and the number of attached chondrocytes, adequate mechanical strength and highly cellular adhesivity are requirements for scaffold materials in cartilage tissue engineering. The other consideration is that the chondrocytes exhibit a profound change in their phenotype after isolation from the ECM. They show the development of a fibroblastic morphology and a switch in production from type II collagen to type I collagen. To maintain the chondrocyte phenotype through the process of cartilage regeneration, scaffold material must have the potential to support the chondrogenesis while maintaining the chondrocyte phenotype. Based on the current data, for cartilage tissue engineering, we may reasonably conclude that our novel chitosan-based hyaluronic acid hybrid polymer fiber serves as an ideal biomaterial to create a 3D fabricated scaffold with adequate strength, high cellular adhesivity, and excellent support for chondrogenesis. In the current study, we focused not on the shape or structure of the 3D fabrication for cartilage tissue, but on the development and assessment of the chitosan-based hyaluronic acid hybrid fiber as a cartilage tissue engineering scaffold. Using the novel 3D scaffold material with these properties, this tissue engineering technique would be applied to the treatment of large cartilaginous lesions in a variety of diseases such as osteoarthritis and rheumatoid arthritis.

A considerable limitation of this study is that the results were derived from an *in vitro* experimental model. Therefore, the biocompatibility of the current fibrous material in living joints is still unclear. A number of studies have reported the tissue response to various chitosan-based materials [36–41]. In general, these chitosan materials have been observed to evoke a minimal foreign body reaction. Sue and Matthew [9] stated that this reaction may play a role in inducing local cell proliferation and ultimately integration of the implanted material with the host tissue. However, the biocompatibility or immunological reaction of fibrous chitosan material to the joint tissue remains unclear. In addition, the process of degradation or absorption of the current fibrous material in the articular environment is still unknown. A further direction of our study will be to clarify these points using animal experimental models. Finally, further research will be needed to determine the adequate shape, pore size and mechanical properties of a 3D fabrication for cartilage tissue regeneration.

Although there is a considerable limitation as mentioned above, the data derived from this study suggest great promise for the future of chitosan-based hyaluronic acid hybrid polymer fibers as a scaffold biomaterial.

The novel scaffold material will be applied to cartilage tissue engineering for relatively wide cartilaginous lesions caused by various joint diseases, including osteoarthritis and rheumatoid arthritis.

Acknowledgements

This work was partly supported by the Hokkaido Bureau of Economy, Trade and Industry, Northern Advancement Center for Science & Technology in Hokkaido, and Grant-in Aid for Scientific Research (B-1539044) from Japan Society for the Promotion of Science. Also, the authors would like to thank Mr. Tohru Mitsuno and Mr. Shouzo Miyoshi (General Research Center, DENKI KAGAKU KOUGYO Co. Ltd., Tokyo, Japan) for their excellent technical assistance in fiber preparation.

References

- [1] Hynes RO. Cell adhesion: old and new questions. *Trends Cell Biol* 1999;9:M33–77.
- [2] Huttmacher DW. Scaffolds in tissue engineering bone and cartilage. *Biomaterials* 2000;21:2529–43.
- [3] LeBaron RG. Athanasiou ka. Ex vivo synthesis of articular cartilage. *Biomaterials* 2000;21:2575–87.
- [4] Aigner J, Tegeler J, Hutzler P, Campoccia D, Pavesio A, Hammer C, Kastenbauer E, Nauman A. Cartilage tissue engineering with novel nonwoven structured biomaterial based on hyaluronic acid benzyl ester. *J Biomed Mater Res* 1998;42:172–81.
- [5] Ishaug-Riley SL, Okun LE, Prado G, Applegate MA, Ratcliffe A. Human articular chondrocyte adhesion and proliferation on synthetic biodegradable polymer films. *Biomaterials* 1999;20:2245–56.
- [6] Madhally SV, Matthew HW. Porous chitosan scaffolds for tissue engineering. *Biomaterials* 1999;20:1133–42.
- [7] Nehrer S, Breina HA, Ramappa A, Shortkroff S, Young G, Minas T, Sledge CB, Yannas IV, Spector M. Canine chondrocytes seeded in type I and type II collagen implants investigated *in vitro*. *J Biomed Mater Res* 1997;38:95–104.
- [8] Sechrist VF, Miao YJ, Niyibizi C, Westerhausen-Larson A, Matthew HW, Evans CH, Fu SH, Suh JK. GAG-augmented polysaccharide hydrogel: a novel biocompatible and biodegradable material to support chondrogenesis. *J Biomed Mater Res* 2000;49:534–41.
- [9] Suh JKF, Matthew HWT. Application of chitosan-based polysaccharide biomaterials in cartilage tissue engineering: a review. *Biomaterials* 2000;21:2589–98.
- [10] Vacanti CA, Langer R, Vacanti JP. Synthetic polymers seeded with chondrocytes provide a template for new cartilage formation. *Plast Reconstr Surg* 1991;88:753–9.
- [11] Caplan AI, Elyaderani M, Mochizuki Y, Wakitani S, Goldberg VM. Principles of cartilage repair and regeneration. *Clin Orthop Rel Res* 1997;342:254–69.
- [12] Minas T, Nehrer S. Current concepts in the treatment of articular cartilage defects. *Orthopaedics* 1997;20:525–38.
- [13] Hauselmann HJ, Fernandes RJ, Mok SS, Schmid TM, Block JA, Aydelotte MB, Kuettner KE, Thonar EJ. Phenotypic stability of bovine articular chondrocytes after long-term culture in alginate beads. *J Cell Sci* 1994;107:17–27.

- [14] Kimura T, Yasui N, Ohsawa S, Ono K. Chondrocytes embedded in collagen gels maintain cartilage phenotype during long-term cultures. *Clin Orthop Rel Res* 1984;186:231–9.
- [15] Tamura H, Tsuruta Y, Tokura S. Preparation of chitosan-coated alginate filament. *Mater Sci Eng C* 2002;20:143–7.
- [16] Nishimura S, Nishi N, Tokura S. Adhesion behaviour of murine lymphocytes on the surface of fibrous chitin and its derivatives *Int J Biol Macromol* 1985;7:100–4.
- [17] Kim YJ, Sah RL, Doong JY, Grodzinsky AJ. Fluorometric assay of DNA in cartilage explants using Hoechst 33258. *Anal Biochem* 1988;174:168–76.
- [18] Reno C, Marchuk L, Sciore P, Frank CB, Hart DA. Rapid isolation of total RNA from small samples of hypocellular, dense connective tissues. *Biotechniques* 1997;22:1082–6.
- [19] Majima T, Marchuk L, Sciore P, Shrive N, Frank CB, Hart DA. Compressive compared with tensile loading of medial collateral ligament scar in vitro uniquely influences mRNA levels for aggrecan, collagen type II, and collagenase. *J Orthop Res* 2000;18:524–31.
- [20] Hart DA, Boykiw R, Sciore P, Reno C. Complex alterations in gene expression occur in the knee ligaments of the skeletally mature multiparous rabbit during pregnancy. *Biochim Biophys Acta* 1998;1397:331–41.
- [21] Marchuk L, Sciore P, Reno C, Frank CB, Hart DA. Postmortem stability of total RNA isolated from rabbit ligament, tendon and cartilage. *Biochim Biophys Acta* 1997;1379:171–7.
- [22] Sciore P, Boykiw R, Hart DA. Semiquantitative reverse transcription-polymerase chain reaction analysis of mRNA for growth factors and growth factor receptors from normal and healing rabbit medial collateral ligament tissue. *J Orthop Res* 1998;16:429–37.
- [23] Kato Y, Mukudai Y, Okimura A, Shimazu A, Nakamura S. Effect of hyaluronic acid on the release of cartilage matrix proteoglycan and fibronectin from the cell matrix layer of chondrocyte cultures: interactions between hyaluronic acid and chondroitin sulfate glycosaminoglycan. *J Rheumatol Suppl.* 1995; 43:158–9.
- [24] Shimazu A, Jikko A, Iwamoto M, Koike T, Yan W, Okada Y, Shinmei M, Nakamura S, Kato Y. Effect of hyaluronic acid on the release of the proteoglycan from the cell matrix in rabbit chondrocyte culture in the presence and absence of cytokines. *Arthr Rheum* 1993;36:247–53.
- [25] Larsen NE, Lombad KM, Parent EG, Balazs EA. Effect of hylan on cartilage and chondrocyte cultures. *J Orthop Res* 1992;10:23–32.
- [26] Kawasaki K, Ochi M, Uchio Y, Adach N, Matsusaki M. Hyaluronic acid enhances proliferation and chondroitin sulfate synthesis in cultured chondrocyte embedded in collagen gels. *J Cell Physiol* 1999;179:142–8.
- [27] Zimmerman E, Geiger B, Addadi L. Initial stages of cell-matrix adhesion can be mediated and modulated by cell-surface hyaluronan. *Biophys J* 2002;82:1848–57.
- [28] Chow G, Knudson CB, Homandberg G, Knudson W. Increased expression of CD44 in bovine articular chondrocytes by catabolic cellular mediators. *J Biol Chem* 1995;270:27734–41.
- [29] Underhill C. CD44: the hyaluronan receptor. *J Cell Sci* 1992;103: 293–8.
- [30] Aruffo A, Stamenkovic I, Melnick M, Underhill CB, Seed B. CD44 is the principal cell surface receptor for hyaluronate. *Cell* 1990;61:1303–13.
- [31] Laurent TC, Fraser JR. Hyaluronan. *FASEB J* 1992;6:2397–404.
- [32] Murdoch AD, Oldershaw RA, Hardingham TE. Differential regulation of cell-surface proteoglycans by chondrocytes during adaptation to cell culture. 49th Annual Meeting of the Orthopaedic Research Society 2003; No 0220.
- [33] Muzzarelli RA, Biagini G, Bellardini M, Simonelli L, Castaldini C, Fratto G. Osteoconduction exerted by methylpyrrolidinone chitosan used in dental surgery. *Biomaterials* 1993;14: 39–43.
- [34] Hirano S, Seino H, Akiyama Y, Nonaka I. Chitosan a biocompatible materials for oral and intravenous administrations. In: Gebelein CG, Dunn RL, editors. *Progress in biomedical polymers*. New York: Plenum Publishing Co.; 1990. p. 283–90.
- [35] Mori T, Okamura M, Matsuura H, Ueno K, Tokura S, Okamoto Y, Minami S, Fujinaga T. Effect of chitin and its derivatives on the proliferation and cytokine production of fibroblast in vitro. *Biomaterials* 1997;18:947–51.
- [36] Rao SB, Sharma CP. Use of chitosan as a biomaterial: studies on its safety and hemostatic potential. *J Biomed Mater Res* 1997;34:21–8.
- [37] Muzzarelli RAA. Human enzymatic activities related to the therapeutic administration of chitin derivatives. *Cell Mol Life Sci* 1997;53:131–40.
- [38] VandeVord PJ, Matthew HWT, DeSilva SP, Mayton L, Wu B, Wooley PH. Evaluation of the biocompatibility of a chitosan scaffold in mice. *J Biomed Mater Res* 2002;59:585–90.
- [39] Tomihata K, Ikada Y. In vitro and in vivo degradation of films of chitin and its deacetylated derivatives. *Biomaterials* 1997;18: 567–75.
- [40] Denuziere A, Ferrier D, Damour O, Domard A. Chitosan-chondroitin sulfate and chitosan-hyaluronate polyelectrolyte complexes: biological properties. *Biomaterials* 1998;19:1275–85.
- [41] Lu JX, Prudhommeaux F, Meunier A, Sedel L, Guillemain G. Effects of chitosan on rat knee cartilages. *Biomaterials* 1999;20: 1937–44.
- [42] Brittberg M, Tallheden T, Sjogren-Jansson B, Lindahl A, Peterson L. Autologous chondrocytes used for articular cartilage repair: an update. *Clin Orthop Rel Res* 2001;391(Suppl):S337–48.
- [43] Ochi M, Uchio Y, Kawasaki K, Wakitani S, Iwasa J. Transplantation of cartilage-like tissue made by tissue engineering in the treatment of cartilage defect of the knee. *J Bone Joint Surg Br* 2002;84:571–8.
- [44] Nettles DL, Elder SH, Gilbert JA. Potential use of chitosan as a cell scaffold material for cartilage tissue engineering. *Tissue Eng* 2002;8:1009–16.
- [45] Risbud M, Ringe J, Bhonde R, Sittinger M. In vitro expression of cartilage-specific markers by chondrocytes on a biocompatible hydrogel: implications for engineering cartilage tissue. *Cell Transplant* 2001;10:755–63.



Chitosan–RGDSGGC conjugate as a scaffold material for musculoskeletal tissue engineering[☆]

Tatsuya Masuko^{a,b}, Norimasa Iwasaki^{a,b}, Shintaro Yamane^{a,b},
Tadanao Funakoshi^{a,b}, Tokifumi Majima^{a,b}, Akio Minami^{a,b}, Noriko Ohsuga^c,
Takashi Ohta^c, Shin-Ichiro Nishimura^{c,*}

^aDepartment of Orthopaedic Surgery, Hokkaido University School of Medicine, Kita-15, Nishi-7, Kita-Ku, Sapporo 060-8638, Japan

^bFrontier Research Center for the Post-Genomic Science and Technology, Hokkaido University, Kita-21, Nishi-11, Kita-Ku, Sapporo 001-0021, Japan

^cLaboratory of Bio-Macromolecular Chemistry, Division of Biological Sciences, Graduate School of Science, Frontier Research Center for the Post-Genomic Science and Technology, Hokkaido University, Kita-21, Nishi-11, Kita-Ku, Sapporo 001-0021, Japan

Received 26 October 2004; accepted 25 January 2005

Available online 13 March 2005

Abstract

In the present study, we have developed a novel and versatile method for the preparation of chitosan-peptide complex based on the selective reaction of chitosan with 2-iminothiolane. The new type of SH-chitosan derivative showed an excellent solubility to aqueous solution even in the alkaline conditions. This characteristic greatly facilitated further modification study of chitosan with a variety of bioactive substances. A synthetic peptide, RGDSGGC containing RGDS moiety that is known as one of the most important cell adhesive peptides, was readily coupled by disulfide bonds formation with sulfhydryl groups of SH-chitosan in the presence of dimethyl sulfoxide. Next, the effect of the introduction of RGDSGGC moiety to chitosan on cell adhesion and proliferation activity of chondrocytes and fibroblasts were evaluated. As a result, it was suggested that this polysaccharide-peptide conjugate exhibited excellent capacities for both cell adhesion and cell proliferation of chondrocytes and fibroblasts. Considering the growing importance of the biocompatible scaffolds in the recent tailored tissue engineering technique, these results indicate that the present strategy of 2-iminothiolane-based conjugation of polysaccharides with biologically active peptides will become a key and potential technology to develop desirable scaffold materials for the tissue regenerations.

© 2005 Elsevier Ltd. All rights reserved.

Keywords: Adhesion; Chondrocyte; Fibroblast; Peptide; Polysaccharide

1. Introduction

The ideal treatment for severely injured tissues is that the involved tissues are replaced with functional ones. However, the current advanced treatments such as reconstructive surgeries and allogeneic transplantations

have the possibility of occurring functional loss of a self-donor organ or tissue and lethal side effects derived from immunosuppressants. Recently, to overcome these limitations in the current treatments, various tissue engineering techniques have been developed for tissue regeneration [1–4].

The fundamental concept of tissue engineering technique is that a culturing isolated cell on a scaffold is transplanted into the target tissue for its regeneration [5]. Therefore, in tissue engineering, the importance of selecting the appropriate biomaterials as scaffolds for the cell attachment and supporting cell proliferation has been emphasized [6–15]. The biological tissues basically

[☆]A part of this work was presented at the 49th Orthopaedic Research Society, February, 2003, New Orleans, LA, USA, and the 50th Orthopaedic Research Society, March, 2004, San Francisco, CA, USA.

*Corresponding author. Tel.: +81 11 706 9043; fax: +81 11 706 9042.

E-mail address: shin@glyco.sci.hokudai.ac.jp (S.-I. Nishimura).

consist of the cells and the extracellular matrix (ECM). It has been well documented that the interactions between the cells and the ECM are essential for various basic biological systems [16–19]. The ECM serves at least three functions in controlling cell behavior such as adhesion signals, growth factor binding sites, and degradation sites. Especially, interaction between the cells and their ECM plays an important role in hypocoellular and hypo-vascular tissue regeneration such as cartilage and ligament tissue regeneration [1,13]. Although a variety of biomaterials, including naturally occurring, synthetic, or composite of the both, have been introduced as potential scaffolds, we believe that the ideal cell-carrier substance should be one that closely mimics the natural environment in the ECM.

It was subsequently shown that various ECM molecules contain specific peptide motifs that allow them to directly bind to cell surface receptors [20–24]. One of the best characterized motifs is the tri(tetra)peptide Arg-Gly-Asp-(Ser) [RGD(S)], first found in fibronectin. The peptides containing this amino acid sequence promote the adhesion of cells and inhibit the adhesive properties of fibronectin. On the other hand, integrins were the first identified ECM receptor. It is well established that, on the ligand binding, integrins can directly induce the biochemical signals into the cells. The cytoplasmic domain of the integrins interacts with the cytoskeleton, suggesting that the ECM signalings through integrins are transduced via the cytoskeletal elements and induce cell shape changes leading to the growth and/or differentiation. It is well known that RGD(S) motif of fibronectin could bind with integrin and the signal transduction was regulated through this RGD(S) motif.

Although cell adhesion molecules are crucial for the relationship between cells and ECM, little attention has been paid to their application to scaffold materials. Therefore, our attention was directed toward the mimicking the ECM functions through the conjugation of cell adhesive molecules to scaffold materials. For introducing functional molecules such as peptides, proteins, and carbohydrates, to stable scaffolds in order to acquire additional preferable interactions, functions, and specific cellular responses, Davis et al. reported three major methods of immobilization of biomolecules and cells [25]: physical adsorption, physical entrapment, and covalent attachment. The first and second approaches are physically based, while the third one is based on covalent or chemical attachment to the support molecules. Concerning sustainable tissue engineering, the immobilization must be preferable to last the time when damaged tissue is replaced with regenerating tissue. This long-standing immobilization of biomolecules to scaffolds will be achieved with covalent bonds. Although a number of methods have been developed for the conjugation of biomolecules to soluble

or solid materials by covalent bonds, few methods are currently applied to develop a practically available scaffold material [25,26].

We focused on the effect of the introduction of cell adhesive peptides to chitosan on the cell adhesion and proliferation activity of this abundant aminopolysaccharide material. Chitosan had long been expected as one of the most potential polysaccharides for the biocompatible and wound healing materials [10,11,27–29]. The hypothesis of this study was that introducing the RGDS-containing sequence to this aminopolysaccharide could provide the versatile biocompatible scaffold materials with the enhanced cell adhesion and cell proliferation activities through the interaction with integrins. To test this hypothesis, for reasons mentioned above, we established a novel and efficient method to conjugate the RGDS-containing peptide with chitosan and evaluated its adhesivity and cell proliferation activity of chondrocytes and fibroblasts.

2. Materials and methods

2.1. Synthesis of RGDSGGC

A model peptide, Arg-Gly-Asp-Ser-Gly-Gly-Cys (RGDSGGC), was synthesized by solid-phase manner on Model 433A Peptide Synthesizer by Applied Biosystems (Foster City, CA, USA) using standard Fmoc/HOBt/DCC protocols. The Fmoc-L-amino acids and solvents used in the solid-phase peptide synthesis (SPPS) were purchased from Nova Biochem (Läufelfingen, Switzerland). The solid-phase synthesis was performed on HMP resin and trifluoroacetic acid (TFA), 1-hydroxybenzotriazole in *N*-methylpyrrolidone (HOBt in NMP) and dicyclohexylcarbodiimide in *N*-methylpyrrolidone (DCC in NMP) were used for the coupling reactions in dichloromethane (DCM) or dimethylformamide (DMF) as solvents. Deprotection and cleavage of the peptide from the resin were carried out by treating with 10 ml of reagent mixture containing 9.5 ml of TFA and 0.5 ml of water, for 3 h at room temperature. After releasing the products from the resin, the peptides were purified by HPLC. As shown in Fig. 1, the MALDI-TOF mass spectrum of fully deprotected and purified peptide was measured on an Ultraflex TOF/TOF mass spectrometer (Bruker Daltonics GmbsH, Bremen, Germany).

2.2. Introduction of the RGDSGGC to chitosan by means of 2-iminothiolane

Derivatization of chitosan with 2-iminothiolane was basically performed by employing the modified condition reported by Fu and Gowda [30], in which this

reaction was used for derivatization of some proteins [31–33] (Schemes 1 and 2). Four gram of chitosan powder (ca. 500 kDa, degree of deacetylation ca. 80%, Yaizu Suisankagaku Industry Co., Yaizu, Japan) was mixed with 1% acetic acid (200 ml) to make a 2% (w/v) stock chitosan solution (pH 2.68). Chitosan solution (3.5 g) was added to 50 mM potassium phosphate buffer solution (44 ml, pH 8.0) containing 2 mM EDTA and 150 mM NaCl. To a suspension containing chitosan was added with 2-iminothiolane (112 mg) and the mixture was incubated for 3 h at room temperature in a nitrogen atmosphere. The unreacted 2-iminothiolane was removed by dialysis against distilled water with Seamless Cellulose Tubing (MWCO 12,000–14,000, Viskase Sales Inc., Chicago, IL, USA) for 7 days. Although the total volume of this reaction mixture increased to 68 ml after dialysis, it was found that the novel chitosan derivative showed much improved solubility to alkaline aqueous solution (pH 7–8, data not shown). Since this intermediate seemed to be easily converted into insoluble form by oxidative crosslinking even in an air atmosphere, we directly employed the homogeneous solution containing the key SH-chitosan intermediate for the

subsequent disulfide bond formation with synthetic peptide as shown in Scheme 3. A synthetic peptide (45 mg of RGDSGGC in 6 ml of DMSO) was added to the solution of SH-chitosan prepared by the above-mentioned procedure (22.5 ml) according to the procedure reported by Tam et al. [34]. The mixture was incubated for 4 h at room temperature and subsequently dialyzed against distilled water for 7 days. Since the resulted solution was used as a stock solution for testing cell adhesion or proliferation assay, the half volume of the final solution was lyophilized to determine the precise concentration of the chitosan–RGDSGGC conjugate. As a result, the concentration of chitosan–RGDSGGC was estimated to be 0.12% (w/v). In the present study, the 96-well microtiter plates coated with this stock solution was termed as “0.12% hybrid”.

2.3. Amino acid analysis

For the purpose of the determination of the degree of substitution by RGDSGGC moiety to SH-chitosan, amino acid analysis was carried out. The lyophilized sample was dissolved in 6 N HCl and placed in a thick-wall pyrex tube. The tube was then vacuum sealed and placed in the oven at 110 °C for 24 h. The hydrolysate was evaporated to dryness under reduced pressure and the residue was dissolved in 0.01 N HCl or citrate buffer (PIERCE, Rockford, IL, USA). The solution was loaded to the JLC/500V Amino Acid Analyzer (JEOL Ltd., Tokyo, Japan). Only the basic amino acids were analyzed on the basis of HPLC analysis.

2.4. Cell culture

Human articular chondrocyte of the knee was provided by BioWhittaker (Walkersville, MD, USA) and cultured in Chondrocyte Growth Medium Bullet-Kit[®]. Human fibroblast was provided by Cascade Biologics, Inc. (Portland, OR, USA) and cultured in medium containing Medium 106S[®], LSGS[®]. Each medium was changed thrice a week.



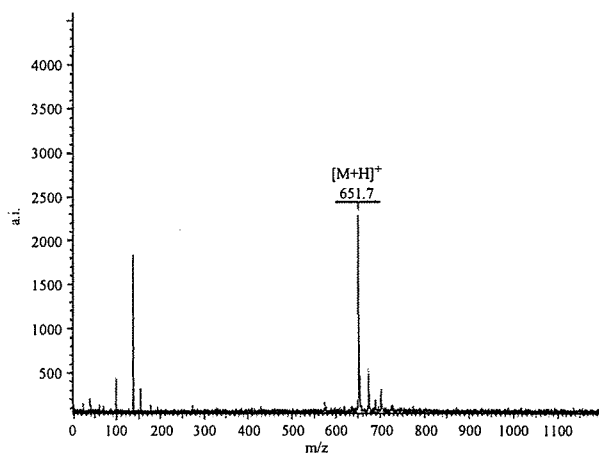



Fig. 1. MALDI-TOF mass spectrum of synthetic RGDSGGC.

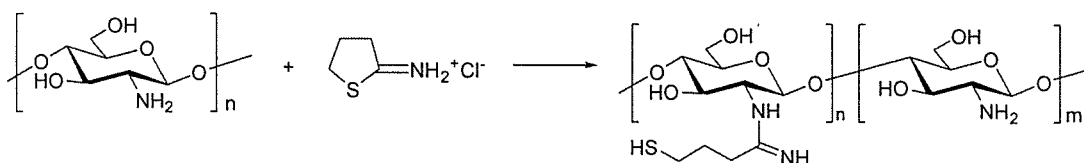

Scheme 1. Ring opening reaction of 2-iminothiolane with chitosan.



Scheme 2. DMSO initiated disulfide bond formation.

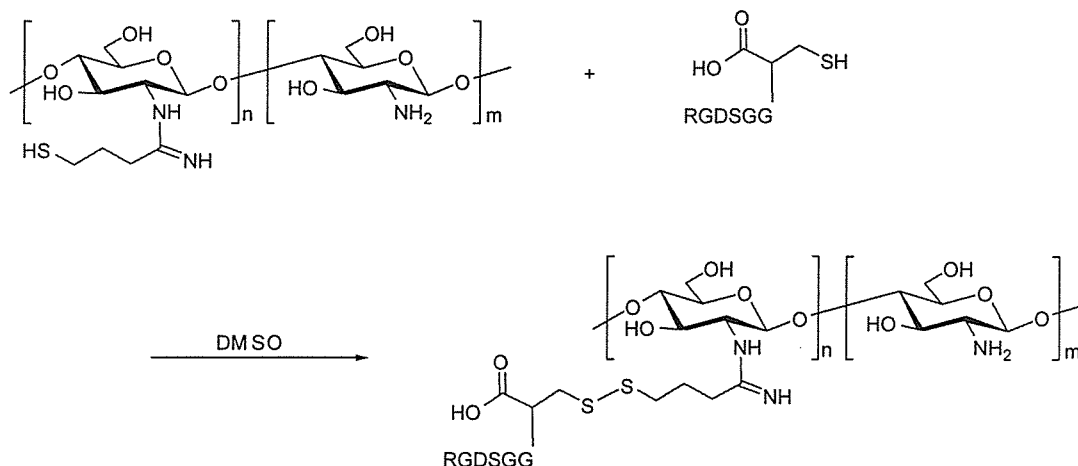

Scheme 3. Coupling reaction of SH-chitosan with RGDSGGC in the presence of DMSO.

2.5. Cell adhesion assay

Cell adhesion assay was performed essentially according to the method described previously [35,36]. In brief, wells of 96-well microtiter plates (Nunc-Immuno™ Plates, NUNC, Rochester, NY, USA) were coated with 50 μl of the RGDSGGC–chitosan solution to each well and incubated at 37 °C for 1 h in a 5% CO₂ incubator. Three kinds of plates were prepared in accordance with the concentration of the material and were termed as 0.12% hybrid, 0.012% hybrid, and 0.0012% hybrid. In addition, 0.00185% RGDSGGC solution, which is equivalent to the amount of RGDSGGC in 0.12% hybrid, was also used for coating the plate (in the text, this plate was called as “non-hybrid”). As a control, non-coating wells were prepared. Nonspecific binding sites were blocked by incubating the plates with 100 μl of 1% bovine serum albumin for 1 h at room temperature. The wells were then washed three times with PBS. Chondrocytes and fibroblasts (1×10^5 cells/well) in 100 μl of HEPES buffer were added to the wells and incubated for 1 h at 37 °C. After the removal of the unbound cells by gently rinsing the wells three times with PBS, the cells attached to the 96-well plates were added 50 μl of 0.25% crystal violet (WAKO Pure Chemicals Co. Ltd., Osaka, Japan) in 20% methanol and incubated for 30 min at room temperature. After rinsing by distilled water, 100 μl /well of 20% acetic acid was added. The degree of cell adhesion was quantified with an optical density at 590 nm by Microplate Reader Model 550 (Bio-Rad, Hercules, CA, USA).

2.6. Cell proliferation assay

Cell proliferation assay was performed by 2-(2-methoxy-4-nitrophenyl)-3-(4-nitrophenyl)-5-(2, 4-disulfophenyl)-2H-tetrazolium, monosodium salt (WST-8)

procedures basically as previously described [37,38]. 1-methoxy-5-methylphenazinium methosulfate (1-Methoxy PMS) and other reagents were obtained from Dojindo Laboratories (Kumamoto, Japan). 96-well microtiter plates (Nunc MicroWell™ Plates, NUNC, Rochester, NY, USA) were coated with 50 μl of RGDSGGC–chitosan conjugate solutions in a similar manner as described in the section of cell adhesion assay. As controls, non-coating plate (Control 1) and 0.12% SH-chitosan-coated plate [chitosan-2-iminothiolane complex, the intermediate without RGDSGGC (Control 2)] were also prepared. Non-specific binding sites were blocked by incubating the plates with 100 μl /well of 1% bovine serum albumin for 1 h at room temperature. The wells were then washed three times with PBS. Chondrocytes (100 μl , 2.25×10^5 cells/ml) suspension was added to the wells and incubated at 37 °C for 24 h. Fibroblasts (100 μl , 2.6×10^5 cells/ml) suspension was added to the wells and incubated for 24 h at 37 °C. A 10 μl of the working solution containing WST-8 and 1-Methoxy PMS (0.5 mM and 20 μM , respectively, as the final concentration) was added to each well. Then, the mixtures were incubated for an additional 2 h. The absorbance of each well was measured at 490 nm by using Microplate Reader Model 550 (Bio-Rad, Hercules, CA, USA). Statistical analyses were performed by using variance (ANOVA) and with Fisher's protected least significant difference post hoc test. Differences were considered significant for $p < 0.05$.

3. Results and discussion

3.1. Preparation of chitosan–RGDSGGC conjugate

It has been known that 2-iminothiolane reacts with general primary amines including N-terminal α -and