

Table 1. The Mean of Thiol Groups per HSA-Fe4P Molecule and Binding Number of the PEG Chains

PEG	[IMT]/[HSA-Fe4P] mol/mol	thiol groups per HSA after IMT addition (A)	thiol groups per HSA after PEG binding (B)	decreased thiol groups (B - A) ^a	averaged PEG number from MS
PEG _{M2}	10	5.6	0.5	5.1	4.6
	15	6.6	0.9	5.7	5.7
	20	8.3	1.1	7.2	6.6
PEG _{M5}	15	6.7	0.6	6.1	5.9
	20	8.0	0.9	7.1	7.2
	30	9.3	1.1	8.2	8.3

^a This number corresponds to the binding numbers of PEG_{M_N} on the protein surface.

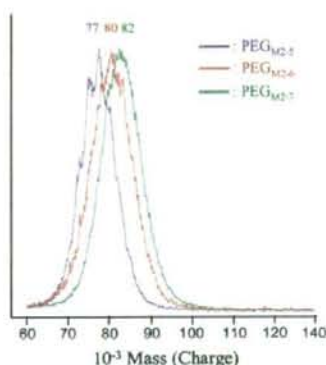


Figure 3. MALDI-TOF MS of PEG_{M2}(HSA-Fe4P) prepared in different [IMT]/[HSA-Fe4P] ratios of 10 (blue), 15 (red), and 20 (green) (mol/mol).

Table 2. Solution Properties of PEG-Conjugated HSA-FeXP Solutions at 37 °C (pH 7.4, [FeXP] = 3 mM)

PEG	density (g/cm ³)	viscosity (cP)	COP (mmHg)
PEG _{M2-5} (HSA-Fe4P)	1.01	1.08	22
PEG _{M2-6} (HSA-Fe4P)	1.01	1.14	27
PEG _{M2-7} (HSA-Fe4P)	1.01	1.17	28
PEG _{M2-6} (HSA-Fe3P)	1.01	1.14	26
PEG _{M5-6} (HSA-Fe4P)	1.01	2.34	65
PEG _{S5-6} (HSA-Fe4P)	1.01	1.14	22
PEG _{S5-6} (HSA-Fe4P)	1.01	2.30	45
HSA-Fe4P	1.01	1.05	21
HSA	1.01	1.00	21

On the contrary, PEG_{M2}(HSA-Fe4P) demonstrated only one broad peak, because the difference in each mass is relatively close compared to the PEG_{M5} conjugate. The peak maxima of PEG_{M2}(HSA-Fe4P) also shifted to the higher region, dependent on the [IMT]/[HSA-Fe4P] ratio (Figure 3, Table 1).

The succinimide-PEG modified HSA-Fe4P showed the same MALDI-TOF MS patterns as PEG_{M_N}(HSA-Fe4P) (data not shown). The number of 5-kDa PEG_{S5} chains per protein increased from 4 → 5 → 6 by elevating the ratio of [PEG_{S5}]/[HSA-Fe4P] (mol/mol): 10 → 20 → 30, respectively. However, the introduced 2-kDa PEG_{S2} number was always 6 in the range of [PEG_{S2}]/[HSA-Fe4P] 10–20. The stoichiometry of the PEG_{S2} binding could not be controlled. This is probably due to the hydrolysis of the succinimidyl end group in aqueous media. The concentration assays of [HSA] by CD and [FeXP] by ICP measurements showed that the initial FeXP/HSA ratio, 4/1 (mol/mol), were constant after the PEG conjugation.

Solution Properties. The viscosity and colloid osmotic pressure (COP) of the 2-kDa PEG-conjugates, PEG_{M2}(HSA-FeXP) and PEG_{S5}(HSA-Fe4P) (PBS solution, [HSA] = 5 g dL⁻¹, pH 7.4), were almost the same as those of the nonmodified HSA-FeXP independent of the number of the PEG chains

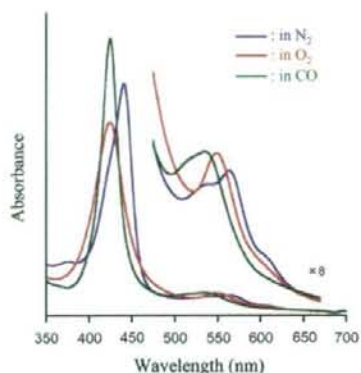


Figure 4. UV-vis absorption spectral change of PEG_{M2-6}(HSA-Fe4P) in PBS solution (pH 7.4).

(Table 2). In contrast, the 5-kDa PEG-conjugate solutions, PEG_{M5}(HSA-FeXP) and PEG_{S5}(HSA-Fe4P), showed a high viscosity (2.30–2.34, at a shear rate of 230 s⁻¹) and hyperoncotic property (45–65 mmHg) in comparison to those of HSA-Fe4P and HSA. From the viewpoint of the design of a blood alternative, it has to achieve a COP similar to that of human blood. However, to increase the effectiveness as a plasma expander, the COP should be higher than the physiological level (18). Similar approaches have been utilized for hypertonic saline-dextran formulations.

On the other hand, maintenance of the viscosity has recently been proposed as an important mechanism to preserve shear forces in the microcirculation which prevents loss of the functional capillary density (19). The latest PEG-Hb product has been designed to approach that of human whole blood (7). Anyway, the COP and viscosity of our PEG-conjugated HSA-FeXP can be adjustable to some extent based on the length of the PEG chains (2-kDa, 5-kDa) on the molecular surface.

O₂-Binding Properties. The UV-vis absorption spectrum of the PEG_{M2}(HSA-Fe4P) solution under an N₂ atmosphere showed λ_{max} at 441, 537, 563 nm (Figure 4), which indicates the formation of the ferrous five-N-coordinate high-spin complex of Fe4P with an intramolecular coordinated 2-methylimidazolyl-group (10b,c, 20). The other amino acid residue of HSA did not bind to the sixth-coordinate position of the central ferrous ion. Upon flowing O₂ gas through this solution, the spectral pattern shifted to that of the well-defined O₂-adduct complex of the tetrakis(phenyl)porphyrinatoiron(II) derivatives (λ_{max}: 424, 550 nm) (10b,c, 20). This oxygenation was reversibly observed, dependent on the O₂-partial pressure. After exposure of this solution to CO, PEG_{M2}(HSA-Fe4P) produced a very stable CO-adduct complex (λ_{max}: 425, 535 nm). The all maleimide- and succinimide-PEG-conjugated HSA-FeXP solutions showed similar UV-vis absorption spectra under N₂, O₂, and CO atmospheres. These spectral changes were completely the same as that observed in the nonmodified HSA-Fe4P.

Table 3. O₂-Binding Parameters of PEG-Conjugated HSA-FeXP Solution at 25 °C (pH 7.4)


system	k_{on} ($\mu\text{M}^{-1}\text{s}^{-1}$)		k_{off} (ms^{-1})		$P_{1/2}$ (Torr)	$\tau_{1/2}$ (h) at 37 °C
	fast	slow	fast	slow		
PEG _{M2-5} (HSA-Fe4P)	11	5.8	0.16	0.08	38 (11)	13
PEG _{M2-6} (HSA-Fe4P)	12	4.6	0.17	0.07	32 (11)	12
PEG _{M2-7} (HSA-Fe4P)	9.3	4.7	0.16	0.08	35 (13)	12
PEG _{M2-8} (HSA-Fe3P)	15	4.2	0.52	0.14	41 (26)	8
PEG _{M5-6} (HSA-Fe4P)	12	6.2	0.17	0.09	31 (11)	16
PEG _{S2-6} (HSA-Fe4P)	10	4.3	0.14	0.06	36 (11)	13
PEG _{S5-6} (HSA-Fe4P)	12	5.5	0.25	0.11	32 (16)	18
HSA-Fe4P	31	7.3	0.53	0.13	34 (13)	9
HSA-Fe3P	29	4.4	1.1	0.16	45 (22)	4

The time course of the absorption decay after laser flash photolysis determined the association rate constants of the O₂-binding to the PEG-conjugated HSA-FeXP. We have previously reported that the O₂-binding reaction to HSA-FeXP was significantly affected by the microenvironment around FeXP in the protein (e.g., steric hindrance of the amino acid residue and difference in polarity) (*JOC-6*). As a result, the binding process of O₂ was observed as the sum of the two single-exponentials, giving fast and slow association rate constants [k_{on} (fast) and k_{on} (slow)]. This unique property of HSA-FeXP has been unaltered after the surface modification by PEG, and all kinetics accompanying the O₂ recombinations consisted of two phases (Table 3). Interestingly, their k_{on} (fast) values were 1.9–3.3-fold lower than those of the corresponding HSA-FeXP, independent of the molecular weight (2-kDa or 5-kDa) and the linkage structure of the PEG. The differences observed in the slow phase were smaller. It may be considered that the presence of flexible polymers on the protein surface retarded the diffusion of the O₂ molecule.

The O₂-binding affinities ($P_{1/2} = K(O_2)^{-1}$) of the PEG-modified HSA-FeXP series were determined by measuring the UV-vis absorption spectral changes by O₂/N₂ titration (Table 3). All the PEG conjugates showed almost the same $P_{1/2}$ values relative to that of the original HSA-FeXP, indicating that the O₂-binding equilibria were not influenced by the presence of PEGs. In contrast, the surface modification by PEG delayed the proton-driven oxidation of the FeXPO₂ species and prolonged the half-life-time of the O₂-adduct complex [$\tau_{1/2}(O_2)$]. The PEG_{M5-6}(HSA-Fe4P)O₂ complex showed the longest $\tau_{1/2}(O_2)$ of 16 h at 37 °C, which is greater than those of HSA-Fe4P and natural hemoprotein, myoglobin ($\tau_{1/2}(O_2)$: 12 h at pH 7, 35 °C) (*21*). Basic polymer PEG conjugation might change the local proton concentration of the HSA interior compared to the outer aqueous solution. Actually, it was shown that the surface PEG modification of hemoproteins has modulated the redox behavior of the active heme site (*1, 2, 22*).

Circulation Lifetime in Bloodstream of Rats. The circulation persistence of FeXP in the bloodstream after the administration of PEG_{M5-6}(HSA-FeXP) or PEG_{S5-6}(HSA-Fe4P) solution in rats is shown in Figure 5. The concentration decays of the PEG_{M5-6}(HSA-FeXP) series showed single exponentials, and the half-lifetimes ($\tau_{1/2}$) were 12.9–15.8 h, independent of the molecular weight of the polymers and FeXP structures. These values are much longer than those of the corresponding nonmodified HSA-FeXP (0.6–3.2 h) (*23*). The surface modification by PEG significantly prevented the rapid clearance of the incorporated FeXP and contributed to increasing the O₂-transporting efficacy.

On the contrary, the PEG_{S5-6}(HSA-Fe4P) series showed biphasic kinetics and a $\tau_{1/2}$ value of 1.5–2.1 h. We have postulated two reasons for this short circulation lifetime. The first reason is the charges of the Lys residues. The maleimide-PEG connects to Lys through the ring-opened IMT, which maintains the positive charge of Lys; therefore, PEG_{M5-6}(HSA-

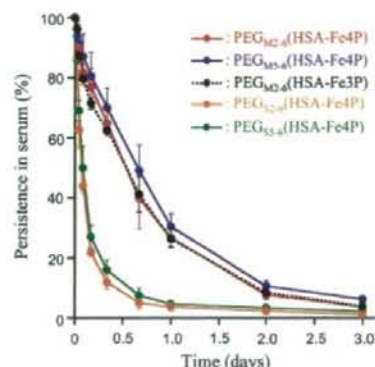**Figure 5.** Persistence of FeXP in serum after administration of PEG-conjugated HSA-FeXP into Wistar rats. All values are mean \pm SD ($n = 4$).

FeXP) could preserve the total electrostatic potential of albumin. In contrast, the succinimide-PEG directly binds to the amino group of Lys to form the amide bond, thereby reducing the positive charge and alters the surface electrostatic potential. This changing of the molecular charge may influence the rapid clearance of the incorporated FeXP.

The second probability is the binding sites of the PEG chains. As shown in Table 1, the difference in the thiol number per protein before and after the reaction with maleimide-PEG was 0.5–1.1. This means that the binding position of PEG_{M5-6} is governed by the reaction place of IMT, which is small enough to statistically attach 59 Lys in HSA. Thus, the molecular surface of HSA-FeXP is uniformly covered by PEG_{M5-6}. On the other hand, the attaching sites of succinimide-PEG are presumably heterogeneous, because PEG_{S5-6} could only bind the accessible amino group of Lys due to the bulkiness of the long polymer. The incorporated Fe4P molecules might be more easily released from the PEG_{S5-6}-modified HSA in the circulatory system.

CONCLUSIONS

The surface modification of the albumin-based synthetic hemoprotein, HSA-FeXP, by PEG (Mw 2-kDa or 5-kDa) has improved its comprehensive O₂-transporting ability. The PEG conjugation decreased the O₂-association rate constant but retarded the irreversible oxidation of the central ferrous ion, thereby increasing the stability of the O₂-adduct complex. The 5-kDa PEG conjugation increased the viscosity and COP; however, the 2-kDa PEG conjugation did not change these rheological parameters. The linkage form of the PEG chain dramatically affects the circulation persistence of FeXP. In particular, the maleimide-PEG_{M5-6} conjugates showed a 6–8-fold longer lifetime compared to the succinimide-PEG_{S5-6} analogues. This is not dependent on the molecular weight of the polymer chains. In summary, the PEG_{M5-6}(HSA-FeXP) solution is the most promising candidate as an entirely synthetic O₂-carrying plasma expander for a red cell substitute.

Furthermore, we have recently found that water evaporation of the PEG_{M5-6}(HSA-FeXP) solution produced a red-colored thin film. Its UV-vis absorption spectrum reversibly changed from the deoxy state under an N₂ atmosphere to the oxy state by exposure to O₂ gas. This PEG_{M5-6}(HSA-FeXP) film was redissolved in nonaqueous organic solvents, ethanol, chloroform, etc., and the reversible O₂ binding was again observed. The detailed study of the oxygenations of PEG_{M5-6}(HSA-FeXP) in a cast film and organic solvent are now underway.

ACKNOWLEDGMENT

This work was partially supported by a Grant-in-Aid for Scientific Research (No. 16350093) from JSPS, a Grant-in-Aid for Exploratory Research (No. 16655049) from MEXT Japan, and Health Science Research Grants (Regulatory Science) from MHLW Japan. Prof. Koichi Kobayashi, Dr. Hirohisa Horinouchi (Keio University), and Mr. Hisashi Yamamoto (NIPRO Corp.) are greatly appreciated for their cooperation with the animal experiments.

LITERATURE CITED

- (1) (a) Harris, J. M., Ed. (1992) *Poly(ethylene glycol) Chemistry: Biotechnical and Biomedical Applications*. Plenum Press, New York; (b) Veronese, F. M., Harris, J. M. (2002) Introduction and overview of peptide and protein PEGylation. *Adv. Drug Delivery Rev.* 54, 453–456. (c) Roberts, M. J., Bentley, M. D., Harris, J. M. (2002) Chemistry for peptide and protein PEGylation. *Adv. Drug Delivery Rev.* 54, 459–476.
- (2) Veronese, F. M. (2001) Peptide and protein PEGylation: a review of problems and solutions. *Biomaterials* 22, 405–417.
- (3) Nucci, M. L., Shorr, R., and Abuchowski, A. (1991) The therapeutic value of poly(ethylene glycol) modified proteins. *Adv. Drug Delivery Rev.* 6, 133–151.
- (4) Kawahara, N. Y., and Ohno, H. (1997) Induced thermostability of poly(ethylene oxide)-modified hemoglobin in glycols. *Bioconjugate Chem.* 8, 643–648.
- (5) Yabuki, A., Yamaji, K., Ohki, H., and Iwashita, Y. (1990) Characterization of a pyridoxalated hemoglobin-polyoxyethylene conjugate as a physiologic oxygen carrier. *Transfusion* 30, 516–520.
- (6) Talarico, T. L., Guise, K. J., and Stacey, C. J. (2000) Chemical characterization of pyridoxalated hemoglobin polyoxyethylene conjugate. *Biochim. Biophys. Acta* 1476, 53–65.
- (7) Vandegriff, K. M., Malavalli, A., Wooldbridge, J., Lohman, J., and Winslow, R. M. (2003) MP4, a new nonvasoactive PEG-Hb conjugate. *Transfusion* 43, 509–516.
- (8) Manjula, B. M., Tsai, A., Upadhyaya, R., Perumalsamy, K., Smith, P. K., Malavalli, A., Vandegriff, K., Winslow, R. M., Intaglietta, M., Prabhakaran, M., Friedman, J. M., and Acharya, A. S. (2003) Site-specific PEGylation of hemoglobin at Cys-93(β): correlation between the colligative properties of the PEGylated protein and the length of the conjugated PEG chain. *Bioconjugate Chem.* 14, 464–472.
- (9) Peters, T. (1996) *All about Albumin: Biochemistry, Genetics and Medical Applications*. Academic Press, San Diego.
- (10) (a) Komatsu, T., Hamamatsu, K., Wu, J., and Tsuchida, E. (1999) Physicochemical properties and O₂-coordination structure of human serum albumin incorporating tetrakis(*o*-pivalamido)phenylporphyrinatoiron(II) derivatives. *Bioconjugate Chem.* 10, 82–86. (b) Tsuchida, E., Komatsu, T., Matsukawa, Y., Hamamatsu, K., and Wu, J. (1999) Human serum albumin incorporating tetrakis(*o*-pivalamido)phenylporphyrinatoiron(II) derivative as a totally synthetic O₂-carrying hemoprotein. *Bioconjugate Chem.* 10, 797–802. (c) Komatsu, T., Matsukawa, Y., and Tsuchida, E. (2000) Kinetics of CO and O₂ binding to human serum albumin-heme hybrid. *Bioconjugate Chem.* 11, 772–776. (d) Komatsu, T., Matsukawa, and Y., Tsuchida, E. (2002) Effect of heme structure on O₂-binding properties of human serum albumin-heme hybrids: Intramolecular histidine coordination provides a stable O₂-adduct complex. *Bioconjugate Chem.* 13, 397–402. (e) Nakagawa, A., Komatsu, T., Iizuka, M., and Tsuchida, E. (2006) Human serum albumin hybrid incorporating tailed porphyrinatoiron(II) in $\alpha, \alpha, \alpha, \beta$ -conformer as an O₂ binding site. *Bioconjugate Chem.* 17, 146–151.
- (11) (a) Komatsu, T., Huang, Y., Yamamoto, H., Horinouchi, H., Kobayashi, K., and Tsuchida, E. (2004) Exchange transfusion with synthetic oxygen-carrying plasma protein "albumin-heme" into an acute anemia rat model after seventy-percent hemodilution. *J. Biomed. Mater. Res.* 71A, 644–651. (b) Huang, Y., Komatsu, T., Yamamoto, H., Horinouchi, H., Kobayashi, K., and Tsuchida, E. (2004) Exchange transfusion with entirely synthetic red-cell substitute albumin-heme into rats: physiological responses and blood biochemical tests. *J. Biomed. Mater. Res.* 71A, 63–69.
- (12) Adams, P. A., and Berman, M. C. (1980) Kinetics and mechanism of the interaction between human serum albumin and monomeric hemin. *Biochem. J.* 191, 95–102.
- (13) Russo, S. M., Pepe, J. A., Donohue, S., Cable, E. E., Lambrecht, R. W., and Bonkovsky, H. L. (1995) Tissue distribution of zinc-mesoporphyrin in rats: relationship to inhibition of heme oxygenase. *J. Pharmacol. Exp. Ther.* 272, 766–774.
- (14) Komatsu, T., Huang, Y., and Tsuchida, E. (2005) paper in preparation.
- (15) Pedersen, A. O., and Jacobsen, J. (1980) Reactivity of the thiol group in human and bovine albumin at pH 3–9, as measured by exchange with 2,2'-dithiodipyridine. *Eur. J. Biochem.* 106, 291–295.
- (16) Komatsu, T., Ohmichi, N., Nakagawa, A., Zunszain, P. A., Curry, S., and Tsuchida, E. (2005) O₂ and CO binding properties of artificial hemoproteins formed by complexing iron protoporphyrin IX with human serum albumin mutants. *J. Am. Chem. Soc.* 127, 15933–15942.
- (17) Doumas, B. T., Watson, W. A., and Biggs, H. G. (1971) Albumin standards and measurement of serum albumin with bromocresol green. *Clin. Chim. Acta* 31, 87–96.
- (18) Vandegriff, K. D., McCarthy, M., Rohlf, R., and Winslow, R. M. (1997) Colloid osmotic properties of modified hemoglobins: chemically cross-linked versus polyethylene glycol surface-conjugated. *Biophys. J.* 69, 23–30.
- (19) Tsai, A. G., Friesenecker, B., and McCarthy, M. (1998) Plasma viscosity regulates capillary perfusion during extreme hemodilution in hamster skinfold model. *Am. J. Physiol.* 275, H2170–80.
- (20) Tsuchida, E., Komatsu, T., Kumamoto, S., Ando, K., and Nishide, H. (1995) Synthesis and O₂-Binding properties of tetraphenylporphyrinatoiron(II) derivatives bearing a proximal imidazole covalently bound at the β -pyrrolic position. *J. Chem. Soc., Perkin Trans.* 2 747–753.
- (21) Sugawara, Y., Shikama, K. (1980) Autoxidation of native oxymyoglobin. *Eur. J. Biochem.* 110, 241–246.
- (22) Ohno, H., and Tsukuda, T. (1992) Electron-transfer reaction of polyethylene oxide-modified myoglobin in polyethylene oxide oligomers. *J. Electroanal. Chem.* 341, 137–149.
- (23) Tsuchida, E., Komatsu, T., Hamamatsu, K., Matsukawa, Y., Tajima, A., Yoshizu, A., Izumi, Y., and Kobayashi, K. (2000) Exchange transfusion of albumin-heme as an artificial O₂-infusion into anesthetized rats: physiological responses, O₂-delivery and reduction of the oxidized heme sites by red blood cells. *Bioconjugate Chem.* 11, 46–50.

BC050315+



PEGylated albumin-heme as an oxygen-carrying plasma expander: Exchange transfusion into acute anemia rat model

Yubin Huang^a, Teruyuki Komatsu^a, Hisashi Yamamoto^{b,c}, Hirohisa Horinouchi^c,
Koichi Kobayashi^c, Eishun Tsuchida^{a,*}

^aAdvanced Research Institute for Science and Engineering, Waseda University, 3-4-1 Okubo, Shinjuku-ku, Tokyo 169 8555, Japan

^bPharmaceutical Research Center, NIPRO Corp., 3023 Noji-cho, Kusatsu-shi, Shiga 525 0055, Japan

^cDepartment of General Thoracic Surgery, School of Medicine, Keio University, 35 Shinanomachi, Shinjuku-ku, Tokyo 160 8582, Japan

Received 11 January 2006; accepted 5 April 2006

Available online 4 May 2006

Abstract

Poly(ethylene glycol) (PEG) conjugated recombinant human serum albumin (HSA) incorporating the synthetic iron-porphyrin (FeP) [PEGylated albumin-heme, PEG(HSA-FeP)] is a unique albumin-based oxygen carrier as a red blood cell (RBC) substitute. The physiological responses to an exchange transfusion with PEG(HSA-FeP) into an acute anemia rat model were investigated. After a 65% isovolemic hemodilution with HSA, a 30% volume of the circulatory blood was withdrawn, affording a hemorrhaged state. The circulation parameters, blood parameters, renal cortical oxygen partial pressure [$PtO_2(R)$], and muscle tissue oxygen partial pressure [$PtO_2(M)$] were continuously monitored. The intravenous infusion of PEG(HSA-FeP) restored the reduced levels of the mean arterial pressure, heart rate, respiration rate, mixed venous PO_2 , and arterial PCO_2 . The increased arterial PO_2 and pH also returned to their basal values. These effects were almost to the same extent as those observed after the administration of the RBC suspension. The relatively low recovery in $PtO_2(R)$ and $PtO_2(M)$ might be due to the Langmuir-type oxygen binding profile of PEG(HSA-FeP) (Hill coefficient: 1.0). All the animals survived during the experiments. In contrast, those injected with HSA died within 41 min. The PEG(HSA-FeP) solution is an oxygen-carrying plasma expander which can be used as a resuscitative fluid for hemorrhagic shock.

© 2006 Elsevier Ltd. All rights reserved.

Keywords: Albumin; Biomimetic material; Blood; In vivo test; Oxygenation; Poly(ethylene glycol)

1. Introduction

Human hemoglobin (Hb)-based oxygen carriers as a blood replacement composition have been vigorously developed in the past decade [1–3], e.g., polymerized Hb [4], polymer-conjugated Hb [5], and phospholipid vesicle encapsulated Hb [6,7]. Some of them have already been used in clinical Phase II/III trials. The most superior property of these materials is certainly “no blood type”. One can administer these materials into patients who need a blood transfusion without cross matching and typing before use. This saves time and facilities, allowing instant transfusion, which is tremendously useful in an emergency. On the other hand, the largest concern of the Hb-products

is the source of the human Hb, which is regulated by the availability of donated human blood.

Based on this background, poly(ethylene glycol) (PEG) conjugated human serum albumin (HSA) incorporating 2-[8-{N-(2-methylimidazolyl)octanoyloxymethyl}-5,10,15,20-tetrakis($\alpha,\alpha,\alpha,\alpha$ -o-(1-methylcyclohexanamido)phenyl)porphyrinatoiron(II) (FeP, Chart 1) [PEGylated albumin-heme, PEG(HSA-FeP)] has been developed as a unique albumin-based oxygen carrier [8]. Recombinant HSA is now manufactured on an industrial scale (one million vials per year) [9] and the batch production of the synthetic FeP has also been established [10]. The oxygen binding affinity (oxygen pressure where 50% of heme is oxygenated) of PEG(HSA-FeP) (P_{50}) was adjusted to 32 Torr (at 37 °C) that is similar to the 28 Torr of human RBC, and the solution properties are almost the same as those of HSA itself. The surface modification with PEG significantly improved not only the

*Corresponding author. Tel.: +81 3 5286 3120; fax: +81 3 3205 4740.
E-mail address: eishun@waseda.jp (E. Tsuchida).

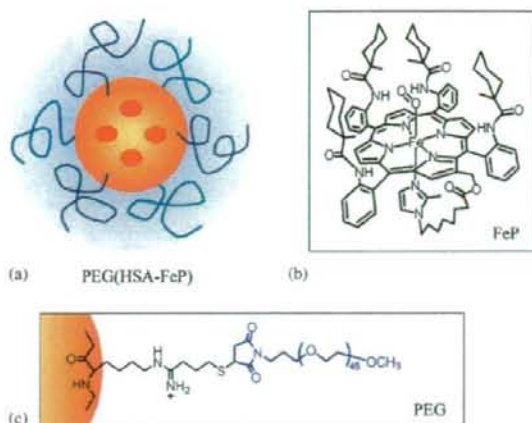


Chart 1. (a) Schematic illustration of PEGylated albumin-heme [PEG(HSA-FeP)], (b) chemical structure of FeP, and (c) binding form of PEG to the lysine group of HSA.

circulation lifetime of FeP *in vivo*, but also the stability of the oxygenated complex [8]. The PEG(HSA-FeP) solution would be of extreme medical importance as a new type of oxygen-carrying plasma expander.

We now report for the first time the systemic evaluations of the physiological responses to an exchange transfusion with PEG(HSA-FeP) into an acute anemia rat model. The animals were first placed in a 65 vol% hemodilution with HSA and then underwent a 30 vol% blood replacement with PEG(HSA-FeP). The circulation parameters, blood parameters, the oxygen deliveries to the renal cortex and the muscle tissue were monitored and compared to the HSA group and RBC group for 120 min after the infusion.

2. Materials and methods

2.1. Preparation of PEG(HSA-FeP) solution

The 5 g/dL HSA solution was prepared by dilution of recombinant HSA [Albrec[®], 25 wt%, NIPRO Corp. (Osaka)] with a saline (Otsuka Pharmaceutical Co., Ltd.). The PEG(HSA-FeP) was prepared according to our previously reported procedure [8] (phosphate buffer saline solution, pH = 7.4, [HSA] = 5 g/dL, [FeP] = 3 mM (FeP/HSA = 4 mol/mol), Mw of PEG = 2333 Da, averaged number of PEG per HSA-FeP = 6, oxygen-binding affinity (P_{50}) = 32 Torr (37 °C), density = 1.01 g/cm³, colloid osmotic pressure = 27 mmHg, viscosity = 1.14 cP).

2.2. Extreme hemodilution and exchange transfusion

The investigations were carried out with 15 male Wistar rats (288 ± 18 g). The methods of operation were described elsewhere in detail [11].

The animals were under an inhalation anesthesia with sevoflurane; its concentration was kept at 1.5% during the experiment. First, a 65% hemodilution was carried out using 5 g/dL HSA. The blood withdrawal via the common carotid artery (2 mL) and the HSA infusion from the femoral vein (2 mL) (each 1 mL/min) were repeated for eight cycles. After 10 min, a 30% volume of the circulatory blood was withdrawn, and the

identical volume of PEG(HSA-FeP) was injected ($n = 5$) (1 mL/min). As negative or positive-control group, the 5 g/dL HSA solution (HSA group, $n = 5$) or the washed RBC suspension (RBC group, $n = 5$) was infused to the similarly operated rats in hemorrhage. The washed RBC suspension was prepared as follows. The fresh withdrawn whole rat blood in the heparinized tube was centrifuged and the plasma layer was discarded. The 5 g/dL HSA was added to the tube and centrifuged again. Then, the supernatant was discarded and 5 g/dL HSA was added to adjust the Hb concentration to 5 g/dL ([heme] = 3 mM).

The blood samples from the artery (0.3 mL) and vein (0.2 mL) were collected at the following seven time-points: (1) before the 65% hemodilution, (2) immediately after the hemodilution, (3) 10 min after the hemodilution, (4) immediately after the 30% bleeding, (5) immediately after the sample infusion, (6) 60 min, and (7) 120 min after the infusion. Mean arterial pressure (MAP) and heart rate (HR) were recorded by a Polygraph System (NIHON KODEN LEG-1000 Ver. 01-02 or PEG-1000 Ver. 01-01) at the following eleven time-points: (1) before the 65% hemodilution, (2) immediately after the hemodilution, (3) 10 min after the hemodilution, (4) immediately after the 30% bleeding, (5) immediately after the sample infusion, (6) 5 min, (7) 15 min, (8) 30 min, (9) 60 min, (10) 90 min, and (11) 120 min after the sample infusion. Collected blood sample was applied to a blood gas system (Radio Meter Trading ABL555) to measure the oxygen pressure (P_{aO_2}), carbon dioxide pressure (P_{aCO_2}) and pH of the arterial blood, and the oxygen pressure (P_{vO_2}) and lactate of the venous blood. Renal cortical oxygen partial pressure [$P_{iO_2}(R)$] and muscle tissue oxygen partial pressure [$P_{iO_2}(M)$] were monitored by a tissue oxygen pressure monitor (Inter Medical PO₂-100 DW) using a polarographic oxygen-electrode (Intermedical POE-10 N and POE-40PS) inserted into the left renal cortex and muscle in the abdomen.

The animals were sacrificed after the experiments by venesection. All animal handling and care were in accordance with the NIH guidelines. The protocol details were approved by the Animal Care and Use Committee of Keio University.

2.3. Statistical analysis

All data were represented by mean ± standard deviation (SD). Statistical analyses were performed using the Tukey–Kramer multiple comparison test for three groups, and by repeated measures analysis of variance followed by paired *t*-test. The software used was a StatView (SAS Institute, Inc.). Values of $p < 0.05$ were considered significant.

3. Results

3.1. Survival time

The changes in the hematocrit (Hct) clearly demonstrated a good accordance with the 65% hemodilution and 30% shock resuscitation (Fig. 1(a)). Isovolemic hemodilution with HSA reduced the Hct to 13–15%; this value is below the threshold at which the organism becomes oxygen supply limited [12,13]. Under an extreme hemodilution, the effect of the RBC substitute is magnified upon introduction into the circulation.

The intravenous infusion of HSA did not make any improvement on the appearance of the animals. All the rats died within 41 min; the average survival time was 17.9 ± 14.0 min (Fig. 1(b)). In contrast, after the transfusion of PEG(HSA-FeP) or washed RBC, all the animals survived over 120 min. In the glass capillaries for the Hct determinations of the PEG(HSA-FeP) group, the supernatant after centrifugation (12 kG, 5 min) was colored red by the homogeneously dispersed sample. This indicates that PEG(HSA-FeP) has a good solubility with the blood components without aggregation.

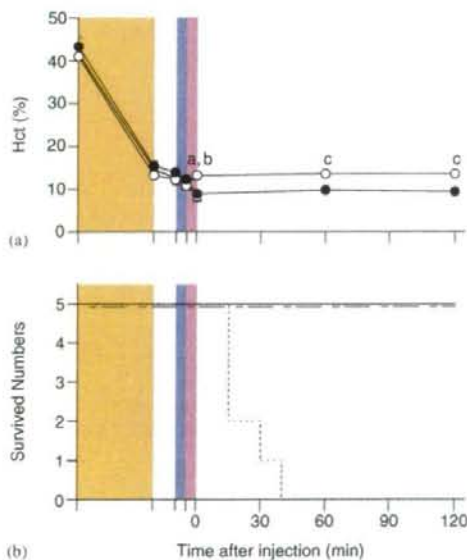


Fig. 1. Effect of PEG(HSA-FeP) solution on (a) Hct in anesthetized rats subjected to hemodilution and hemorrhage, and (b) the changes of their survived numbers. In (a), each value represents the mean \pm SD of 5 rats [\bullet : PEG(HSA-FeP) group, \circ : RBC group, and Δ : HSA group]. ^a $p < 0.05$ versus HSA group (Tukey–Kramer test), ^b $p < 0.05$ versus PEG(HSA-FeP) group (Tukey–Kramer test), and ^c $p < 0.05$ versus PEG(HSA-FeP) group (unpaired *t*-test). In (b), solid line; PEG(HSA-FeP) group, broken and dotted line; RBC group, and dotted line; HSA group. The yellow, blue, and pink areas indicate the periods of 65% hemodilution, 30% bleeding, and sample infusion, respectively.

3.2. Circulation parameters (MAP, HR, and respiration rate)

The MAP decreased to 70–73 mmHg [72–74% of the basal value (b.v.)] after the 65% hemodilution, and further dropped to 28–29 mmHg (28–29% of the b.v.) by the 30% bleeding in all groups (Fig. 2(a)). The injection of PEG(HSA-FeP) or RBC significantly increased the lowered values to 70 or 73 mmHg, that corresponds to 85% or 98% of the levels before the bleedings. On the other hand, no recovery was observed in the HSA group.

The HR and respiration rate decreased to 332–356 beats/min (86–91% of the b.v.) and 51–57 time/min (80–93% of the b.v.) by the 30% bleeding (Fig. 2(b), (c)). Both parameters returned to their initial levels by the infusion of PEG(HSA-FeP). The degree of the recovery was almost the same as those of the RBC transfusion.

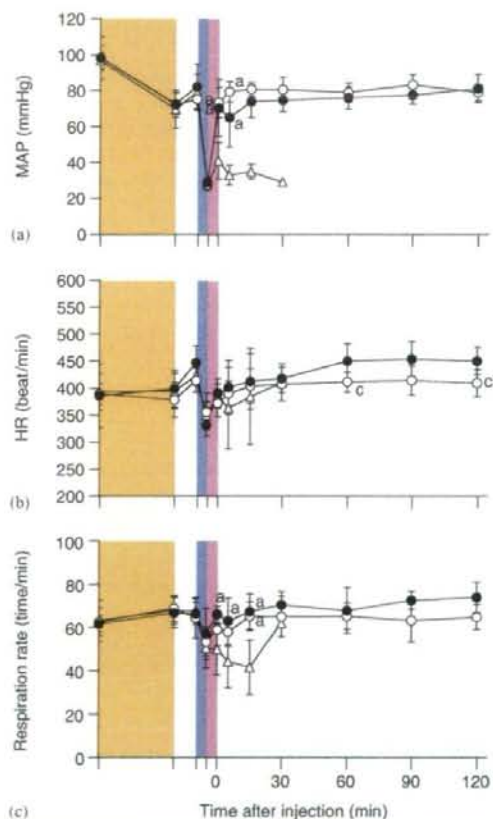


Fig. 2. Effect of PEG(HSA-FeP) solutions on (a) MAP, (b) HR, and (c) respiration rate in anesthetized rats subjected to hemodilution and hemorrhage. Each value represents the mean \pm SD of 5 rats [\bullet : PEG(HSA-FeP) group, \circ : whole blood group, and Δ : HSA group]. The yellow, blue, and pink areas indicate the periods of 65% hemodilution, 30% bleeding, and sample infusion, respectively. ^a $p < 0.05$ versus HSA group (Tukey–Kramer test) and ^c $p < 0.05$ versus PEG(HSA-FeP) group (unpaired *t*-test).

3.3. Blood parameters [PaO_2 , PvO_2 , $PaCO_2$, and pH]

The PaO_2 increased to 96–118 mmHg (120–140% of the b.v.) after the 65% hemodilution, and became further elevated to 131–137 mmHg (156–167% of the b.v.) after the 30% bleeding (Fig. 3(a)). It was not changed by the injection of HSA, however, the administration of RBC immediately restored the PaO_2 to 97 mmHg (118% of the b.v.), and kept the level constant throughout the measurement. The injection of PEG(HSA-FeP) also showed a similar restoration like that of RBC.

The PvO_2 decreased to 32–35 mmHg (59–67% of the b.v.) after the 30% bleeding (Fig. 3(b)). Although the administration of HSA did not improve the low value, the infusion of PEG(HSA-FeP) or RBC increased the PvO_2 to 49 or 52 mmHg (91% or 95% of the b.v.).

The $PaCO_2$ dropped to 23–26 mmHg (59–66% of the b.v.) after the 30% bleeding (Fig. 3(c)). The injection of HSA did not recover the low level, while the administration

of PEG(HSA-FeP) or RBC increased the $PaCO_2$ to 31 mmHg, and it reached 35 mmHg after 1 h.

The pH of 7.43–7.45 was increased to 7.53–7.56 after the 30% bleeding. The administration of PEG(HSA-FeP) or RBC quickly decreased the high pH to the initial value before the hemodilution (Fig. 3(d)).

3.4. Tissue oxygen partial pressure [$PtO_2(R)$ and $PtO_2(M)$]

The $PtO_2(R)$ decreased to 8–10 mmHg (51–59% of the b.v.) after the 65% hemodilution, and further declined to 3–5 mmHg (17–28% of the b.v.) after the 30% bleeding (Fig. 4(a)). The administration of HSA showed no improvement, however, the injection of PEG(HSA-FeP) or RBC immediately increased the $PtO_2(R)$ to 8–9 mmHg (84–97% of the values before the bleeding). In the RBC group, the $PtO_2(R)$ became somewhat higher and reached

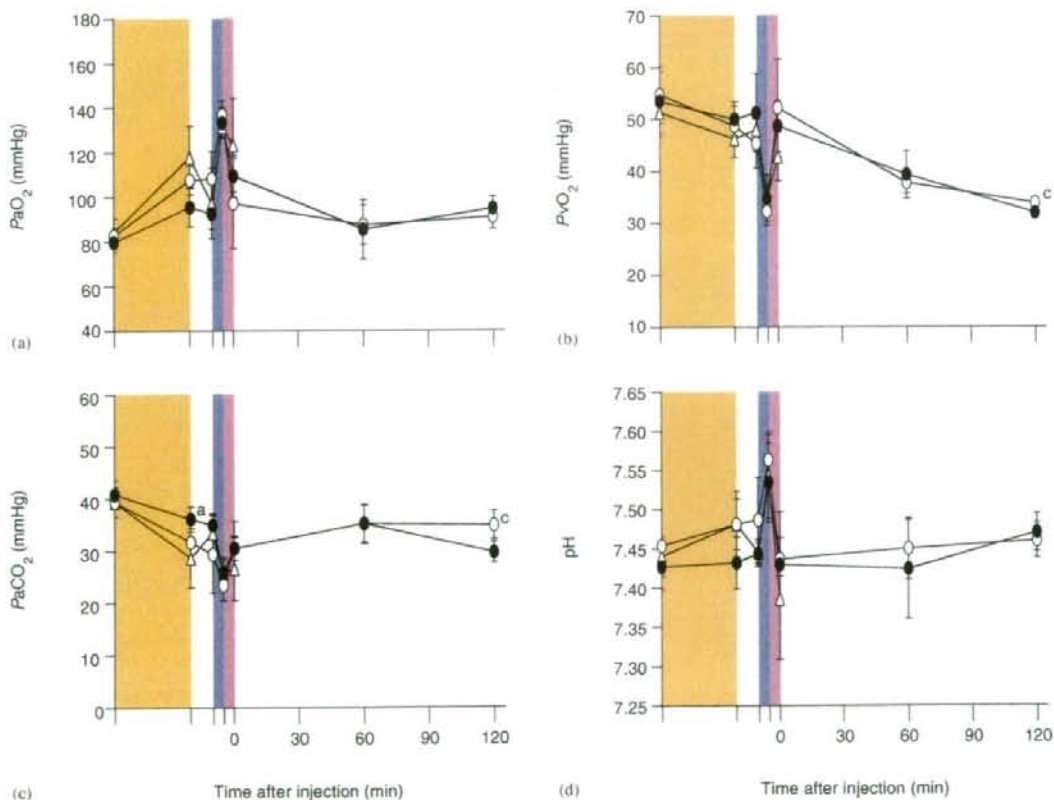


Fig. 3. Effect of PEG(HSA-FeP) solutions on (a) PaO_2 , (b) PvO_2 , (c) $PaCO_2$, and (d) pH in anesthetized rats subjected to hemodilution and hemorrhage. Each value represents the mean \pm SD of 5 rats (\bullet ; PEG(HSA-FeP) group, \circ ; whole blood group, and Δ ; HSA group). The yellow, blue, and pink areas indicate the periods of 65% hemodilution, 30% bleeding, and sample infusion, respectively. * $p < 0.05$ versus HSA group (Tukey-Kramer test) and $^{\#}p < 0.05$ versus PEG(HSA-FeP) group (Unpaired *t*-test).

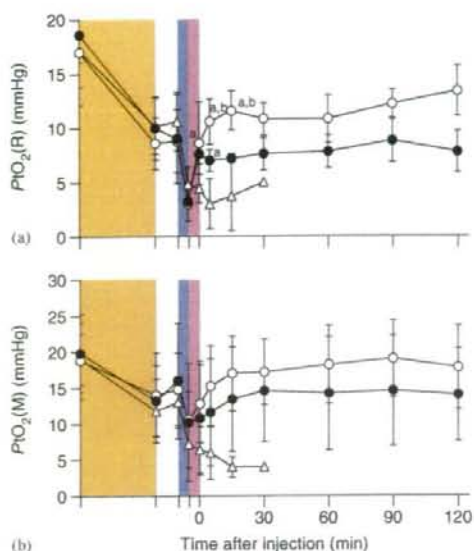


Fig. 4. Effect of PEG(HSA-FeP) solutions on (a) $PtO_2(R)$ and (b) $PtO_2(M)$ in anesthetized rats subjected to hemodilution and hemorrhage. Each value represents the mean \pm SD of 5 rats (●; PEG(HSA-FeP) group, ○; whole blood group, and △; HSA group). The yellow, blue, and pink areas indicate the periods of 65% hemodilution, 30% bleeding, and sample infusion, respectively. ^a $p < 0.05$ versus HSA group (Tukey–Kramer test) and ^b $p < 0.05$ versus PEG(HSA-FeP) group (Tukey–Kramer test).

11 mmHg after 15 min. They both remained constant by the end of the measurements.

The $PtO_2(M)$ decreased to 7–11 mmHg (38–56% of the b.v.) by the 30% bleeding (Fig. 4(b)). The administration of the RBC gradually increased the $PtO_2(M)$ to 17 mmHg (90% of the b.v.) for 15 min, and maintained this level. The transfusion of PEG(HSA-FeP) also slowly increased the $PtO_2(M)$ to 15 mmHg (74% of the b.v.) for 30 min, and the value was stable throughout the experiment.

4. Discussion

4.1. Acute anemia

The isovolemic 65% hemodilution with HSA reduced the Hb concentration, leading to a decrease in the oxygen supply to the tissue. Hypoxia in vital organs and muscle tissues were clearly shown by the declines of MAP, $PtO_2(R)$, and $PtO_2(M)$. The initial response to compensate for this acute anemia is generally an increase in the rate or depth of respiration (hyperventilation); both result in an elevation of the PaO_2 level. In fact, the PaO_2 was increased to 120–140% of the b.v. just after the 65% hemodilution. Since the respiration rate was not changed, we theorized that the increase of depth of respiration is the major factor for the high PaO_2 .

4.2. Hemorrhagic shock

During the hemorrhagic shock by the 30% bleeding, significant decreases in the MAP, PvO_2 , $PtO_2(R)$, and $PtO_2(M)$ were observed by the loss of the circulation blood volume. The HR and respiration rate also decreased. On the contrary, PaO_2 was increased to about 160% of the b.v., because the RBC has to increase its oxygen saturation. The $PaCO_2$ decreased to about 62% of the b.v. and the pH increased to 7.55. A respiratory alkalosis probably overcomes the metabolic acidosis. The lactate also increased (data not shown), which could be due to the anaerobic metabolism in the peripheral circulation systems.

4.3. Responses to infusion of PEG(HSA-FeP)

The injection of the sample solutions increased the blood volume and improved the circulatory flows. The lactate was washed out from the tissues and into the circulatory system, which decreased the pH to the initial level of 7.43 in all groups. The administration of HSA did not restore any parameters, leading to death within 41 min. In contrast, the infusion of PEG(HSA-FeP) or RBC kept all the rats alive until the end of the measurement.

The circulation half lifetime of FeP (τ_{50}) after the administration of PEG(HSA-FeP) (20% top loading) in anesthetized rats has been determined to be 14 h [8]. The surface modification by PEG significantly prevented the rapid clearance of the incorporated FeP and contributed to increasing the oxygen-transporting efficacy. In this experimental setup, over 80% of the material remained in the bloodstream 120 min after the injection. It is almost the same level as those observed in the 20% top-loading test.

After the injection of PEG(HSA-FeP), the animals showed significant and quick recoveries in MAP, HR, respiration rate, PaO_2 , PvO_2 , $PaCO_2$, and pH, the same as seen in the RBC group. These results definitely show the oxygen-transporting capability of the PEG(HSA-FeP) solution as a resuscitative fluid. The PvO_2 is a crucial parameter to evaluate the oxygen saturation in blood. The complete restoring of PvO_2 to the level before the bleeding implies a sufficient oxygen supply by PEG(HSA-FeP). The hyperventilation by hypoxia was also depressed and PaO_2 returned to the b.v.

Among the vital organs, renal perfusion is first impaired due to redistribution of the systemic blood flow, so that the $PtO_2(R)$ is a sensitive parameter to the subtle change in the blood circulation and oxygen delivery. The increase in $PtO_2(R)$ by the transfusion of PEG(HSA-FeP) or RBC was very quick, because the oxygen is preferentially supplied to the vital organs. On the other hand, the $PtO_2(M)$ was gradually elevated for 30 min with the stabilization of the blood circulation.

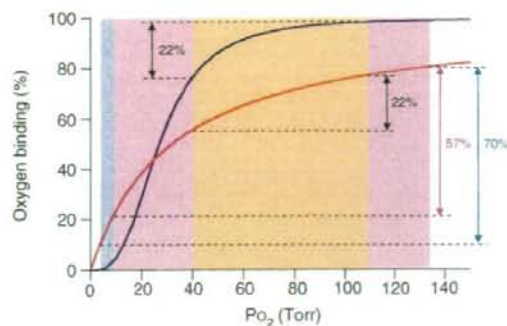


Fig. 5. Oxygen equilibrium curves of PEG(HSA-FeP) (red line) and human RBC (blue line) at 37 °C. The yellow-colored area represents the difference between 110 mmHg at lungs and 40 mmHg at muscle tissues in human. The pink-colored area corresponds to the difference between 134 mmHg of P_{aO_2} and 9.3 mmHg of $P_{tO_2}(M)$ in hemorrhagic shock state after the 30% bleeding. The left edge of the blue-colored area indicates 3.7 mmHg of $P_{tO_2}(R)$ at the hemorrhagic shock state. The values represented in percent indicate the OTEs.

4.4. Oxygenation of the tissues by PEG(HSA-FeP)

All the physiological responses showed that PEG(HSA-FeP) has the capability to transport oxygen throughout the body. Nevertheless, the restoration effect by PEG(HSA-FeP) in $P_{tO_2}(R)$ and $P_{tO_2}(M)$ was slightly weak compared to that observed in the RBC group. The infusion volume and heme concentration ($[heme] = 3 \text{ mM}$) were exactly the same. The oxygen transporting efficiency (OTE) of PEG(HSA-FeP) between the lungs ($P_{O_2} = 110 \text{ Torr}$) and muscle tissues ($P_{O_2} = 40 \text{ Torr}$) (22%) is also identical to the human RBC (Fig. 5) [10]. Therefore, we theorized that the relatively low oxygenation of the renal cortex is due to a Langmuir-type absorption of the oxygen binding of PEG(HSA-FeP); the Hill's coefficient (n) is 1.0. It is well known that human RBC has an allosteric effect on the oxygen-binding equilibrium ($n = 3.0$) [14]. If the oxygen partial pressure of the peripheral tissue dramatically decreased, a significant difference would appear in the OTEs of PEG(HSA-FeP) and RBC. For instance, in this experimental set up, the 30% blood-bleeding induced extreme low-oxygen partial pressures in the renal cortex (3.7 mmHg) and muscle tissue (9.3 mmHg), and also the high P_{aO_2} of 134 mmHg. In this situation, the RBC shows maximum OTE of 94–99%, because of the allosteric effect on the oxygen binding to Hb. On the contrary, PEG(HSA-FeP) demonstrated a 57–70% OTE (Fig. 5). This would provide an insufficient oxygen supply to the renal cortex and muscle tissues to some degree, even though the increased $P_{tO_2}(R)$ and $P_{tO_2}(M)$ after the infusion of PEG(HSA-FeP) remained constant for 120 min during the experiment period.

5. Conclusions

The administration of the PEGylated albumin-heme solution into the acute anemia rat model showed a

significant efficacy on (i) resuscitation of hemorrhagic shock, (ii) improving the blood circulation, and (iii) oxygen delivery throughout the body. The overall restoration ability of PEG(HSA-FeP) occurred to almost the same extent as that of the RBC suspension. All the systemic responses imply that the PEG(HSA-FeP) solution can be used as a valuable oxygen-carrying plasma expander. The relatively low improvement in $P_{tO_2}(R)$ and $P_{tO_2}(M)$ may be due to the absence of the allosteric effect of the oxygen binding to FeP ($n = 1.0$). It is also of great interest to design a cooperative oxygen-binding system using a synthetic molecule. This may be an essential issue for constructing the next generation albumin-based artificial RBC substitutes.

Acknowledgements

This work was supported by Health Science Research Grants (Regulatory Science) of the MHLW Japan, Grant-in-Aid for Scientific Research (No. 16350093) from JSPS, and Grant-in-Aid for Exploratory Research (No. 16655049) from MEXT Japan.

References

- [1] Riess JG. Oxygen carriers ("blood substitute")—raison d'être, chemistry, and some physiology. *Chem Rev* 2001;101:2797–919.
- [2] Squires JE. Artificial blood. *Science* 2002;295:1002–5.
- [3] Winslow R. Blood substitutes. London: Elsevier; 2005.
- [4] Gould SA, Moore EE, Moore FA, Haenel JB, Burch JM, Sehgal H, et al. The clinical utility of human polymerized hemoglobins as a blood substitute following acute trauma and urgent surgery. In: Tsuchida E, editor. Blood substitutes. Present and future perspectives. Amsterdam: Elsevier; 1998. p. 41–54.
- [5] Vandergriff KD, Malavalli A, Wooldridge J, Lohman J, Winslow RM. MP4, a new nonvasoactive PEG-Hb conjugate. *Transfusion* 2003;43: 509–16.
- [6] Sakai H, Hara H, Yuasa M, Tsai AG, Takeoka S, Tsuchida E, et al. Molecular dimensions of Hb-based O_2 carriers determine constriction of resistance arteries and hypertension. *Am J Physiol Heart Circ Physiol* 2000;279:H908–15.
- [7] Sakai H, Horinouchi H, Masada Y, Takeoka S, Ikeda E, Takaori M, et al. Metabolism of hemoglobin-vesicles (artificial oxygen carriers) and their influence on organic functions in a rat model. *Biomaterials* 2003;25:4317–25.
- [8] Huang Y, Komatsu T, Wang RM, Nakagawa A, Tsuchida E. Poly(ethylene glycol)-conjugated human serum albumin including iron porphyrins: surface modification improves the O_2 -transporting ability. *Bioconjugate Chem* 2006;17:393–8.
- [9] Sumi A, Ohtani W, Kobayashi K, Ohmura T, Yokoyama K, Nishida M, et al. Purification and physicochemical properties of recombinant human serum albumin. In: Rivat C, Stoltz J-F, editors. Biotechnology of blood proteins, vol. 227. Montrouge: John Libbey Eurotext; 1993. p. 293–8.
- [10] Komatsu T, Matsukawa Y, Tsuchida E. Effect of heme structure on O_2 -binding properties of human serum albumin-heme hybrids: intramolecular histidine coordination provides a stable O_2 -adduct complex. *Bioconjugate Chem* 2002;13:397–402.
- [11] Komatsu T, Yamamoto H, Huang Y, Horinouchi H, Kobayashi K, Tsuchida E. Exchange transfusion with synthetic oxygen-carrying plasma protein "albumin-heme" into an acute anemia rat model

- after seventy-percent hemodilution. *J Biomed Mater Res* 2003;71A: 644–51.
- [12] Tsai AG, Vandegriff KD, Intaglietta M, Winslow RM. Targeted O₂ delivery by low-P₅₀ hemoglobin: a new basis for O₂ therapeutics. *Am J Physiol Heart Circ Physiol* 2003;285:H1411–9.
- [13] Cabrales P, Tsai AG, Intaglietta M. Microvascular pressure and functional capillary density in extreme hemodilution with low and high plasma viscosity expander. *Am J Physiol Heart Circ Physiol* 2004;287:H363–73.
- [14] Antonini E, Brunori M. Hemoglobin and myoglobin in their reactions with ligands. In: Neuberger A, Tatum EL, editors. North-Holland research monographs. *Frontiers of biology*, vol. 21. Amsterdam: North-Holland Publisher Co.; 1971. p. 153–87.

Poly(ethylene glycol)-conjugated Phospholipids in Aqueous Micellar Solutions: Hydration, Static Structure, and Interparticle Interactions

Takaaki Sato,[†] Hiromi Sakai,[†] Keitaro Sou,[†] Richard Buchner,[‡] and Eishun Tsuchida^{†,*}

Advanced Research Institute for Science and Engineering, Waseda University, Okubo 3-4-1, Shinjuku-ku, Tokyo 169-8555, Japan, and Institut für Physikalische und Theoretische Chemie, Universität Regensburg, D-93040 Regensburg, Germany

Received: October 25, 2006; In Final Form: November 30, 2006

By means of dielectric relaxation spectroscopy (DRS) and small-angle X-ray scattering (SAXS), we have investigated hydration behavior, solvent dynamics, and static structures of aqueous solutions of poly(ethylene glycol)-conjugated distearoyl phosphatidylethanolamine (DSPE-PEG) (molecular weight of PEG: $M_{\text{PEG}} = 2000, 5000, \text{ and } 12\,000 \text{ Da}$). A quantitative analysis of the bulk-water relaxation amplitude revealed the effective hydration number of a DSPE-PEG molecule per ethylene oxide monomer unit to be $\sim 5.0\text{--}5.5$, virtually independent of M_{PEG} . The overall hydration number of a DSPE-PEG molecule is ca. 20% higher than that of the corresponding normal PEG (without DSPE). This is attributed to both hydration of a charged head group of phosphoric acid in DSPE and a packing effect of PEG chains into micellar structures. The pair-distance distribution functions, $p(r)$, extracted from the GIFT analysis of SAXS intensities show that the DSPE-PEGs form spherical-like micelles in water having the maximum diameter of $\sim 16, 22, \text{ and } 31 \text{ nm}$, respectively, for $M_{\text{PEG}} = 2000, 5000, \text{ and } 12\,000 \text{ Da}$ and nearly identical aggregation numbers of $72 (\pm 10\%)$. The DSPE-PEG micelles behave as charged colloids whose interparticle interaction potential can be approximated by the screened Coulomb potential model. The extracted pair correlation function $g(r)$ demonstrates that both electrostatic repulsion induced by the charged head group and excluded volume effects of the fully hydrated PEG layer contribute to repulsive interactions among the PEG-lipid micelles. This should be a key factor for the function of PEG lipids as a stabilizer of liposomes.

1. Introduction

The hydrophobic driving forces, the solvent–water mediated segregating tendency of hydrophobic molecules or units, play a vital role in various self-assembly phenomena, ranging from the formation of molecular clusters to micelles and vesicular structures.¹ One example is the phospholipid vesicle or liposome that has extensively been studied as a drug delivery system since the formation of a vesicular structure was discovered in the suspension of egg-yolk phosphatidylcholine.² Some liposomes are now approved for clinical use as antifungal or anticancer therapies.³ Poly(ethylene glycol) (PEG)-conjugated phospholipids (PEG-phospholipids) have widely been recognized as efficient stabilizers of phospholipid vesicles or liposomes.^{4–6}

They are also effective for the vesicles used to encapsulate concentrated hemoglobin (Hb-vesicles, HbV) that have been developed as an artificial oxygen carrier.⁷ Sakai, Sou, Tsuchida, and co-workers have confirmed that the surface modification of liposomes by an incorporation of PEG-phospholipids on the surface of HbV is effective for the stabilization of the vesicles. Long-term preservation of HbV dispersions is improved by suppressing the tendency for conventional liposomes to aggregate with subsequent sedimentation.^{8,9} The stabilization has also been found to be useful for biocompatibility, microcirculatory blood flow, and prolonged circulation in the blood stream.^{10–12} So far, the underlying mechanism of such stabiliza-

tion has mainly been explained in terms of the steric hindrance or the excluded volume effect of the extended and hydrated PEG chains on the surface,¹³ and the fundamental structural and physicochemical properties of PEG-phospholipids in micellar systems were studied by several authors.^{14,15} However, specific knowledge of the hydration of PEG chains in PEG-phospholipid micelles and of the geometric profiles of the micelles, that would be of cardinal importance to elucidate the stabilizing mechanism provided by PEG-phospholipids, is still rare.

Here, we investigated static structures and molecular to cooperative dynamics of aqueous solutions of a series of PEG-conjugated phospholipids, aiming at elucidating key properties that contribute to the stabilization of liposomes. The unique combination of dielectric relaxation spectroscopy (DRS) and small-angle X-ray scattering (SAXS) provides an eminent tool to investigate diverse aspects of aqueous PEG-phospholipid solutions, such as hydration behavior, solvent dynamics, static structures, and intermicellar interaction potentials.

Owing to its eminent sensitivity to all kinds of polarization fluctuations occurring in the nano- to picosecond time scales, DRS^{16–26} has proven to be a powerful method for scrutinizing the wide-ranged multifaceted dynamical properties of liquids, involving collective dynamics of solvent,^{17–19} hydration,^{20–22} micellar specific processes,^{23,24} and so on. By an elaborate least-squares fitting procedure of the complex dielectric spectrum, the relaxation times and amplitudes for polarization fluctuations of different physical origins can separately be extracted for further quantitative analysis. DRS is generally regarded as a “mature” technique, but it has only recently reached sufficient accuracy and resolution that enables successful application to

* To whom correspondence should be addressed. E-mail: eishun@waseda.jp. Phone: +81-3-5286-3120. Fax: +81-3-3205-4740.

[†] Advanced Research Institute for Science and Engineering.

[‡] Institut für Physikalische und Theoretische Chemie.

ionic and non-ionic micellar solutions typically showing multistep relaxation behavior.^{20–24}

On the one hand, SAXS^{21,27–37} is a widely applied technique to investigate the structure and interaction potential of colloids, e.g., micelles, vesicles, and proteins, whose length scale is typically within the range of 1–100 nm. The generalized indirect Fourier transformation (GIFT) technique^{32–36} developed by Glatter and co-workers in the past decade as an extension of the well-established indirect Fourier transformation (IFT) technique²⁹ has renovated situations in small-angle scattering (SAS) data analysis. GIFT allows us to access virtually model-free real space structural information on the nanoassemble systems even for the strongly interacting dense systems.

2. Experimental Section

2.1. Materials. Poly(ethylene glycol)-conjugated phospholipids, 1,2-distearoyl-*sn*-glycero-3-phosphatidylethanolamine-*N*-[monomethoxy-poly(ethylene glycol)], hereafter abbreviated as DSPE-PEG, having PEG of molar mass of 2000, 5000, and 12 000 Da and poly(ethylene glycol)s (PEGs) with molecular masses of 2000, 5000, and 12 000 Da were purchased from NOF Co. (Tokyo, Japan).

2.2. Sample Preparation. Solutions were prepared by weight from solid samples of DSPE-PEG and PEG ($M_{\text{PEG}} = 2000, 5000, \text{ and } 12\,000 \text{ Da}$) by adding Millipore (Milli-Q) water. According to the procedure of Johnsson et al., DSPE-PEG solutions were incubated at $\sim 60^\circ\text{C}$ for about 3 h. These freshly prepared solutions were kept for a half day at ambient temperature for equilibration and were immediately used for dielectric relaxation spectroscopy (DRS) and small-angle X-ray scattering (SAXS) experiments.

2.3. Dielectric Relaxation Spectroscopy (DRS). To obtain specific information about hydration of hydrophilic groups and states of water in aqueous DSPE-PEG systems from the view point of molecular dynamics, we have determined the complex dielectric spectra, $\epsilon^*(\nu) = \epsilon'(\nu) - i\epsilon''(\nu)$, of these aqueous solutions at 25°C in the frequency range $0.03 \leq \nu/\text{GHz} \leq 20$ by the use of time domain reflectometry (TDR)^{18,19} based on the Hewlett-Packard instruments HP54121A and HP54120B. All time-domain measurements and conversion of the time-domain reflected plus waveforms to the frequency-domain spectrum were made according to the previously reported procedure of Sato and Buchner.¹⁸ For selected systems, the frequency range was expanded to the millimeter-wave region by the use of A-band and E-band waveguide interferometry,²⁶ covering $27 \leq \nu/\text{GHz} \leq 89$. For the quantitative description of the experimental $\epsilon^*(\nu)$ spectra, we have tested various conceivable relaxation models based on a superposition of n Havriliak–Negami (HN) equations, or its variants, using a nonlinear least-squares fitting procedure

$$\epsilon^*(\nu) = \epsilon_\infty + \sum_{j=1}^n \frac{\Delta\epsilon_j}{[1 + (i2\pi\nu\tau_j)^{\beta_j}]^{\alpha_j}} \quad (1)$$

In these models, the j th dispersion step ($j = 1, 2, \dots, n$) is defined by its relaxation time, τ_j ($\tau_j > \tau_{j+1}$), and amplitude, $\Delta\epsilon_j$, where n is the number of the separable dispersion steps. ϵ_∞ is the infinite frequency permittivity, and α_j and β_j are the shape parameters representing asymmetric and symmetric shapes of a spectrum, respectively.

2.4. Small-Angle X-ray Scattering (SAXS). All SAXS experiments were performed using a SAXSess camera (Anton-Paar, Graz, Austria). A PW3830 X-ray generator with a long

fine focus sealed glass X-ray tube (PANalytical) was operated at 40 kV and 50 mA. A focusing multilayer optics and a block collimator provide an intense monochromatic primary beam (Cu K α radiation, $\lambda = 0.154 \text{ nm}$) with negligible background. A semi-transparent beam stop enables measurement of the attenuated primary beam at $q = 0$. The samples were filled into vacuum-tight thin quartz capillaries and set in a TCS 120 temperature-controlled sample holder unit (Anton Paar). The 2D scattered intensity distribution recorded by an imaging-plate (IP) detector was read out by a Cyclone storage phosphor system (Perkin-Elmer, USA). The 2D data were integrated into the 1D scattering function $I(q)$ as a function of the magnitude of the scattering vector

$$q = \frac{4\pi}{\lambda} \sin(\theta/2) \quad (2)$$

where θ is the total scattering angle.

All $I(q)$ data were normalized so as to have the uniform primary intensity at $q = 0$ for transmission calibration. The background scattering contributions from capillary and solvent were corrected. The absolute intensity calibration was made by using water intensity as a secondary standard.

2.5. Theoretical Basis of SAXS Data Analysis. The total scattered intensity, $I(q)$, from one-component globular particle systems can generally be formulated as

$$I(q) = n P(q) S(q) \quad (3)$$

where n is the particle density, $P(q)$ is the averaged form factor, and $S(q)$ is the static structure factor. SAXS observes the structure of nanoparticles via the convolution square (or the spatial autocorrelation function) of the electron density fluctuations

$$\gamma(r) \equiv \Delta\bar{\rho}^2(r) = \langle \Delta\bar{\rho}^2(r) \rangle = \left\langle \int_{-\infty}^{\infty} \Delta\rho(r_1) \Delta\rho(r_1 - r) dr_1 \right\rangle \quad (4)$$

where $\Delta\rho(r)$ is the electron density fluctuation at the position r , and r is the distance between two scattering centers chosen inside the particle. The so-called pair-distance distribution function (PDDF), defined as $p(r) = \gamma(r) r^2$, is an essential real-space function that contains information on the geometry (size and shape) as well as the internal density fluctuation of the particle. $P(q)$ is the reciprocal-space coordinate associated with $p(r)$, and they are connected via the Fourier transformation

$$P(q) = 4\pi \int_0^\infty p(r) \frac{\sin qr}{qr} dr \quad (5)$$

The static structure factor $S(q)$ embodies a (time-averaged) length-scale dependent (particle) density fluctuation and therefore offers information about interparticle potentials of colloidal systems. $S(q)$ is given by the Fourier transformation of the total correlation function, $h(r) = g(r) - 1$, as

$$S(q) = 1 + 4\pi n \int_0^\infty [g(r) - 1] r^2 \frac{\sin qr}{qr} dr \quad (6)$$

where $g(r)$ is the pair-correlation function. The SAXS data for aqueous DSPE-PEG solutions were analyzed by the generalized indirect Fourier transformation (GIFT) technique.

3. Results and Discussions

3.1. Dielectric Relaxation Behavior of Aqueous DSPE-PEG Solutions. In Figure 1, we present representative complex

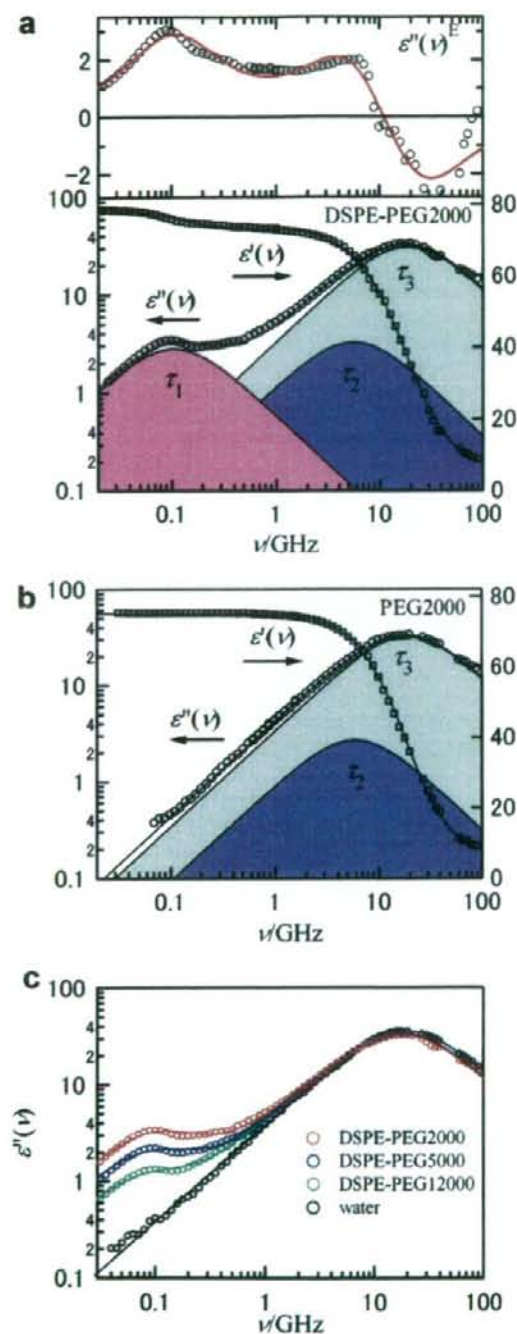


Figure 1. The complex dielectric spectra of aqueous DSPE-PEG and PEG solutions in $0.03 \leq \nu/\text{GHz} \leq 89$ at 25 ± 0.03 °C. The spectrum of aqueous DSPE-PEG at polymer concentration $c = 7.1$ g dL⁻¹ (a) and that of PEG at $c = 5.1$ g dL⁻¹ (b), corresponding to $W_{\text{PEG}} = 0.05$. In the upper panel of (a), the excess loss spectrum defined as $\epsilon''(\nu)^E = \epsilon''(\nu) - \epsilon_w''(\nu)$ is also shown, where $\epsilon_w''(\nu)$ is an ideal bulk-water loss spectrum scaled according to analytical water concentration $c_w(c)$. The comparison among DSPE-PEGs with different molecular masses of PEG, $M_{\text{PEG}} = 2000, 5000,$ and $12\,000$, at fixed $W_{\text{PEG}} = 0.05$ (c), where the water spectrum from ref 17 is also shown for comparison.

dielectric spectra of aqueous DSPE-PEG and PEG solutions at 25 °C. An addition of either DSPE-PEG or PEG to water induces a pronounced broadening of the $\epsilon''(\nu)$ spectrum on the lower frequency side of the loss peak frequency; the loss peak frequency centered at ~ 19 GHz remains virtually unchanged. The interferometry data covering up to 89 GHz confirm that there is no significant broadening of the high-frequency part of the spectrum. Thus, the low-frequency broadening is not likely due to a Cole–Cole-like relaxation-time distribution of the bulk water process but is validly attributed to the emergence of a new slow process. This also confirms the validity of the interpretation given in a recent dielectric study of Shikata et al.²² on aqueous poly(ethylene oxide)s, where the frequency coverage was limited up to 20 GHz.

The observation of an almost constant loss peak frequency is fairly different from that of the situation for, e.g., alcohol/water mixtures,^{18,19} where the loss peak frequency is continuously and rapidly sifted to lower frequencies with increasing solute concentration. The excess loss spectrum shown in the upper panel of Figure 1a indicates that, without imposing any relaxation model, two additional relaxation processes emerge upon addition of DSPE-PEG that are centered at ~ 100 MHz and ~ 5 GHz. Simultaneously, a negative excess polarization fluctuation appears for bulk-water relaxation without exhibiting a significant shift of the loss peak frequency. As for the results of the fitting procedure, we confirmed that a superposition of three Debye ($j = 3$) relaxation processes described as

$$\epsilon^*(\nu) = \epsilon_\infty + \sum_{j=1}^3 \frac{\Delta\epsilon_j}{1 + 2i\pi\nu\tau_j} \quad (7)$$

gives the best description to the spectra for all the aqueous DSPE-PEGs ($M_{\text{PEG}} = 2000, 5000,$ and $12\,000$) and a consistent set of fitting parameters, whereas the corresponding normal PEG (without DSPE) solutions show only two dispersion steps, lacking the well-pronounced 100 MHz dispersion for DSPE-PEG solutions.

Figures 2 and 3 show the relaxation times τ_j and amplitudes $\Delta\epsilon_j$ of aqueous DSPE-PEG and PEG solutions, respectively. The relaxation times of the dominating high-frequency process, τ_3 , of both DSPE-PEG and PEG solutions, are practically identical to that of the main dispersion of pure water, $\tau_D = 8.3$ ps, and almost independent of polymer concentration, c , and molecular weight, M . As demonstrated by Figure 3, the amplitude, $\Delta\epsilon_3$, smoothly decreases from that for pure water with increasing c . Thus, the assignment of the τ_3 -process is straightforward; this can clearly be attributed to the cooperative rearrangement of the hydrogen-bond network of bulk-like water. Note that, as already indicated by the negative excess loss spectrum at high-frequencies and demonstrated by Figure 3a, $\Delta\epsilon_3$ always exhibits smaller values than expected from analytical water concentration.

Neither the intermediate relaxation nor the lowest-frequency one can be attributed to the rotational diffusion of a whole DSPE-PEG micelle because τ_1 and τ_2 are too small if referring to the prediction of the Stokes–Einstein–Debye (SED) equation for the micellar radius determined from SAXS experiments (cf. Section 3.3). The τ_2 -process centered at 5–6 GHz cannot necessarily be attributed to a micelle-specific process because the features are common to DSPE-PEG and normal PEG solutions. Judging from the time scale of τ_2 , which is greater than that of bulk-water relaxation by a factor of 3 to 4, and from the behavior of $\Delta\epsilon_2$, which almost proportionally increases with c , the intermediate τ_2 -relaxation is related to cooperative

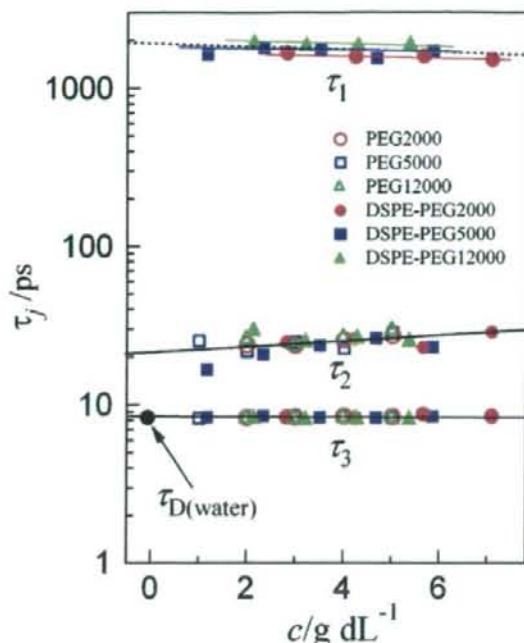


Figure 2. Dielectric relaxation times of aqueous solutions of DSPE-PEG and PEG for $M_{\text{PEG}} = 2000, 5000,$ and $12\,000$ at $25\text{ }^\circ\text{C}$ as a function of polymer concentration, c .

molecular motions in hydrated PEG layers. This is in line with the interpretation of dielectric spectra of the water/poly-(oxyethylene) alkylether system given by Schrödle et al.²⁰ The process must be highly cooperative in the densely packed hydrated PEG layer because the conformational change of the poly(oxyethylene) chains and displacement of water molecules are required to occur simultaneously, leading to the sufficiently slower dielectric relaxation time compared to that of bulk water.

The low-frequency relaxation process characterized by $\tau_1 \sim 2$ ns (loss peak frequency ~ 0.1 GHz) exists only for DSPE-PEG systems, as clearly illustrated in Figure 1. The finding indicates that the possible assignment is either to micellar- or DSPE-specific processes. As shown in Figure 3b, if we re-plot $\Delta\epsilon_1$ as a function of the molar concentration of the DSPE-PEGs, the data for different M_{PEG} perfectly collapse on the same straight line. Thus, this relaxation has to be assigned to the rotation of the charged DSPE head group. This interpretation is well supported by the data of Katzee et al.²⁴ A slightly larger τ_1 for higher M_{PEG} may reflect the stronger frictional forces for head group rotation with longer PEG chains.

3.2. Hydration of DSPE-PEG Micelles. Using the experimentally obtained bulk-water amplitude, $\Delta\epsilon_3$, we estimated the effective hydration number of the DSPE-PEG molecule and that for the corresponding PEG.

The generalized Cavell equation²⁵

$$\Delta\epsilon_i = \frac{\epsilon}{3(\epsilon + (1 - \epsilon)A_i)} \frac{N_A}{k_B T \epsilon_0} \frac{g \mu_{Gi}^2}{(1 - \alpha_i f_i)^2} c_i \quad (8)$$

connects the relaxation amplitude of the i th process, $\Delta\epsilon_i$, to the concentration of the relaxation species, c_i , where μ_{Gi} is a gas-phase dipole moment, α_i a polarizability, f_i the field factor, A_i

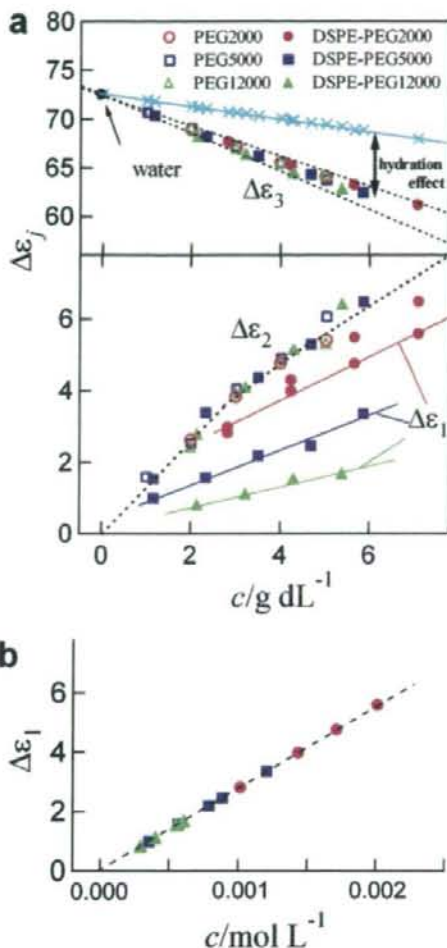


Figure 3. The relaxation amplitudes for aqueous solutions of DSPE-PEG and normal PEG with $M_{\text{PEG}} = 2000, 5000,$ and $12\,000$ at $25\text{ }^\circ\text{C}$ as a function of polymer concentration in g dL^{-1} (a) and $\Delta\epsilon_i$ replotted as a function of molar concentration of DSPE-PEG (b). A light blue colored solid line shown together with $\Delta\epsilon_3$ in panel a represents the ideal bulk-water amplitude calculated from analytical water concentration under the assumption that all water molecules in solution contribute to the bulk-water process with the same Kirkwood dipole-dipole orientational correlation factor as pure water.

the shape parameter of the reaction field, ϵ the static permittivity, g_i the dipole-dipole correlation factor, k_B the Boltzmann constant, N_A the Avogadro's number, and ϵ_0 the vacuum permittivity.

Equation 8, normalized to pure water, yields the apparent water concentration at polymer concentration c , $c_w^{\text{app}}(c)$, as

$$c_w^{\text{app}}(c) = c_w(c) \frac{g_w(c)}{g_w(0)} = \frac{\epsilon(0)(2\epsilon(c) + 1)(1 - \alpha_w f_w(c))^2 \Delta\epsilon_w(c)}{\epsilon(c)(2\epsilon(0) + 1)(1 - \alpha_w f_w(0))^2 \Delta\epsilon_w(0)} c_w(0) \quad (9)$$

where $\Delta\epsilon_w(0) = 72.5$ and $\Delta\epsilon_w(c) = \Delta\epsilon_3(c)$. Assuming a spherical water molecule ($A_i = 1/3$) having a radius $r = 0.1425$

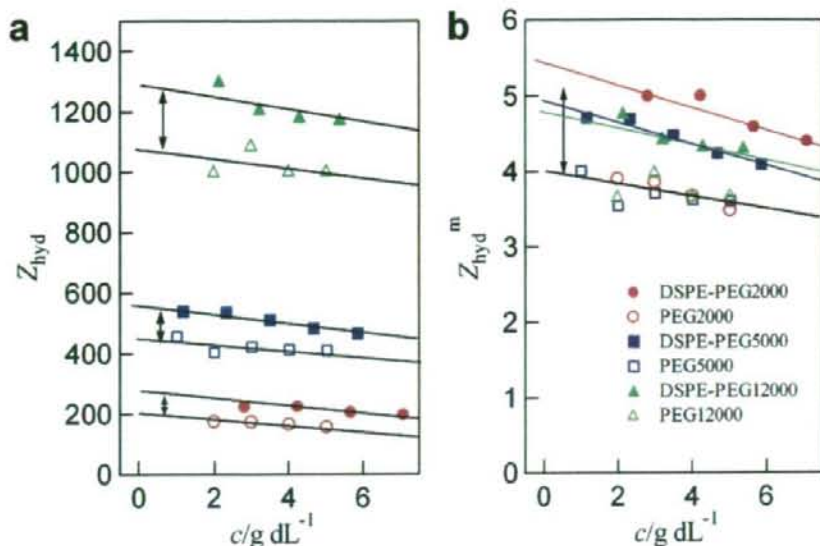


Figure 4. The effective hydration number of DSPE-PEG and PEG molecules, Z_{hyd} (a), and those per ethylene glycol monomer unit, Z_{hyd}^m (b), as a function of polymer concentration, c . These quantities are calculated from the concentration dependence of the dispersion amplitude of the bulk-water process, $\Delta\epsilon_1$. Z_{hyd} explains the number of water molecules that cannot contribute to the bulk-water process due to the hydration effects.

nm and a polarizability $\alpha_w = 1.607 \times 10^{-40} \text{ Cm}^2/\text{V}$, the apparent concentration of bulk water, $c_w^{\text{app}}(c)$, i.e., the concentration of water molecules contributing to the bulk-water relaxation process, can be deduced. We define the effective hydration number of a polymer molecule, Z_{hyd} , or that per PEG monomer unit, Z_{hyd}^m , by converting the difference between the apparent water concentration, $c_w^{\text{app}}(c)$ and analytical water concentration, $c_w(c)$, to the corresponding number of water molecules per DPSE-PEG molecule

$$Z_{\text{hyd}} = [c_w(0) - c_w^{\text{app}}(c)]/c \quad (10)$$

or that per EG monomer unit, $Z_{\text{hyd}}^m = Z_{\text{hyd}}/N$, where N is the degree of polymerization of PEG. According to the definition, using the magnitude of polarization fluctuations as a suitable measure, Z_{hyd} gives the number of water molecules that cannot contribute to the bulk-water relaxation process due to the hydration effects, which significantly slow down their intermolecular collective dynamics.

In Figure 4, Z_{hyd} and Z_{hyd}^m are plotted as a function of c . Z_{hyd} for all the investigated solutions seems to be a gradually decreasing function of c , giving the Z_{hyd}^m value of 5.0–5.5 ($c \rightarrow 0$) for all DSPE-PEGs and ~ 4 ($c \rightarrow 0$) for the corresponding PEGs as shown in Figure 4b. This demonstrates that approximately 5.0–5.5 hydrated water molecules per EG unit are as tightly bound as they show significant slowing down and consequently lose the nature of bulk water. The systematically higher Z_{hyd} values for DSPE-PEG than those for the corresponding normal PEG indicate that the difference is not likely to be related simply to the additional hydration water to the DSPE charged head group. If the difference of Z_{hyd} values was solely attributed to the hydration of the phosphatidylethanolamine group, the effect should become less pronounced with increasing M_{PEG} due to relatively smaller contribution of the DSPE head group hydration compared to dominating long-chain PEG hydration. However, we can see the significant difference,

~ 200 , for $M_{\text{PEG}} = 12\,000$, well within the accuracy of our DRS experiments/analysis. Also, a hydration number of ~ 200 for phosphatidylethanolamine group would be too large to be accommodated around the phosphatidylethanolamine group. Therefore, we conclude that not only excess hydration water molecules to the DSPE charged head group, but packing effects of PEG into a micellar structure also contribute to higher Z_{hyd} values for DSPE-PEG than those for normal PEG.

Direct numerical comparison of Z_{hyd} with literature values is rather restricted because of the lack of appropriate references. However, NMR studies of Nilsson and Lindman on poly(oxyethylene) alkylether (often abbreviated as C_jE_j) in D_2O yielded hydration numbers in the range of 5 to 6 from the translational self-diffusion constant of D_2O .³⁷ Recently, Schrödle et al.²⁰ made an extensive dielectric study on aqueous C_{12}E_5 , for both aqueous micellar and liquid crystalline phases and obtained about 3.5 to 4.0 bound water molecules per ethylene glycol (EG) monomer unit for micellar solutions. Using DRS also, Sato et al. reported that, for aqueous poly(oxyethylene) cholesteryl ether (ChE_j with $j = 10$ and 15), each oxyethylene unit is hydrated by approximately 4 to 4.5 water molecules at ambient condition.²¹ The latter evaluation is in better agreement with the present Z_{hyd}^m for the DSPE-PEGs. Apparently, there is some dependence of the oxyethylene group hydration on the chain length j for short-chain PEGs in surfactants. The present results on DSPE-PEG solutions also fit into the existing set of PEG hydration numbers. Besides the contribution of direct phosphatidylethanolamine group hydration, the slightly higher hydration number possibly reflects a different packing of DSPE-PEG molecules into the micelles compared to C_jE_j surfactants. The present Z_{hyd}^m for normal PEGs is comparable with the recent estimation of Shikata et al.²² by DRS on aqueous poly(ethylene oxide)s.

Anyway, for sufficiently long oxyethylene chains, on average 4–5 water molecules are hydrated per EG monomer unit irrespective of the type of hydrophobic group, and this number

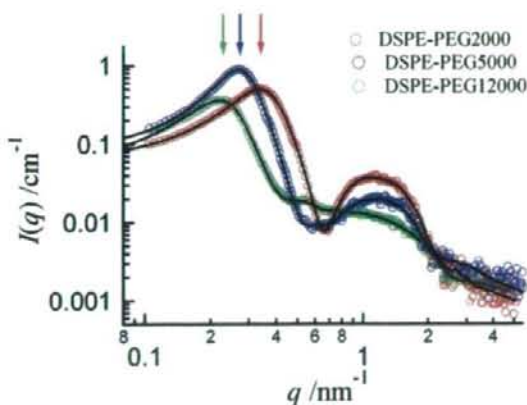


Figure 5. The absolute X-ray scattered intensities $I(q)$ of the aqueous DSPE-PEG solutions with $M_{\text{PEG}} = 2000, 5000,$ and 12000 at $W_{\text{DSPE-PEG}} = 0.04$ at 25°C . The arrows indicate the intermicellar correlation peak positions q^* , where the distance $d^* = 2\pi/q^*$ gives a measure of center-of-mass to center-of-mass distance of the micelles.

may be almost universal for all PEG-based surfactant systems. Namely, the hydration of the PEG chain is basically governed by the hydration of each EG monomer, and the total hydration number of a polymer or a micelle is approximately given by the simple sum of hydrated water molecules to each EG monomer unit. These hydrated water molecules must contribute to the compressibility of the system and repulsive interaction between the micelles inducing steric hindrance effect.

3.3. The Static Structures of DSPE-PEG Micelles. Figure 5 shows the (collimation-corrected) absolute X-ray scattered intensities $I(q)$ for the aqueous solutions of DSPE-PEG with $M_{\text{PEG}} = 2000, 5000,$ and 12000 , respectively, at a weight fraction of DSPE-PEG, $W_{\text{DSPE-PEG}} = 0.04$. The experimental $I(q)$ of all DSPE-PEG solutions clearly shows the typical features of a scattering function from globular particles. The scattering vector q^* , corresponding to the apparent low- q peak position in $I(q)$, provides a semiquantitative estimation of the averaged intermicellar (i.e., center-of-mass to center-of-mass) distance d^* without imposing any interaction potential model. If we simply extend the idea of Bragg reflections, d^* is approximated as $2\pi/q^*$. As we will show later using a quantitative $S(q)$ analysis, this leads to a small systematic overestimation of d^* . As highlighted by arrows, q^* is shifted to lower- q values with rising M_{PEG} , resulting in $d^* = 19, 24,$ and 28 nm, respectively, for $M_{\text{PEG}} = 2000, 5000,$ and 12000 . To extract more specific information about the micellar structure (size, shape, and internal core-shell structure) as well as the intermicellar interaction potentials, we need further quantitative analysis of the scattering functions. As will be shown below, the GIFT technique^{21,30–36} offers an excellent route to access to these quantities.

The SAXS data for aqueous DSPE-PEG solutions were analyzed by the generalized indirect Fourier transformation (GIFT) technique. $P(q)$ and $S(q)$ were simultaneously determined, leaving $P(q)$ model-free, whereas the choice of a plausible interaction potential model and an appropriate closure relation were necessary for $S(q)$. In Figure 6, we display the results of the GIFT analysis.

Within the framework of the mean-spherical approximation (MSA),³⁸ the direct correlation function $c(r)$ is related to the particle potential $v(r)$ as

$$c(r) = -\beta v(r) \quad (11)$$

where $\beta = 1/k_B T$. $S(q)$ for aqueous DSPE-PEG solutions is calculated assuming a screened Coulomb (Yukawa) potential

$$\beta v(r) = \frac{Z_{\text{eff}}^2 e_0^2}{4\pi\epsilon\epsilon_0 k_B T} \frac{-e^{-\kappa(r-\sigma)}}{r(1+\kappa\sigma)^2} \quad r > \sigma \quad (12)$$

$$= \infty \quad r < \sigma$$

where e_0 is the elementary charge, Z_{eff} the effective charge number of the particle, σ the hard-sphere diameter, and ϵ the static dielectric constant of the solvent. When there is no salt added, the reciprocal Debye screening length κ is determined by

$$\kappa^2 = \frac{e_0^2}{\epsilon\epsilon_0 k_B T} n Z_{\text{eff}} \quad (13)$$

where n is the number density of the particle, and nZ_{eff} is the net charge of released counter ions in unit volume. We numerically solved the Ornstein-Zernike (OZ) equation³⁹

$$h(r) = c(r) + n \int dr' c(|r-r'|) h(r') \quad (14)$$

by employing the Rogers-Young⁴⁰ (RY) closure relation

$$g(r) = e^{-\beta u(r)} \left\{ 1 + \frac{1}{f(r)} \left[e^{f(r)h(r)-c(r)} - 1 \right] \right\} \quad (15)$$

where $f(r) = 1 - \exp(-\alpha r)$ is the mixing function. When $\alpha \rightarrow 0$ and $\alpha \rightarrow \infty$, RY coincides respectively with Percus-Yevick⁴¹ (PY) and hypernetted chain (HNC). The mixing parameter is adjusted so as to attain the self-consistency of the thermodynamic parameters calculated via the fluctuation root and the virial root.

In Figure 7, the pair-distance distribution functions, $p(r)$, for the DSPE-PEG micelles are shown, where $p(r)$ was obtained as an inverse Fourier transformation of $P(q)$. From the r -value at which $p(r)$ goes to zero, the total diameter of the DSPE-PEG micelle, the so-called D_{max} , is obtained. The low- r local maximum and minimum in $p(r)$ come essentially from the convolution of the negative and positive electron density fluctuations, respectively, of the hydrophobic core and hydrophilic shell of the micelles. It is well-established that, even when these local maximum and minimum do not clearly show up but only appear as a low- r bump due to a relatively good contrast of the core-shell structure, the distance corresponding to the inflection point located on the higher- r side of the local minimum gives a semiquantitative measure of the hydrophobic core diameter, D_C . This holds even when the micelle is highly elongated. Furthermore, the distance between the local maximum and minimum almost universally coincides with $D_C/2$, so that this point can provide a semiquantitative measure of the core radius, r_C . Accordingly, we found that, for all the investigated DSPE-PEG solutions, the deduced D_C and r_C are 5.0 and 2.5 nm, respectively, which is virtually independent of M_{PEG} . Taking molecular volumes from literatures,^{42,43} the partial volume of the hydrocarbon group of DSPE, V_{hc} , is calculated as $V_{\text{hc}} = 1.016 \text{ nm}^3$. If we estimate the aggregation number of DSPE-PEG molecules into micellar structure, according to $N_{\text{agg}} = 4\pi r_C^3 / 3V_{\text{hc}}$, we obtain $N_{\text{agg}} \sim 72$. This estimation may involve about 10% of error due to spatial resolution of our SAXS measurements and analysis, but the N_{agg} value is very close to the aggregation number of about 75 for DSPE-PEG2000 and DSPE-PEG5000 obtained by static light scattering (SLS) experiments in the pioneer work of Jonsson et al.¹⁴

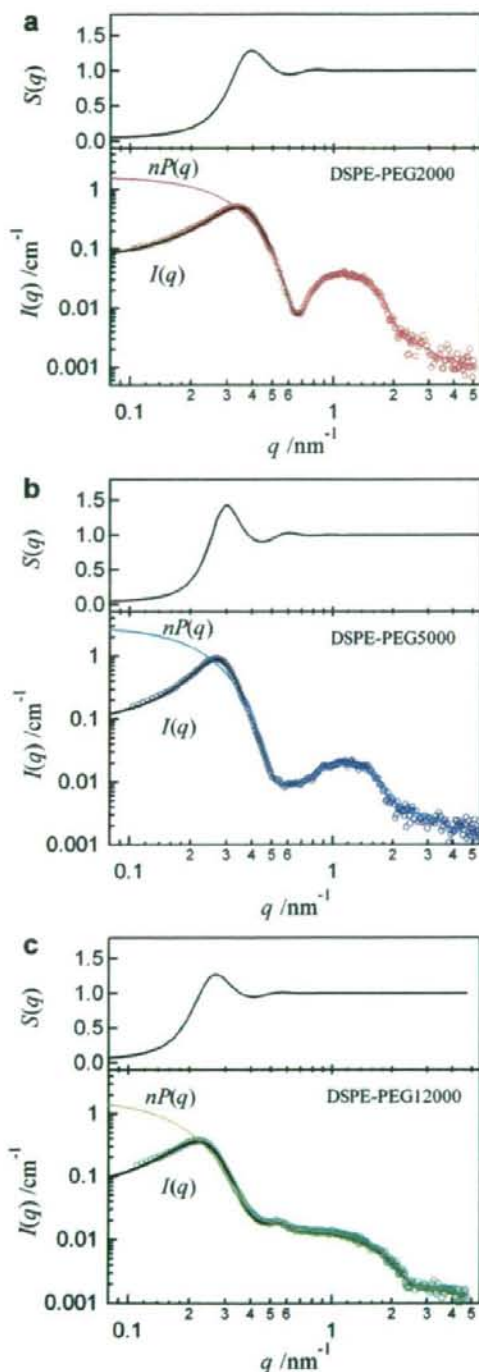


Figure 6. GIFT analysis of the X-ray scattered intensities $I(q)$ of aqueous DSPE-PEG solutions at $W_{\text{DSPE-PEG}} = 0.04$ at 25 °C for $M_{\text{PEG}} = 2000$ (a), 5000 (b), and 12 000 (c). Black solid and colored solid curves in the lower panel represent GIFT fit to $I(q)$ and the calculated form factor for n particles existing in unit volume, $nP(q)$, respectively. Also shown in the upper panel is the static structure factor $S(q)$ calculated assuming a screened Coulomb (Yukawa) potential model and Rogers–Young (RY) closure relation.

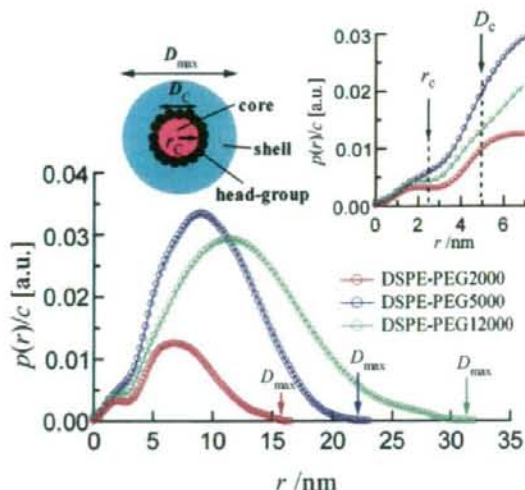


Figure 7. Particle characterization of the DSPE-PEG micelles. The normalized pair-distance distribution functions by polymer molar concentration, $p(r)/c$, for aqueous DSPE-PEG solutions with $M_{\text{PEG}} = 2000, 5000$, and 12 000 at $W_{\text{DSPE-PEG}} = 0.04$. The enlarged view in the low- r region is also presented in the inset. The two inflection points in $p(r)$ highlighted by two arrows can be the prominent measure of the core radius, r_c , and diameter, D_c , from which $r_c = 2.5 \pm 0.1$ nm is deduced for all M_{PEG} . This implies nearly identical aggregation numbers for all DSPE-PEG micelles despite the considerable variation of hydrophilic PEG chain length.

Figure 8 presents the number of water molecules existing in different states when involved into a DSPE-PEG micelle and the resulting fraction, ϕ_{bulk} , of the micelle volume occupied by bulk water. The difference between the total number of water molecules existing in the micelle (per DSPE-PEG molecule), $Z_{\text{mic}}^{\text{m}}$, estimated from micellar geometry, and the effective hydration number of a DSPE-PEG molecule, $Z_{\text{hyd}}^{\text{m}}$, provides the number of water molecules that still preserve the nature of bulk water, despite penetrating the area of the PEG hydrophilic groups of the micellar structure. Those water molecules are situated in the region $r_c < r < D_{\text{max}}/2$ from the center of micelle. ϕ_{bulk} is calculated as $\phi_{\text{bulk}} = 1 - [N_{\text{agg}}(V_{\text{DSPE-PEG}} + V_{\text{hyd}})]/V_{\text{mic}}$, where $V_{\text{mic}} = 4\pi(D_{\text{max}}/2)^3/3 = \pi D_{\text{max}}^3/6$ is the micellar volume. V_{hyd} is the volume occupied by the water molecules hydrated to a DSPE-PEG molecule, deduced from DRS as shown in Figure 4a, and $V_{\text{DSPE-PEG}}$ is the molecular volume of DSPE-PEG. N_{agg} is fixed to 72.

The combined DRS/SAXS analysis clearly reveals that, as shown in the upper panel of Figure 8, a significant amount of water molecules residing inside the head group area of the micelle, indeed reaching 60–75% volume of the total volume of the micelle, still preserves the nature of bulk water. This means that the interpretation of the structure of DSPE-PEG micelles as perfect charged hard spheres (HS) of diameter D_{max} is obviously too simplified. The pronounced increase of ϕ_{bulk} with increasing M_{PEG} demonstrates that more “diluted” or compressible micelles are formed for longer PEG chains, which are essentially stretched. With increasing M_{PEG} , such an open structure will allow easier mutual penetration or overlap of the hydrated PEG layers of approaching micelles.

In Figure 9, we display the pair-correlation functions $g(r)$ for the DSPE-PEG micelles, which are deduced from $S(q)$ analysis of the GIFT procedure. In view of the above results, it is certainly not possible to reproduce SAXS data of the DSPE-PEG solutions using a hard sphere (HS) interaction potential

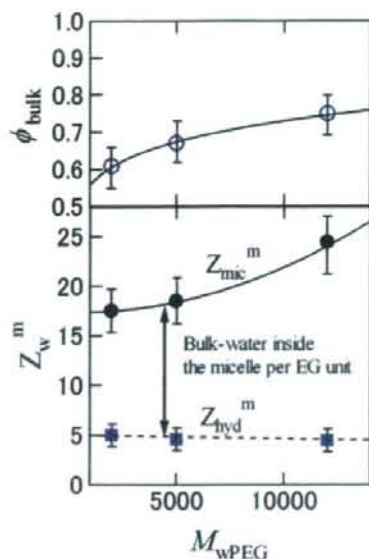


Figure 8. The amount of water molecules in different states involved into a DSPE-PEG micelle for different M_{PEG} as obtained by SAXS and DRS. The lower panel shows the total number of water molecules per EG monomer, Z_{mic}^m , that reside within the micelle (i.e., for $r < D_{mic}/2$) according to SAXS, and the effective hydration number per EG unit, Z_{hyd}^m , of a DSPE-PEG molecule deduced from DRS. Because Z_{hyd}^m represents the number of tightly bound, thus slowly relaxing water molecules, the difference between Z_{mic}^m and Z_{hyd}^m gives the number of "bulk-water" molecules (per EG monomer) in the micelle, Z_{bulk}^m . The upper panel displays the resulting fraction, ϕ_{bulk}^m , of the micelle volume occupied by bulk water.

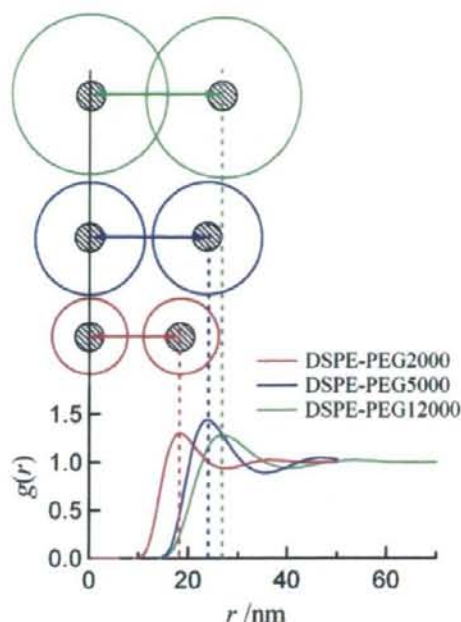


Figure 9. The pair-correlation functions $g(r)$ for the DSPE-PEG micelles ($M_{PEG} = 2000, 5000,$ and 12000) in water at $W_{DSPE-PEG} = 0.04$ as obtained by GIFT analysis of SAXS intensities $I(q)$, assuming a screened Coulomb (Yukawa) potential and the Rogers–Young (RY) closure relation. On the same spatial scale, the schematic picture of the micelles is drawn to visualize the interplay between the intermicellar (average) distance and the micellar geometry, where the shaded circle represents a hydrophobic core having $r_c \sim 2.5$ nm.

model for $S(q)$. Although we found that the shape of $S(q)$ can be approximated by a screened Coulomb (Yukawa) potential, one has to recognize that the produced $S(q)$ parameters cannot necessarily be exact. The major reason is that the charges of the DSPE head groups are not on the surface of micelles but are highly localized close to the hydrophilic/hydrophobic interface, whereas the total size of the micelles is far bigger than that of the effective charged sphere, consisting of a hydrophobic core and charged head groups. Furthermore, we cannot exactly define the static dielectric constant of the hydrated PEG layer due to its definition as a macroscopic quantity. However, its anticipated lower (effective) value compared to pure water will give rise to a larger strength but shorter screening length for the electrostatic repulsion between the effective charged spheres than one would obtain when the charged spheres were directly put into water. Of course, the excluded volume effect caused by DSPE-PEG polymers in themselves and hydrated water molecules also greatly contribute to the intermicellar repulsive interaction and osmotic compressibility of the systems. Therefore, it is apparent that a DSPE-PEG micelle cannot be treated as an ideal charged colloid in water. Nevertheless, the extracted $g(r)$, shown in Figure 9, provides an intuitive picture of spatial correlations of these micelles, giving insights into the interplay between the intermicellar distance and the micellar geometry. Note that the pronounced peak positions in $g(r)$ more or less coincide with d^* obtained with a potential model-free approach; see Figure 5. This indicates that the discussion made here is not biased by an approximate modeling of $S(q)$.

At the investigated concentrations, an overlap and interpenetration of hydrated PEG layers eventually occur among DSPE-

PEG12000 micelles, whereas a direct contact of micelles hardly takes place for DSPE-PEG2000 and DSPE-PEG5000. Owing to the low ionic strength and the relatively small micellar radii of DSPE-PEG2000 and DSPE-PEG5000, long-range electrostatic repulsion is strong enough to keep the relatively small micelles apart. Figure 9 reveals that at low ionic strength both an electrostatic repulsion induced by the charged head group and an excluded volume effect of the hydrated PEG layer contribute to the net repulsive interaction among the PEG-lipid micelles, which must be an essential factor for the function of PEG-lipids as a stabilizer of liposomes. It is naturally anticipated that, at higher ionic strength, such as a physiological condition, the steric hindrance induced by hydrated PEG chains becomes more and more dominant over the efficiently screened electrostatic repulsion for the interparticle repulsive interaction of PEG-lipid micelles. We consider that the main conclusion of Jonsson et al.¹⁴ (that the electrostatic intermicellar interactions are of minor importance for the PEG-lipid micelles compared to the repulsive forces from the steric interaction from the overlap of PEG layers) arose from the fact that all their experiments were made in 150 mM NaCl solutions. To clarify this aspect, we plan to investigate further the effect of ionic strength of solvent on the repulsive interactions of DSPE-PEG micelles. From the methodological point of view, the DRS/SAXS approach will be applicable to detailed physicochemical analyses of PEG-conjugated proteins, such as PEG-Hb and PEG-albumin.⁴⁴

4. Conclusions

We have carried out SAXS and DRS experiments on aqueous solutions of PEG-conjugated phospholipid (DSPE-PEG) with

different $M_{\text{PEG}} = 2000, 5000, \text{ and } 12\,000$ Da. The results have provided deep physical insights into hydration and static structures of the DSPE-PEG micelles. The complex dielectric spectra of these solutions exhibit typical multistep relaxation behavior, the three relaxation processes centered at $\sim 0.1, \sim 5,$ and ~ 19 GHz, being respectively assigned to the charged DSPE head group rotation, cooperative molecular motions in hydrated PEG layers, and cooperative hydrogen-bond network rearrangement dynamics of bulk water. A quantitative analysis of the bulk-water amplitude based on Cavell theory yields the effective hydration number of a DSPE-PEG molecule, $Z_{\text{hyd}} \sim 5.0$ (per ethylene oxide monomer unit), which turns out to be virtually independent of M_{PEG} . Although the extracted Z_{hyd} for DSPE-PEG, exceeding that for normal PEG by ca. 20%, involves inseparable effects of the DSPE charged head group hydration and packing of PEG chains into micellar structure, the finding clearly indicates that the hydration of PEG chains is mainly governed by the hydration of each EG monomer. In view of the pair-distance distribution functions, $p(r)$, deduced by the GIFT evaluation of the SAXS intensity distributions, the DSPE-PEGs produce nearly spherical micelles in aqueous environment, whose maximum diameters are estimated to be $\sim 16, 22,$ and 31 nm, respectively, for $M_{\text{PEG}} = 2000, 5000,$ and $12\,000$. The volume of DSPE-PEG and hydrated water molecules only accounts for 30–40% of the total micellar volume; the remaining more than 60% is occupied by bulk-like water. The structure factor $S(q)$ analysis unambiguously demonstrates that, at low ionic strength, both electrostatic repulsion induced by the charged head group and excluded volume effects of the hydrated PEG layer, significantly contribute to the net repulsive interaction among the PEG-lipid micelles, which should be a key factor for the function of PEG-lipids as a stabilizer of liposomes. Our finding does not necessarily support the generally accepted view that only the latter, excluded volume effect of hydrated PEG chains, is of major importance for the repulsive forces acting on PEG-lipid micelles. This will hold only at high ionic strength.

Acknowledgment. This work was supported in part by Health Sciences Research Grants (Research on Regulatory Science of Pharmaceuticals and Medical Devices), from the Ministry of Health, Labour, and Welfare, Japan, and Grants-in-Aid for Young Scientists (B) (No. 18740264) from the Ministry of Education, Culture, Sports, Science, and Technology (MEXT), Japan. T.S. acknowledges supports from the 21st century COE program at Waseda University funded by MEXT. The authors thank Alexander Stoppa for providing interferometer data of DSPE-PEG and PEG solutions. Professor Kenji Aramaki and late Professor Hironobu Kunieda are gratefully appreciated for their kind help for SAXS measurements. Some of the PEG-derivatives were kindly provided by NOF Co.

References and Notes

- (1) Chandler, D. *Nature* **2005**, *437*, 640.
- (2) Bangham, A. D.; Horne, R. W. *J. Mol. Biol.* **1964**, *12*, 660.
- (3) Torchilin, V. P. *Nat. Rev. Drug Discovery* **2005**, *4*, 145.
- (4) Klibanov, A. L.; Maruyama, K.; Torchilin, V. P.; Huang, L. *FEBS Lett.* **1990**, *268*, 235.

- (5) Yoshioka, H. *Biomaterials* **1991**, *12*, 861.
- (6) Mobed, M.; Chang, T. M. S. *Biomaterials* **1998**, *19*, 1167.
- (7) Tsuchida, E., Ed. *Blood Substitutes, Present and Future Perspectives*; Elsevier Science S.A.: Lausanne, Switzerland, 1998.
- (8) Sakai, H.; Tomiyama, K. I.; Sou, K.; Takeoka, S.; Tsuchida, E. *Bioconjugate Chem.* **2000**, *11*, 425.
- (9) Sou, K.; Endo, T.; Takeoka, S.; Tsuchida, E. *Bioconjugate Chem.* **2000**, *11*, 372.
- (10) Sakai, H.; Tsai, A. G.; Kerger, H.; Park, S. I.; Takeoka, S.; Nishide, H.; Tsuchida, E.; Intaglietta, M. *J. Biomed. Mater. Res.* **1998**, *40*, 66.
- (11) Sakai, H.; Takeoka, S.; Park, S. I.; Kose, T.; Nishide, H.; Izumi, Y.; Yoshizu, A.; Kobayashi, K.; Tsuchida, E. *Bioconjugate Chem.* **1997**, *8*, 23.
- (12) Sou, K.; Klipper, R.; Goins, B.; Tsuchida, E.; Phillips, W. T. *J. Pharmacol. Exp. Ther.* **2005**, *312*, 702.
- (13) Kenworthy, A. K.; Hristova, K.; Needham, D.; McIntosh, T. J. *Biophys. J.* **1995**, *68*, 1921.
- (14) Johansson, M.; Hansson, P.; Edwards, K. J. *Phys. Chem. B* **2001**, *105*, 8420.
- (15) Koynova, R.; Tenchov, B.; Rapp, G. *Colloids Surf., A* **1999**, *149*, 571.
- (16) Buchner, R.; Barthel, J. *Annu. Rep. Prog. Chem., Sect. C: Phys. Chem.* **2001**, *97*, 349.
- (17) Fukasawa, T.; Sato, T.; Watanabe, J.; Hama, Y.; Kunz, W.; Buchner, R. *Phys. Rev. Lett.* **2005**, *95*, 197802.
- (18) Sato, T.; Buchner, R. *J. Phys. Chem. A* **2004**, *108*, 5007.
- (19) Sato, T.; Buchner, R. *J. Chem. Phys.* **2003**, *119*, 10789.
- (20) Schrödle, S.; Hefter, G.; Kunz, W.; Buchner, R. *Langmuir* **2006**, *22*, 924.
- (21) Sato, T.; Hossain, M. d. K.; Acharya, D. P.; Glatter, O.; Chiba, A.; Kunieda, H. *J. Phys. Chem. B* **2004**, *108*, 12927.
- (22) Shikata, T.; Takahashi, R.; Sakamoto, A. *J. Phys. Chem. B* **2006**, *110*, 8941.
- (23) Fernandez, P.; Schrödle, S.; Buchner, R.; Kunz, W. *ChemPhysChem* **2003**, *4*, 1065.
- (24) Kaatze, U.; Gopel, K.-D.; Pottel, R. *J. Phys. Chem.* **1985**, *89*, 2565.
- (25) Barthel, J.; Hetzenauer, H.; Buchner, R. *Ber. Bunsen Ges.* **1992**, *96*, 1424.
- (26) Barthel, J.; Bachhuber, K.; Buchner, R.; Hetzenauer, H.; Kleebauer, K. *Ber. Bunsen Ges.* **1991**, *95*, 853.
- (27) Glatter, O.; Kratky, O. *Small-Angle X-ray Scattering*; Academic: London, 1982.
- (28) Lindner, P.; Zemb, Th., Eds. *Neutron, X-Ray and Light Scattering*; North-Holland: Amsterdam, 1991.
- (29) Glatter, O. *J. Appl. Crystallogr.* **1997**, *10*, 415.
- (30) Strey, R.; Glatter, O.; Schubert, K. -V.; Kaler, E. W. *J. Chem. Phys.* **1996**, *105*, 1175.
- (31) Shrestha, L. K.; Sato, T.; Acharya, D. P.; Iwanaga, T.; Aramaki, K.; Kunieda, H. *J. Phys. Chem. B* **2006**, *110*, 12266.
- (32) Brunner-Popela, J.; Glatter, O. *J. Appl. Crystallogr.* **1997**, *30*, 431.
- (33) Weyerich, B.; Brunner-Popela, J.; Glatter, O. *J. Appl. Crystallogr.* **1999**, *32*, 197.
- (34) Orthaber, D.; Bergmann, A.; Glatter, O. *J. Appl. Crystallogr.* **2000**, *33*, 218.
- (35) Bergmann, A.; Orthaber, D.; Scherf, G.; Glatter, O. *J. Appl. Crystallogr.* **2000**, *33*, 869.
- (36) Fritz, G.; Bergmann, A.; Glatter, O. *J. Chem. Phys.* **2000**, *113*, 9733.
- (37) Nilsson, P. G.; Lindman, B. *J. Phys. Chem.* **1983**, *87*, 4756.
- (38) Hayter, J. B.; Penfold, J. *Mol. Phys.* **1981**, *42*, 109.
- (39) Ornstein, L. S.; Zernike, F. *Proc. Sect. Sci. K. Ned. Akad. Wet.* **1914**, *17*, 793.
- (40) Rogers, F. J.; Young, D. A. *Phys. Rev. A* **1984**, *30*, 999.
- (41) Percus, J. K.; Yevick, G. J. *Phys. Rev.* **1958**, *110*, 1.
- (42) Nagle, J. F.; Tristram-Nagle, S. *Biochim. Biophys. Acta* **2000**, *1469*, 159.
- (43) Nagarajan, R.; Ruckenstein, E. *Langmuir* **1991**, *7*, 2934.
- (44) Manjula, B. N.; Tsai, A.; Upadhyay, R.; Perumalsamy, K.; Smith, P. K.; Malavalli, A.; Vandegriff, K.; Winslow, R. M.; Intaglietta, M.; Prabhakaran, M.; Friedman, J. M.; Acharya, A. S. *Bioconjugate Chem.* **2003**, *14*, 464.

Hemoglobin vesicles reduce hypoxia-related inflammation in critically ischemic hamster flap tissue

Jan A. Plock, MD; Annemarie E. Tromp, MD; Claudio Contaldo, MD; Timo Spanholtz, MD; Dubravko Sinovcic, MD; Hiromi Sakai, PhD; Eishun Tsuchida, PhD; Michael Leunig, MD; Andrej Banic, MD, PhD; Dominique Erni, MD

Objectives: The aim of this study was to investigate the effect of a highly viscous, left-shifted hemoglobin vesicle solution (HbV) on the hypoxia-related inflammation and the microcirculation in critically ischemic peripheral tissue.

Design: Randomized prospective study.

Setting: University laboratory.

Subjects: Twenty-four male golden Syrian hamsters.

Interventions: Island flaps were dissected from the back skin of anesthetized hamsters for assessment with intravital microscopy. The flap included a critically ischemic, hypoxic area that was perfused via a collateralized vasculature. One hour after completion of the preparation, the animals received an injection of 25% of total blood volume of 0.9% NaCl or NaCl suspended with HbVs at a concentration of 5 g/dL (HbV5) or 10 g/dL (HbV10).

Measurements and Main Results: Plasma viscosity was increased from 1.32 cP to 1.61 cP and 2.14 cP after the administration of HbV5 and HbV10, respectively (both $p < .01$). Both HbV solutions raised partial oxygen tension (Clark-type microprobes) in the ischemic tissue from approximately 10 torr to 17 torr ($p <$

.01), which was paralleled by an increase in capillary perfusion by $>200\%$ ($p < .01$). The 50% increase in macromolecular capillary leakage found over time in the control animals was completely abolished by the HbV solutions ($p < .01$), which was accompanied by a $>50\%$ ($p < .01$) reduction in cells immunohistochemically stained for tumor necrosis factor- α and interleukin-6 and in leukocyte counts, whereas no such changes were observed in the anatomically perfused, normoxic tissue.

Conclusions: Our study suggests that in critically ischemic, hypoxic peripheral tissue, hypoxia-related inflammation may be reduced by a top-load infusion of HbV solutions. We attributed this effect to a restoration of tissue oxygenation and an increase in plasma viscosity, both of which may have resulted in attenuation of secondary microcirculatory impairments. (Crit Care Med 2007; 35:899-905)

KEY WORDS: blood substitutes; capillary hemodynamics; capillary leakage; tumor necrosis factor- α ; interleukin-6; collateral circulation

In tissues rendered ischemic due to traumatic devascularization or arterial occlusion, hypoxia may occur when the vascular oxygen supply is no longer sufficient to cover the demand of adenosine triphosphate required to maintain normal physiologic function. Besides having a direct impact on cellular function and survival, hypoxia may induce an inflammatory response, thus causing secondary damage to the critically ischemic tissue.

Hypoxic inflammation is mediated by the activation of a large number of genes (1). In this scenario, a pivotal role has been ascribed to master regulators of hypoxic signaling, such as the hypoxia-inducible factor (HIF)-1 α and nuclear factor- κ B (1, 2). HIF-1 α accumulates under hypoxic conditions due to the attenuation of its natural degradation, which takes place under normoxic conditions at a posttranscriptional level. In addition, HIF-1 α induces

the recruitment, adhesion, infiltration, and activation of leukocytes (3, 4). Target genes for nuclear factor- κ B include the hyperacute proinflammatory cytokine tumor necrosis factor (TNF)- α (5) and the subacute proinflammatory cytokine interleukin (IL)-6 (6).

The primary approach to prevent hypoxic inflammation should be to correct the oxygen debt in the ischemic tissues. Improving vascular oxygen supply was the rationale for developing artificial oxygen carriers such as perfluorocarbons and modified hemoglobins (7, 8). In a previous series of experiments we were able to demonstrate that oxygenation and survival in collateralized, critically ischemic hamster flap tissue were improved after isovolemic hemodilution with colloidal solutions supplemented with phospholipid vesicles containing isolated, purified human hemoglobin (hemoglobin vesicles, HbVs) (9-12). Hemodilution, as well as the high viscosity and high colloid osmotic pressure of the HbV solutions, was responsible for the ben-

From the Department of Orthopedic, Plastic and Hand Surgery, Inselspital University Hospital, Berne, Switzerland (JP, AT, TS, DS, ML, AB and DE); Department of Reconstructive Surgery, University Hospital, Zurich, Switzerland (CC); and Advanced Research Institute for Science and Engineering, Waseda University, Tokyo, Japan (HS, ET).

Supported, in part, by grants 32-054092.98 and 32-065149.01 (DE) and grant 32-050771.97 (ML) from the Swiss National Foundation for Scientific Research; the Department of Clinical Research, University of Berne, Switzerland; Health Sciences Research (Research on Regulatory Science, H18-IYAKU-Ippan-021, 022) from the Ministry of Health,

Labour and Welfare, Japan (HS, ET); Grants in Aid for Scientific Research from the Japan Society for the Promotion of Science (B16300162, HS); and Oxygenix Inc.

Drs. Sakai and Tsuchida are consultants for Oxygenix, Inc., own stock and stock options in the company, and hold patents related to technologies to produce Hb vesicles. The remaining authors have not disclosed any potential conflicts of interest.

Copyright © 2007 by the Society of Critical Care Medicine and Lippincott Williams & Wilkins

DOI: 10.1097/01.CCM.0000257463.71761.97