

Fig. 1. (a) Schematic illustration of a biofuel cell sheet constructed by laminating enzyme-modified nanoengineered carbon fabric strips with a hydrogel film that retains electrolyte solutions and fructose fuel. (b) Schemes of fructose oxidation at the enzymatic anode. (c) Schemes of oxygen reduction at the enzymatic gas-diffusion cathode. (d) Schematic illustration of multi-lamination for boosting power.

(0.09 MPa), the CNT-modified strip shows hydrophilic property. Then, the CNT-modified CF strip was immersed in a stirred solution of D-fructose dehydrogenase (FDH) (EC1.1.99.11, 169.9 U mg⁻¹, ca. 140 kDa, from Gluconobacter, purchased from Toyobo Enzyme Co.) for FDH immobilization (Tominaga et al., 2009; Tsujimura et al., 2010; Miyake et al., 2011b). It has been reported that FDH works as an electrocatalyst for two-electron oxidation of fructose (Tominaga et al., 2007; Murata et al., 2009). The flavin-containing subunit of FDH accepts electrons from fructose, and transfers these electrons to the heme c-containing subunit that can electrically communicate with electrode. A geometric area of 0.564 cm² was utilized for calculation of the current density in cyclic voltammetry (CV).

2.2. Preparation of gas-diffusion carbon fabric cathodes

The preparation of the cathode basically followed the procedures used for our previous carbon particle (ketjenblack)-based BOD cathode (Miyake et al., 2011b; Haneda et al., in press). BOD is one of the multi-copper oxidases that can directly catalyze the four-electron reduction of O₂ to H₂O even without electron transfer mediators (Tsujimura et al., 2007; Wen et al., 2011). The type 1 Cu site of BOD accepts electrons from fabric electrode, and transfers these electrons to the type 2–3 cluster of BOD for O₂ reduction. A 40 μl aliquot of a 10 mg ml⁻¹ CNT solution was put on a CF strip and dried in air, followed by thoroughly washing out the surfactant by soaking in an ethanol solution for more than 1 h with stirring. The surface of the CNT-modified CF electrode was

further modified with a 0.1 ml solution of 5 mg ml⁻¹ bilirubin oxidase (BOD, EC 1.3.3.5, 2.5 U/mg, from Myrothecium) in vacuum oven (AVO-205N, purchased from AS ONE, 0.09 MPa, 35 °C). The strip was additionally coated with the CNT solution to make the surface hydrophobic. A surface area of 0.25 cm² was utilized for calculation of the current density in cyclic voltammetry (CV).

2.3. Preparation of the hydrogel films

The fructose-containing double-network (DN) hydrogel films were prepared by a three-step process (Gong, 2010; Wu and Gong, 2011): (1) single network hydrogel formation, (2) second network formation into the single network hydrogel and (3) loading of 500 mM fructose. We used stock solutions A, B and C. Solution A contains 2-acrylamido-2-methylpropane (AMPS, 1 M), N,N-methylenebisacrylamide (MBAA, 40 mM), 2-oxoglutaric acid (OA, 1 mM) and ammonium persulfate (APS, 19 mM). Solution B was a mixture of acrylamide (AAM, 4 M), OA (1 mM), NaCl (80 mM) and APS (19 mM). Solution C contains AAM (2 M), OA (1 mM) and APS (19 mM). At first, the solution A was poured into a silicone mold, and preliminarily crosslinked by UV exposure (265 nm, 8 W) for 5 h. The formed cross gel was then immersed in solution B for 14 h to prevent dramatic swelling and further irradiated with the UV lamp for 5 h to reinforce the gel in order to become a sheet. After washing with water for 24 h, the gel sheet was immersed in solution C for 14 h followed by UV irradiation (5 h) to form a DN network. Finally, the DN gel sheet was immersed in 500 mM fructose solution for 24 h.

2.4. Electrochemical measurements

The performance of the CF electrodes was analyzed by a three-electrode system (BSA, 730C electrochemical analyzer) in solution using a Ag/AgCl reference and a platinum counter electrode. The FDH-modified anodes were evaluated in stirred McIlvaine buffer (pH 5.0) containing 500 mM fructose, while the BOD-modified cathodes were used in air-saturated McIlvaine buffer (pH 5.0). The performance of a biofuel cell sheet constructed using the fructose-containing DN hydrogel film (0.5 mm thick) was evaluated from the cell voltage upon connecting with a variable external resistance between 180 Ω and 10 kΩ. The current and the power were derived from the cell voltage and the resistance. Unless otherwise indicated, the electrochemical measurements were carried out at room temperature, around 25 °C.

3. Results and discussion

3.1. Performance of FDH/CNT/CF bioanodes

Fig. 2a shows cyclic voltammograms of the FDH/CNT/CF electrodes (solid plots) at 10 mV s⁻¹ in a stirred buffer solution containing 500 mM fructose. In comparison with the FDH/CF electrode prepared without CNTs (broken line plot), the increased specific surface area produced by CNT-modification obviously increased the current density by at least an order of magnitude. In fact, the measured double-layer capacitance of the CNT-modified electrodes has a 2 orders larger value (ca. 6.7 mF cm⁻²) than that of the original CF (0.07 mF cm⁻²). The oxidation current density depended on the concentration of the Triton X-100 surfactant used for the CNT dispersion (Haneda et al., in press). The CNT dispersion with 0.5% surfactant is capable of entirely penetrating into the CF strip (see Supplementary Fig. 1b). This uniform modification with CNT would be a reason for the enhanced anode performance. In addition, the electrode

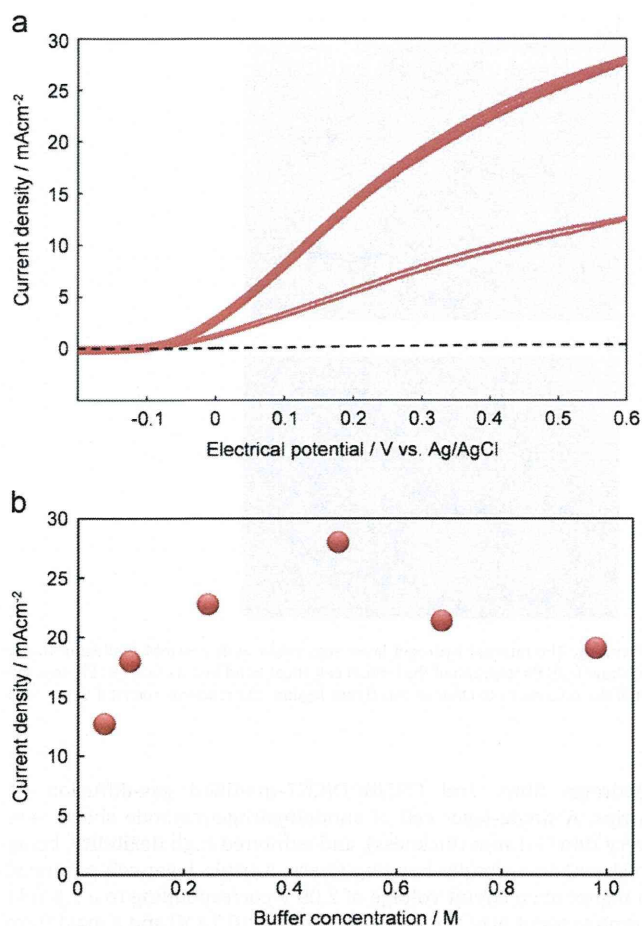


Fig. 2. (a) Cyclic voltammograms of fructose oxidation at 10 mV s^{-1} in a stirred 50 mM buffer solution (pH 5) containing 500 mM fructose. The CF strip electrodes were modified with only 10 mg ml^{-1} FDH (broken black line) or with both 10 mg ml^{-1} CNT and 10 mg ml^{-1} FDH (red line). The activity of the bioanode fabric was enhanced by optimizing the buffer concentration to 0.5 M (red bold line). (b) Current density at $0.6 \text{ V vs. Ag/AgCl}$ of the FDH anode measured in different buffer concentration. The measurements were carried out for the same FDH anode specimen. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

performance was drastically enhanced by increasing the buffer concentration in the measurement solutions from 50 mM to 0.5 M (red bold line). This is made possible by the existence of adequate buffer capacities that prevent local pH changes caused by oxidation products. Excess buffer concentration, however, lead to a low current density (see Fig. 2b). This is probably due to lowering of the enzyme activity because the enzyme is exposed by a high ionic strength solution. The maximum current of the optimized bioanode produced 15.8 mA (28.0 mA cm^{-2}) at 0.6 V using a 500 mM buffer. Even in quiescent conditions, the current reached 5.8 mA (10 mA cm^{-2}) at 0.6 V (Supplementary Fig. 2), being equivalent to that in DN hydrogel made with 500 mM McIlvaine buffer solution (pH 5.0) containing 500 mM fructose.

3.2. Performance of gas-diffusion biocathodes

Fig. 3a shows cyclic voltammograms of a BOD-modified CF cathode at 10 mV s^{-1} . The electrode strip was put on an oxygenic pH 5.0 buffer solution so as to contact the solution by the BOD-modified face (green line). The reduction current density reaches $\sim 1.9 \text{ mA cm}^{-2}$ (at 0 V) by utilizing an oxygen supply from the ambient air through the CF. Moreover, an additional CNT coating

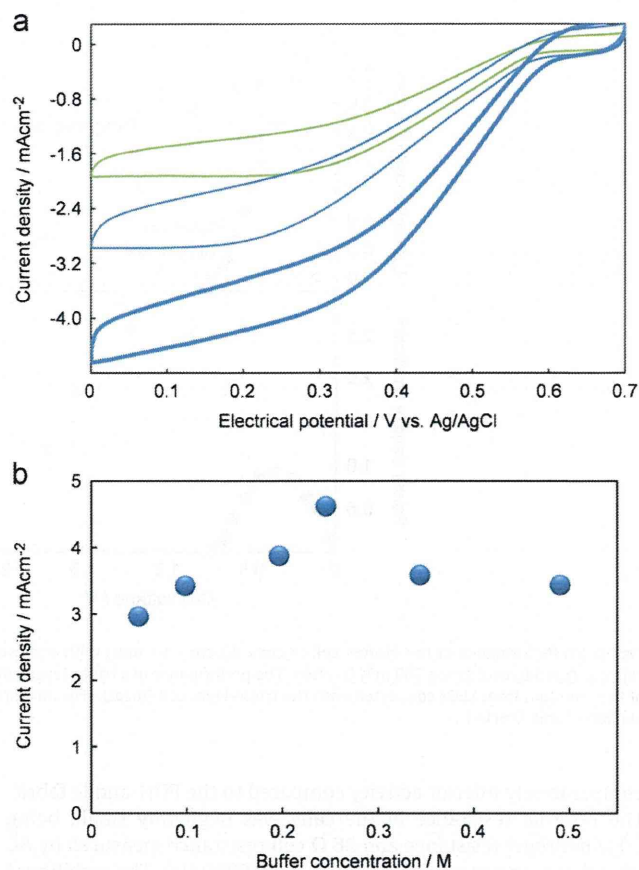


Fig. 3. (a) Cyclic voltammograms of O_2 reduction at a BOD/CNT-modified CF strip measured at 10 mV s^{-1} on the solution (green). The activity of the CF electrode was enhanced by further modification with CNT after the BOD immobilization (blue line) and by subsequent optimization of buffer concentration (bold blue). (b) Current density at 0 V vs. Ag/AgCl of the BOD cathode fabric with different buffer concentration. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

onto the BOD-modified face of the CF strip enhanced the performance further to 2.9 mA cm^{-2} . Presumably, the hydrophobic nature of that coating controls excess penetration of solution into the CF electrodes (Supplementary Fig. 3) (Miyake et al., 2011b; Haneda et al., in press). In addition to optimizing the performance of the bioanode fabric, the cathodic performance can be optimized by changing the buffer concentration (Fig. 3b); the maximum current was 4.6 mA cm^{-2} at 0 V using a 250 mM buffer condition.

3.3. Performance of the laminated biofuel cell sheets

The FDH/CNT-modified CF anode and the CNT/BOD/CNT-modified gas-diffusion CF cathode were laminated to the opposite faces of a DN hydrogel sheet (0.5 mm thick) made with 250 mM McIlvaine buffer solution (pH 5.0) containing 500 mM fructose. The enzyme-modified hydrophilic anode appeared to become moistened by blotting of the solution from the hydrogel layer. On the other hand, the O_2 reduction at the hydrophobic cathode proceeded at the three-phase boundary of the hydrogel–electrode interface. Fig. 4a shows typical examples of the cell performance. The open-circuit voltage of the cell was 0.74 V , which is similar to the difference between the potentials at which fructose oxidation and oxygen reduction start to occur in cyclic voltammograms (-0.14 V and 0.60 V in Figs. 2a and 3, respectively). The maximum power density reached 0.95 mW cm^{-2} at 0.36 V , which was determined by the BOD-cathode fabric because of its

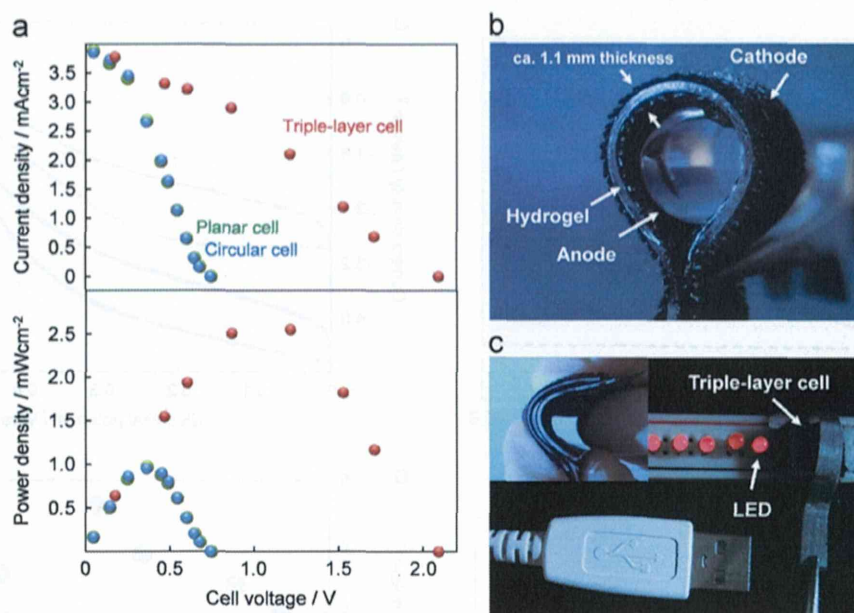


Fig. 4. (a) Performance of the biofuel cell ($1\text{ cm} \times 0.2\text{ cm} \times 1.1\text{ mm}$) with and without bending. The internal hydrogel layer was made with 250 mM McIlvaine buffer solution (pH 5.0) containing 500 mM fructose. The performance of a triple-layer cell is also shown. (b) Photograph of the biofuel cell sheet bent into a circle. (c) Photograph of the emission from LEDs connected with the triple-layer cell (inset). (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

comparatively inferior activity compared to the FDH-anode fabric. The internal resistance of the cells was negligibly small, being $10\ \Omega$ hydrogel resistance and $26\ \Omega$ cell resistance measured by AC impedance spectroscopy ($\pm 5\text{ mV}$, 1–10,000 Hz). The stability of the cells decreased extremely for few hours. Since the bioelectrodes maintained 85% performance in 500 mM fructose buffer solution (pH 5.0) for 24 h (Supporting Fig. 4), the shorter stability is due to drying of the hydrogel.

Importantly, the performance of the cell bent into a circle (blue plots) is almost identical to that of a cell that was not bent (green plots). Such high flexibility originates in the superior mechanical strength of both the fabric bioelectrodes and the DN hydrogel. As shown in Fig. 4b, the present laminar cell is thin, being only 1.12 mm thick, which also leads to a flexible character. Moreover, owing to the characteristic properties of the hydrogel, the laminar cell requires no sealing frame. Such important cell characteristics confer attractive advantage from a practical viewpoint. The application of such a laminar cell for boosting the output voltage is demonstrated in Fig. 4. The booster cell was fabricated simply by lamination of anode/hydrogel/cathode sheets (see Fig. 1d). As shown in Fig. 4a (red plots), the open-circuit voltage of the laminated cell was 2.09 V, which is 2.8-fold that of a single cell. The maximum current was quite similar to that of the single cell. These results indicate that layered cells can be connected in series without suffering from short-circuit, even without packaging. Ionic isolation between the cells could be avoided by the hydrophobicity of gas-diffusion cathodes and the solid-like property of hydrogels. The laminated cell produced a maximum power of 0.64 mW at 1.21 V (2.55 mW cm^{-2} , 6.28 mW cm^{-3}); using this level of power, we were able to light the LEDs, as demonstrated in Fig. 4c.

4. Conclusions

We have developed layered biofuel cells constructed by laminating FDH/CNT-modified CF strips, fuel-containing DN

hydrogel films, and CNT/BOD/CNT-modified gas-diffusion CF strips. A single-layer cell of anode/hydrogel/cathode sheets was very thin (1.1 mm thickness), and exhibited high flexibility, being resistant to a circular bending stress. A triple-layer cell produced a higher open circuit voltage of 2.09 V corresponding to a 2.8-fold improvement over the single cell voltage (0.74 V) and a maximum power of 0.64 mW (2.55 mW cm^{-2}) at 1.21 V, indicating a successful series-connection even without packaging of each cell. It is important to note that the output voltage can easily be tuned by changing the number of layers. Such a flexible, tunable, totally organic power source could be combined in the future with wearable electronics.

Acknowledgement

The carbon fabric and carbon nanotubes were kindly donated from Toho Tenax Co. and Bayer Co., respectively. This work was partly supported by the Noguchi Institute.

Appendix A. Supporting information

Supplementary data associated with this article can be found in the online version at <http://dx.doi.org/10.1016/j.bios.2012.05.041>.

References

- Barton, S.C., Gallaway, J., Atanassov, P., 2004. *Chemical Reviews* 104 (10), 86–4867.
- Cooney, M.J., Svoboda, V., Lau, C., Martin, G., Minteer, S.D., 2008. *Energy and Environmental Science* 1 (3), 320–337.
- Ferrigno, R., Stroock, A.D., Clark, T.D., Mayer, M., Whitesides, G.M., 2002. *Journal of the American Chemical Society* 124 (44), 12930–12931.
- Gao, F., Viry, L., Maugey, M., Poulin, P., Mano, N., 2010. *Nature Communications* 1, 2.
- Gellett, W., Kesmez, M., Schumacher, J., Akers, N., Minteer, S.D., 2010. *Electroanalysis* 7, 727–731.
- Gong, J.P., 2010. *Soft Matter*. 6 (12), 2583–2590.

- Haneda, K., Yoshino, S., Ofuji, T., Miyake, T., Nishizawa, M. *Electrochimica Acta* 1–4, in press. <http://dx.doi.org/10.1016/j.electacta.2012.01.112>.
- Heller, A., 2004. *Physical Chemistry Chemical Physics* 6 (2), 209–216.
- Holzinger, M., Le Goff, A., Cosnier, S. *Electrochimica Acta*, in press. <http://dx.doi.org/10.1016/j.electacta.2011.12.135>.
- Miyake, T., Yoshino, S., Yamada, T., Hata, K., Nishizawa, M., 2011a. *Journal of the American Chemical Society* 133 (13), 5129–5134.
- Miyake, T., Haneda, K., Nagai, N., Yatagawa, Y., Onami, H., Yoshino, S., Abe, T., Nishizawa, M., 2011b. *Energy & Environmental Science* 4, 5008–5012.
- Murata, K., Kajiya, K., Nakamura, N., Ohno, H., 2009. *Energy & Environmental Science* 2 (12), 1280–1285.
- Sakai, H., Nakagawa, T., Tokita, Y., Hatazawa, T., Ikeda, T., Tsujimura, S., Kano, K., 2009. *Energy & Environmental Science* 2 (1), 133–138.
- Tominaga, M., Shirakihara, C., Taniguchi, I., 2007. *Journal of Electroanalytical Chemistry* 610 (1), 1–8.
- Tominaga, M., Nomura, S., Taniguchi, I., 2009. *Biosensors & bioelectronics* 24 (5), 1184–1188.
- Tsujimura, S., Kamitaka, Y., Kano, K., 2007. *Fuel Cells* 7 (6), 463–469.
- Tsujimura, S., Nishina, A., Hamano, Y., Kano, K., Shiraishi, S., 2010. *Electrochemistry Communications* 12 (3), 446–449.
- Wen, D., Xu, X., Dong, S., 2011. *Energy & Environmental Science* 4 (4), 1358–1363.
- Willner, I., Yan, Y.-M., Willner, B., Tel-Vered, R., 2009. *Fuel Cells* 9 (1), 7–24.
- Wu, Z.L., Gong, J.P., 2011. *NPG Asia Materials* 3 (6), 57–64.
- Zebda, A., Gondran, C., Le Goff, A., Holzinger, M., Cinquin, P., Cosnier, S., 2011. *Nature Communications* 2, 370.

Molecularly Ordered Bioelectrocatalytic Composite Inside a Film of Aligned Carbon Nanotubes

Syuhai Yoshino, Takeo Miyake, Takeo Yamada, Kenji Hata, and Matsuhiko Nishizawa*

Molecularly ordered composites of polyvinylimidazole-[Os(bipyridine)₂Cl] (PVI-[Os(bpy)₂Cl]) and glucose oxidase (GOD) are assembled inside a film of aligned carbon nanotubes. The structure of the prepared GOD/PVI-[Os(bpy)₂Cl]/CNT composite film is entirely uniform and stable; more than 90% bioelectrocatalytic activity could be maintained even after storage for 6 d. Owing to the ideal positional relationship achieved between enzyme, mediator, and electrode, the prepared film shows a high bioelectrocatalytic activity for glucose oxidation (ca. 15 mA cm⁻² at 25 °C) with an extremely high electron-transfer turnover rate (ca. 650 s⁻¹) comparable to the value for GOD solutions, indicating almost every enzyme molecule entrapped within the ensemble (ca. 3 × 10¹² enzymes in a 1 mm × 1 mm film) can work to the fullest extent. This free-standing, flexible composite film can be used by winding on a needle device; as an example, a self-powered sugar monitor is demonstrated.

using GOD, an Os-complex polymer, and a carbon nanotube (CNT)-modified electrode.^[16] However, because of random mutual positioning in the 3D composite, many enzyme molecules are isolated from the molecular network for continuous bioelectrocatalysis. On the other hand, direct immobilization of an enzyme monolayer on the electrode surface has improved the efficiency of enzyme utilization. A striking example is the reconstituting apo-GOD on a relay-FAD monolayer linked to electrode surfaces.^[2,17–20] Since all the enzyme units are oriented in an optimal position with respect to the electrode surface, a high electron-transfer turnover rate comparable to that for bulk GOD reaction (approximately 700 s⁻¹ at 25 °C) has been achieved. However, the drawback of such 2D monolayer engineering is the lower

bioelectrocatalytic performance due to the limited amount of immobilized enzymes.

We present herein an enzyme/mediator/electrode ordered ensemble that shows both “high turnover rate” and “large catalytic current”. In order to satisfy both of these requirements, the larger amount of enzymes than monolayer should be immobilized while keeping effective contact with electrodes. We realize such ideal conditions by taking advantage of a film of well-aligned carbon nanotube forest (CNTF)^[21] consisting of single-walled CNTs arrayed with a pitch of 16 nm. The CNTF was synthesized by water-assisted chemical vapor deposition on a line-patterned Al₂O₃/Fe catalyst on silicon wafers (see the Experimental Section for details).^[21] As shown in Figure 1a, the synthesized CNTF film (1.5 mm × 1 mm) was pulled from the substrate and pinched by inverse operating tweezers (electrical lead), to produce an exposed electrode geometric area of ca. 2 mm² (sum of both faces of a 1 mm × 1 mm sheet). The thickness of the CNTF films (4, 12, or 20 μm) was determined by the width of the line-patterns of Al₂O₃/Fe catalyst. Recently, we reported that the intraspaces of the CNTF is useful for immobilization of fructose dehydrogenase and laccase, which are the direct electron transfer (DET)-type enzymes.^[22] Although there are a few recent reports that also GOD is capable of direct communication with electrodes,^[23–25] our repeated attempts to prepare a workable GOD/CNTF ensemble electrode without any mediators have failed. Therefore we developed a stepwise process to construct the molecular architecture with polyvinylimidazole-[Os(bipyridine)₂Cl] (PVI-[Os(bpy)₂Cl]; MW: 15 000) and GOD (EC:1.1.3.4; MW: 186 kDa), as illustrated in Figure 1b and 1c. The PVI-[Os(bpy)₂Cl] was synthesized according to a

1. Introduction

Controlling the electrical contact of redox enzymes with electrodes is a critical issue for enzymatic biodevices such as biofuel cells and biosensors.^[1–12] The mutual positioning between enzyme molecules, mediator molecules (not always necessary), and electrode surface determines the efficiency, reproducibility, and stability of the bioelectrocatalysis systems. A conventional engineering for accelerating the electron transfer to the redox enzymes is inclusive immobilization with mediator polymer matrices, in which the successive electron exchange between the neighboring mediator groups connects the enzyme redox center and the electrode surface.^[10–12] For example, Os-complex-pendant polymers are successful mediating matrices for glucose oxidase (GOD) and can provide glucose oxidation current at a mA cm⁻² level.^[13–16] Barton et al. reported ca. 20 mA cm⁻²

S. Yoshino, Dr. T. Miyake, Prof. M. Nishizawa
Department of Bioengineering and Robotics
Tohoku University
6-6-1 Aoba, Sendai 980-8579, Japan
E-mail: nishizawa@biomems.mech.tohoku.ac.jp

Dr. T. Yamada, Dr. K. Hata
National Institute of Advanced Industrial Science and Technology (AIST)
Tsukuba Central 5, 1-1-1 Higashi, Tsukuba, Ibaraki 308-8565, Japan
Dr. T. Miyake, Dr. T. Yamada, Dr. K. Hata, Prof. M. Nishizawa
Core Research for Evolutional Science and Technology (CREST)
Japan Science and Technology Agency (JST)
Tokyo 102-0075, Japan



DOI: 10.1002/aenm.201200422

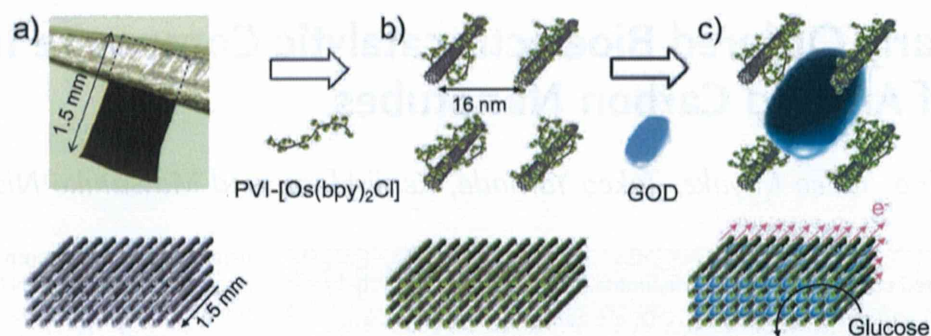


Figure 1. Schematic illustration of the stepwise process for constructing bioelectrocatalytic composite inside a CNTF film.

literature method,^[26] with a molar ratio of imidazole group to [Os(bpy)₂Cl] of 5.

2. Results and Discussion

2.1. Adsorption of PVI-[Os(bpy)₂Cl] inside CNTF Films

The CNTF film was first treated with 0.1% Triton X-100 to make it hydrophilic, and then soaked in a stirred phosphate buffer solution (PBS, pH 7.0) containing 1 mg mL⁻¹ PVI-[Os(bpy)₂Cl] at 4 °C. As shown in Figure 2a, the cyclic voltammogram (CV) of the treated CNTF showed a symmetric shape typical for adsorbed redox species.^[27] In fact, the amplitude of peak currents were proportional to the scan rates (Figure 2b). The amount of PVI-[Os(bpy)₂Cl] adsorbed within the CNTF films were estimated by

integrating the CV currents and is plotted in Figure 2c against the soaking time in the 1 mg mL⁻¹ PVI-[Os(bpy)₂Cl] solution. The amount of PVI-[Os(bpy)₂Cl] in a CNTF film increased with the soaking time and reached a maximum after 2 h. Importantly, these values are proportional to the CNTF film thickness (7.2 × 10⁻¹⁰ mol for a 12 μm thick film and 12.8 × 10⁻¹⁰ mol for a 20 μm thick film), indicating that the PVI-[Os(bpy)₂Cl] molecules can entirely and uniformly adsorbed inside the CNTF films, as illustrated in Figure 1b. A part of the free imidazole groups of the mediator polymer would adsorb on CNT surfaces via π-π interaction.^[28] The adsorption density of PVI-[Os(bpy)₂Cl] calculated using the effective inner surface area of the CNTF films (8.2 cm² for 20 μm thick film)^[21] was (1.6 ± 0.1) × 10⁻¹⁰ mol cm⁻², which is comparable with the value for a PVI-[Os(bpy)₂Cl] film adsorbed on a flat Au surface (3.2 × 10⁻¹⁰ mol cm⁻²).^[29]

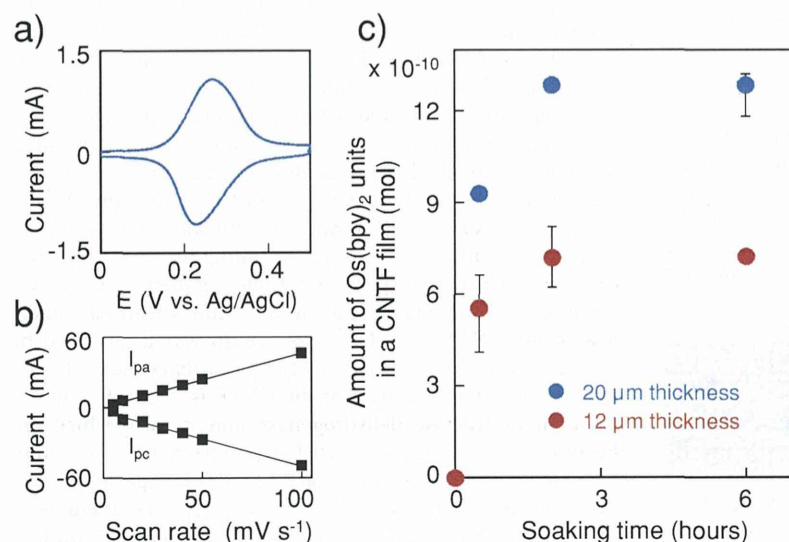


Figure 2. a) Cyclic voltammograms at 10 mV s⁻¹ of the PVI-[Os(bpy)₂Cl]-modified CNTF film (20 μm thickness) in PBS (pH 7.0). A CNTF film was soaked in the 1 mg mL⁻¹ PVI-[Os(bpy)₂Cl] PBS for 6 h. b) Redox peak currents of the CVs as a function of scan rate. c) The amount of Os(bpy)₂ unit inside a CNTF film (film thickness: 12 and 20 μm) as a function of soaking time for 1 mg mL⁻¹ PVI-[Os(bpy)₂Cl] PBS solution. The mean values (± standard deviation) of three independent specimens are given.

2.2. Electrocatalytic Activity of GOD/ PVI-[Os(bpy)₂Cl]/CNTF Ensemble Films

Subsequent loading of the enzyme GOD was conducted by immersing the PVI-[Os(bpy)₂Cl]-adsorbed CNTF films in a stirred PBS solution (pH 7.0) containing 3 mg mL⁻¹ GOD for 1 hour. Figure 3a shows the CVs of GOD/ PVI-[Os(bpy)₂Cl]/CNTF ensemble films at 10 mV s⁻¹ in a stirred 200 mM D-glucose PBS solution. The catalytic current for glucose oxidation increased in response to the thickness of CNTF films (3.7 mA cm⁻² for 4 μm thickness and 14.7 mA cm⁻² for 20 μm thickness), indicating that also GOD can entirely penetrate inside the PVI-[Os(bpy)₂Cl]-modified CNTF films. For example, the content of GOD incorporated in a 20 μm thick film was measured as ca. 0.86 μg by a C-6667 Protein Quantitation Kit, the value being a little below the case when GOD molecules (6.7 × 6.7 × 21 nm³)^[30] align to form lines in the interspace of CNTs (1.17 μg). The current density under stirred condition was enhanced to as high as 26.7 mA cm⁻² by turning up the buffer temperature to 37.5 °C. This glucose

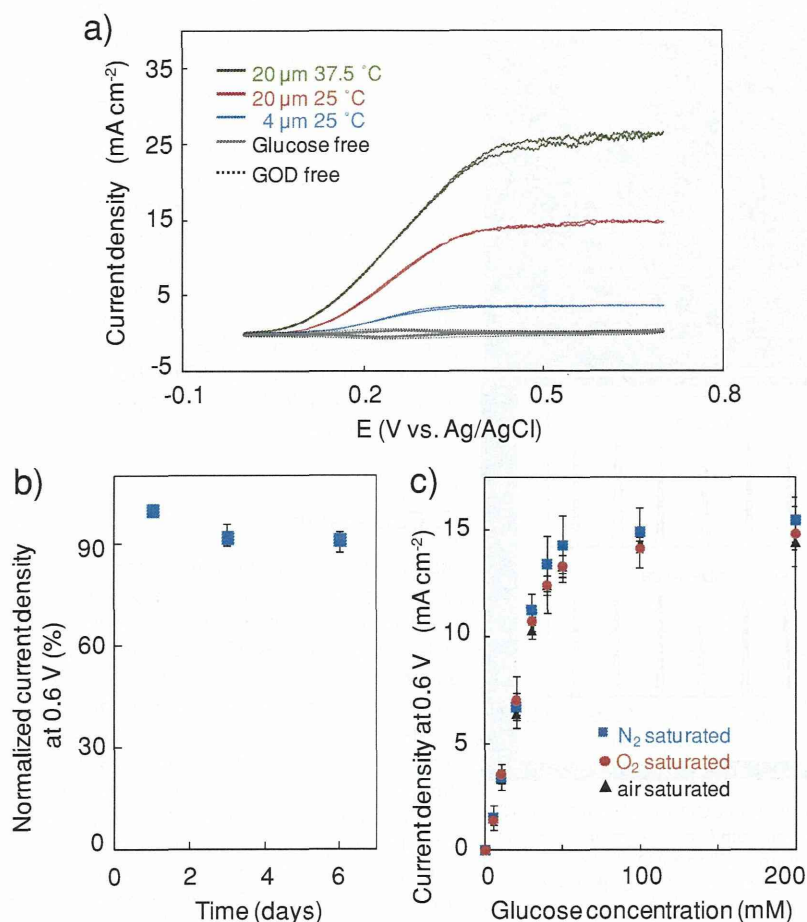


Figure 3. a) Cyclic voltammograms of GOD/PVI-Os/CNTF ensemble films at 10 mV s^{-1} in stirred air-saturated $25 \text{ }^\circ\text{C}$ (or $37.5 \text{ }^\circ\text{C}$) PBS containing 200 mM -glucose. The thicknesses of CNTF films were 4 or $20 \text{ }\mu\text{m}$. The control voltammograms without GOD and glucose are also shown. We used a total geometric area of the pinched film (2 mm^2) for the calculation of the current densities. b) The oxidation current densities at $0.6 \text{ V vs. Ag/AgCl}$ for the GOD/PVI-[Os(bby)₂Cl]/CNTF film ($20 \text{ }\mu\text{m}$ thickness) in a stirred 200 mM -glucose PBS solution, periodically measured during 6 d of storage in PBS solution. c) The current densities at 0.6 V for the $20 \text{ }\mu\text{m}$ GOD/PVI-[Os(bby)₂Cl]/CNTF film as a function of the glucose concentration, measured in O_2 , N_2 , and air-saturated stirred PBS ($\text{pH } 7.0$) solutions. The mean values (\pm standard deviation) of three independent specimens are given.

oxidation activity is comparable or superior to those previously reported using GOD.^[13–16] In a quiescent condition, the current density decreased by half, probably due to the limited mass-transfer inside the film. Importantly, more than 90% of the electrode activity could be maintained even after 6 d storage in an air-saturated PBS solution (Figure 3b), proving the stability of bioelectrocatalytic architecture with the composite of PVI-[Os(bpy)₂Cl] polymer and GOD. The anionic GOD molecules could be stably entrapped by electrostatic interaction with cationic Os-complex of the mediator polymer that is anchored on the CNT surface via π - π interaction.^[28]

The electron-transfer turnover rate for the $20 \text{ }\mu\text{m}$ thick film was calculated from the current value at $25 \text{ }^\circ\text{C}$ (0.29 mA), the Faraday constant ($96\,500 \text{ C mol}^{-1}$), the molecular weight of GOD ($186\,000 \text{ g mol}^{-1}$), and the content of GOD molecules in

a piece of the ensemble film (ca. $0.86 \text{ }\mu\text{g}$). The derived averaged turnover rate was ca. 650 s^{-1} , being comparable to that of GOD in bulk solution containing the natural electron acceptor O_2 (700 s^{-1}) at $25 \text{ }^\circ\text{C}$.^[31] These results indicate that most of ca. 3×10^{12} GOD units within the film could efficiently work to the fullest extent, presumably owing to the molecularly ordered structure of enzyme/mediator/electrode ensemble. Such a high efficiency of the present GOD electrode resulted in a resistance to oxygen inhibition, as shown in Figure 3c. The catalytic performance was almost identical in N_2 -saturated, air-saturated, and even O_2 -saturated solutions. In general, glucose oxidation with GOD-modified electrodes is often disturbed by dissolved O_2 , which is troublesome for glucose sensing.^[32,33] However, the ordered Os(bby)₂ groups in the present ensemble electrode could effectively accept the electron from GOD in preference to O_2 , resulted in excellent O_2 resistance.

2.3. Application as a Flexible Anode of Biofuel Cells

The present free-standing, bioelectrocatalytic film could be used for miniature biofuel cell devices. We demonstrate here the application of the film to a self-powered sugar indicator designed for inserting into a fruit. For indicating the glucose concentration, the net performance of the biofuel cell system should be controlled by the glucose anode. Because the oxygen in fruits is limited to a lower concentration than glucose, we employ a gas-diffusion biocathode^[34] for utilizing the abundant oxygen in air outside of the fruits (see the Experimental Section for details). Figure 4a shows the biofuel cell performance measured using 200 mM glucose PBS solution with a couple consisting of a GOD/PVI-[Os(bby)₂Cl]/CNTF film anode ($20 \text{ }\mu\text{m}$ thickness) and a cathode made from bilirubin oxidase (BOD)-modified carbon fabric ($1 \text{ cm} \times 1 \text{ cm}$). The open-circuit voltage of the cell was 0.5 V in agreement with the difference between the potentials at which glucose oxidation and oxygen reduction start to occur in cyclic voltammetry (0.1 V in Figure 3a and 0.6 V in Figure S1, see the Supporting Information). The maximum output current (0.27 mA) is almost equivalent to the maximum oxidation current at the composite anode (0.29 mA) that can be calculated by the current density in Figure 3a (14.7 mA cm^{-2}) and the electrode area of 2 mm^2 . This result indicates that the system is limited by the anode even in 200 mM glucose, a concentration that is markedly higher than that found in raw fruits (a few tens of mM). As shown in Figure 4b, a piece of GOD/PVI-[Os(bby)₂Cl]/CNTF film was wound on one lead of a light-emitting-diode (LED) device, whose blinking interval is inversely proportional

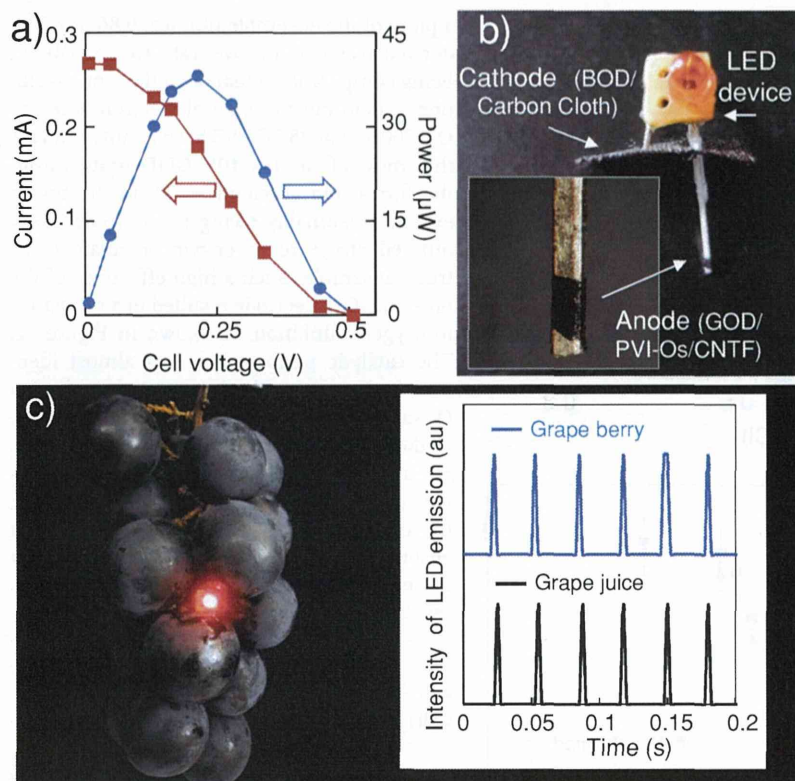


Figure 4. a) Performance of a biofuel cell composed of an anode of GOD/PVI-[Os(bby)₂Cl]/CNTF film (20 µm thickness) and a cathode of BOD-modified carbon cloth (1 cm × 1 cm) in 200 mM glucose PBS solution, measured by changing the external resistance (28 to 46 kΩ). b) Photograph of the LED-based self-powered sugar indicator, at the tip of which the GOD/PVI-[Os(bby)₂Cl]/CNTF film was wound. c) The device assembly was inserted in a grape and the LED blinking was measured (inset). The time course of LED emission, taken using an extracted juice, is also shown.

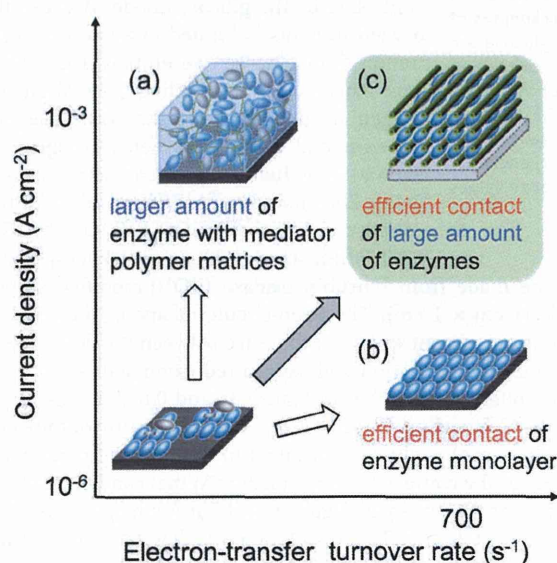


Figure 5. Scheme showing correlative characters of: a) an enzyme-film with mediator polymer matrices for larger current, b) an enzyme-monolayer electrode for higher turnover rate, and, c) the present ensemble electrode for both large current and high turnover rate.

to the power of the biofuel cell.^[35,36] The other lead was connected to the BOD-based gas-diffusion cathode. The blinking interval of the LED upon inserting the device to a grape was coincident with that for the extracted juice (Figure 4c), proving that this device could serve as a sugar indicator by simply being inserted into a grape. We confirmed that there is no corrosion reaction at the LED lead wire during the operation. The present principle of the self-powered sensor could be applied to more important blood sugar monitoring applications; we are planning to develop a GOD/PVI-[Os(bby)₂Cl]/CNTF-based device structure suitable for low-invasive insertion into a blood vessel through skins.

3. Conclusions

An amount of enzyme units larger than that in a monolayer were successfully immobilized while keeping effective electrical contact with the electrode (CNTs), as summarized in Figure 5. In particular, we have succeeded in forming an entirely uniform bioelectrocatalytic architecture with PVI-[Os(bby)₂Cl] and GOD inside a CNTF film. The voltammograms of the PVI-[Os(bby)₂Cl]-modified CNTF indicated the uniform adsorption of PVI-[Os(bpy)₂Cl] on the CNT surface via π - π interaction with the density of ca. $(1.6 \pm 0.1) \times 10^{-10}$ mol cm⁻². The subsequent GOD seemed to become stably entrapped at the interspaces of PVI-[Os(bby)₂Cl]-modified CNTs by the electrostatic interaction. Owing to the ordered positional relationship between GOD, PVI-[Os(bby)₂Cl], and CNT, the composite film showed both high activity for glucose oxidation (ca. 15 mA cm⁻²) and high electron-transfer turnover rate (ca. 650 s⁻¹), indicating almost every enzyme molecules within the film could work to the fullest extent.

4. Experimental Section

CNTF Preparation: CNTF was synthesized in a 1 inch tube furnace by water-assisted chemical vapor deposition at 750 °C with a C₂H₄ carbon source and an Al₂O₃ (10 nm)/Fe (1.0 nm) thin-film catalyst grown on silicon wafers.^[21] We used He with H₂ as the carrier gas (total flow 1000 standard cubic centimeters per minute (sccm)) at 1 atm with a controlled amount of water vapor with ethylene (100 sccm) for 10 min.

Quantitative Analysis of the Entrapped Enzymes: The quantitative analysis of GOD was conducted as explained in our previous paper.^[22] The enzyme-incorporated CNTF film was first washed and immersed in 20 mM sodium phosphate buffer (pH 9.3) containing 0.1 M sodium borate and 1% sodium cholate and dispersed with an ultrasonic homogenizer for 15 min. The GOD in the dispersion was then analyzed using a C-6667 Protein Quantitation Kit (Molecular Probes), using 5 mM (3-(4-carboxybenzoyl)-quinoline-2-carboxaldehyde) (ATTO-TAG CBQCA) and 20 mM KCN to label the enzyme with CBQCA. After 1.5 h of incubation, the fluorescent intensity was measured by a luminescent

image analyzer system (Fuji Photo Film, LAS-3000 mini), and the amount of enzyme was determined by referencing a calibration curve.

Preparation of Gas-diffusion Carbon Fabric (CF) Cathodes: The preparation of the cathode basically followed the procedures used for our previous work.^[34] A 40 μL aliquot of a 10 mg mL^{-1} multiwalled CNT solution was put on a CF strip and dried in air, followed by thoroughly washing out the surfactant by soaking in an ethanol solution for more than 1 h with stirring. The surface of the CNT-modified CF electrode was further modified with a 0.1 mL solution of 5 mg mL^{-1} bilirubin oxidase (BOD, EC 1.3.3.5, 2.5 U mg^{-1} , from Myrothecium) in a vacuum oven (0.09 MPa, 35 $^{\circ}\text{C}$). The strip was additionally coated with the CNT solution to make the surface hydrophobic.

Electrochemical Measurements: The GOD/PVI-[Os(bpy)₂Cl]/CNTF ensemble films, anchored at the edge with SUS316L fine tweezers, was analyzed by a three-electrode system (BSA, 730C electrochemical analyzer) in stirred solutions using a Ag/AgCl reference and a platinum counter electrode. The gas-diffusion cathode (BOD-modified CF strip) was put on an air-saturated solution so as to contact the solution by the BOD-modified face during cyclic voltammetry (Figure S1 in the Supporting Information). The performance of a biofuel cell constructed from an GOD-based CNTF anode and an BOD-based CF cathode was evaluated on the basis of the cell voltage upon changing the external resistance between 1 $\text{k}\Omega$ and 2 $\text{M}\Omega$ at the time step of 60 s. Unless otherwise indicated, the electrochemical measurements were carried out at room temperature (25 $^{\circ}\text{C}$).

Supporting Information

Supporting Information is available from the Wiley Online Library or from the author.

Acknowledgements

Authors express appreciation to Toho Tenax Co. for donation of the carbon fabrics and to Bayer Co. for multiwalled carbon nanotubes.

Received: June 8, 2012

Revised: June 29, 2012

Published online: August 24, 2012

- [1] I. Willner, Z. Katz, *Bioelectronics*, Wiley-VCH, Weinheim Germany **2005**.
- [2] I. Willner, Y. M. Yan, B. Willner, R. Tel-Vered, *Fuel Cells* **2009**, *1*, 7.
- [3] G. T. R. Palmore, H. Bertschy, S. H. Bergens, G. M. Whitesides, *J. Electroanal. Chem.* **1998**, *443*, 155.
- [4] R. L. Arechederra, S. D. Minter, *Fuel Cells* **2009**, *1*, 63.
- [5] W. Gellett, M. Kesmez, J. Schumacher, N. Akers, S. D. Minter, *Electroanalysis* **2010**, *22*, 727.
- [6] S. D. Minter, P. Atanassov, H. R. Luckarift, G. R. Johnson, *Mater. Today* **2012**, *15*, 166.

- [7] L. Halámková, J. Halámek, V. Bocharova, A. Szczupak, L. Alfonta, E. Katz, *J. Am. Chem. Soc.* **2012**, *134*, 5040.
- [8] D. Leecha, P. Kavanagha, W. Schuhmann, *Electrochim. Acta* **2012**, DOI:10.1016/j.electacta.2012.02.087.
- [9] M. Holzinger, A. L. Goff, S. Cosnier, *Electrochim. Acta* **2012**, DOI:10.1016/j.electacta.2011.12.135.
- [10] A. Heller, B. Feldman, *Acc. Chem. Res.* **2010**, *43*, 963.
- [11] S. G. Barton, J. Gallaway, P. Atanassov, *Chem. Rev.* **2004**, *104*, 4867.
- [12] W. Schuhmann, T. J. Ohara, H. L. Schmidt, A. Heller, *J. Am. Chem. Soc.* **1991**, *113*, 1394.
- [13] F. Mao, N. Mano, A. Heller, *J. Am. Chem. Soc.* **2003**, *125*, 4951.
- [14] F. Gao, L. Viry, M. Maugey, P. Poulin, N. Mano, *Nat. Commun.* **2010**, *1*, 2.
- [15] H. Wen, V. Nallathambi, D. Chakraborty, S. C. Barton, *Microchim. Acta* **2011**, *175*, 283.
- [16] S. C. Barton, Y. Sun, B. Chandra, S. White, J. Hone, *Electrochem. Solid-State Lett.* **2007**, *10*, B96.
- [17] Y. Xiao, F. Patolsky, E. Katz, J. F. Hainfeld, I. Willner, *Science* **2003**, *299*, 1877.
- [18] F. Patolsky, Y. Weizmann, I. Willner, *Angew. Chem., Int. Ed.* **2004**, *43*, 2113.
- [19] M. Zayats, E. Katz, I. Willner, *J. Am. Chem. Soc.* **2002**, *124*, 2120.
- [20] I. Willner, V. Heleg-Shabtai, R. Blonder, E. Katz, G. Tao, A.F. Bückmann, A. Heller, *J. Am. Chem. Soc.* **1996**, *118*, 10321.
- [21] D. N. Futaba, K. Hata, T. Yamada, T. Hiraoka, Y. Hayamizu, Y. Kakudate, O. Tanaike, H. Hatori, M. Yumura, S. Iijima, *Nat. Mater.* **2006**, *5*, 987.
- [22] T. Miyake, S. Yoshino, T. Yamada, K. Hata, M. Nishizawa, *J. Am. Chem. Soc.* **2011**, *133*, 5129.
- [23] A. Guiseppi-Elie, C. Lei, R. H. Baughman, *Nanotechnology* **2002**, *13*, 559.
- [24] A. Zebda, C. Gondran, A. L. Goff, M. Holzinger, P. Cinquin, S. Cosnier, *Nat. Commun.* **2011**, *2*, 1.
- [25] J. T. Holland, C. Lau, S. Brozik, P. Atanassov, S. J. Banta, *J. Am. Chem. Soc.* **2011**, *133*, 19262.
- [26] T. J. Ohara, R. Rajagopalan, A. Heller, *Anal. Chem.* **1993**, *65*, 3512.
- [27] A. J. Bard, L. R. Faulkner, *Electrochemical Methods: Fundamental and Applications*, Wiley, New York, **2001**, 589.
- [28] T. Roman, W. A. Dino, H. Nakanish, H. Kasai, *Eur. Phys. J. D* **2006**, *38*, 117.
- [29] Y. Wang, P. P. Joshi, K. L. Hobbs, M. B. Johnson, D. W. Schmidtke, *Langmuir* **2006**, *22*, 9776.
- [30] G. Wohlfahrt, S. Witt, J. Hendle, D. Schomburg, H. M. Kalisz, H. Hecht, *J. Acta Cryst., Sect. D: Biol. Crystallogr.* **1999**, *D55*, 969.
- [31] C. Bourdillon, C. Demaille, J. Gueris, J. Moiroux, J. M. Savebant, *J. Am. Chem. Soc.* **1993**, *115*, 12264.
- [32] J. Wang, *Electroanalysis* **2001**, *13*, 983.
- [33] B. A. Gregg, A. Heller, *Anal. Chem.* **1990**, *62*, 258.
- [34] K. Haneda, S. Yoshino, T. Ofuji, T. Miyake, M. Nishizawa, *Electrochim. Acta* **2012**, DOI: 10.1016/j.electacta.2012.01.112.
- [35] T. Hanashi, T. Yamazaki, W. Tsugawa, S. Ferri, D. Nakayama, M. Tomiyama, K. Ikebukuro, K. Sode, *Biosens. Bioelectron.* **2009**, *24*, 1837.
- [36] T. Miyake, K. Haneda, N. Nagai, Y. Yatagawa, H. Onami, S. Yoshino, T. Abe, M. Nishizawa, *Energy Environ. Sci.* **2011**, *4*, 5008.

平成 25 年度